

1524-2123-1-SM.pdf

by

Submission date: 28-Aug-2019 09:08PM (UTC+0700)

Submission ID: 1164406641

File name: 1524-2123-1-SM.pdf (1.04M)

Word count: 3815

Character count: 18034

13 3 Adsorption of Synthetic Dye by Betel Nuts Activated Carbon in a Fixed-bed Column, Experiments and Prediction of Breakthrough Curves

5
I. Cundari*, M N Fakhri, M Z Rizki

Chemical Engineering Department Faculty of Engineering Universitas Sriwijaya
Jl. Raya Palembang – Prabumulih Km.32 Indralaya, OI, Sumatera Selatan 30662

E-mail: liacundari@ft.unsri.ac.id

Abstract. Wastewater produced from textile industry contain synthetic dye that couldn't degrade naturally. The dye waste adsorbed in a continuous fixed-bed column by betel nuts activated carbon. Fixed-bed column had 60 cm of height and 2inch ID. The synthetic dye solution fed to the top of column with flow 10 ml/min. Fixed-bed column performance was evaluated with varying bed height in 5,10, and 15 cm. The increased of bed height indicated longer of breakthrough time and column life. The 15 cm of bed height result column maximum capacity(q_{exp}), % total removal, and total adsorbed dye solute (q_{total}) in the amount of 21.99 mg/g, 68.17%, dan 3299 g. The prediction of breakthrough curve has been done using kinetic adsorption study the of Thomas, Yoon-Nelson, Adam Bohart, and Bed I Breakthrough Service Time (BDST) model. The result of the experiment indicates the kinetic model of Thomas and Yoon-Nelson are the fit models, with the coefficients of regression (R^2) are 0.98 and 0.95 at the bed heights of 10 and 5cm.

1. Introduction

The Water pollution is an environmental problem that must be avoided because it causes a losses. Water pollution usually comes from industrial waste, household waste, and geographical effects. The example of industrial waste is Jumputan dye waste. The industry of jumputan cloth is usually a household industry that does not have waste processing.

The industrial waste of jumputan contains the dyestuff of organic compounds of the procion, erionyl, auramin, and rodhamin species. Dyestuff organic compounds that are channeled into the waters can reduce the dissolved oxygen levels needed by aquatic organisms because oxygen is actually used as an oxidizing dye organic compound [1].

20
One effort to overcome jumputan dye waste is by using adsorption method. Adsorption is a process that occurs when a fluid (liquid or gas) is bonded to a solid and ultimately forms a film (thin film) on the surface of the solid. In general, the adsorbent used is activated carbon. One of the active ingredients of activated carbon is Betel nuts. Betel nuts are used as activated carbon due to carbohydrate content of 60.86% which will become the main component of the activator of activated carbon (Lia Cundari, et al 2018). Activated carbon of betel nuts made by carbonization and activation process. The major components are carbon with 86.27% [2].

The adsorption kinetics is the adsorption absorpti rate by the adsorbent. In continuous-system adsorption, the calculation of the adsorption kinetics is often referred to as the calculation of the adsorption column performance. In the calculation of the performance of columns, there are several commonly used modeling models namely Thomas, Yoon Nelson, Adam-Bohart, and Bed Depth Service Time (BDST) model.

2. Research Methodology

2.1. Adsorbent preparation

Activated carbon from betel nut is Adsorbent used in this research. The carbonized betel nuts use a furnace with a temperature of 500°C, uniformed the size to 60 mesh, and activated with 0.5 M HCl solution [2].

2.2. Adsorbate preparation

Preparation The dye solution is carried out by dissolving 10 g of powdered synthetic dye and 10 ml acetic acid 15% v/v in 10 L of water with a temperature of 80-90°C.

2.3. Application of dye removal in an adsorption column

The fixed-bed adsorption column used has an inner diameter of 2 inches and a height of 60 cm and made from PVDF. The activated carbon set in the middle of wool cloth aluminum plate layer. The adsorbate fed to the top of column by using peristaltic pump with a flow rate of 10 ml/min. To evaluate the effect of bed height, the adsorbent mass in the adsorption column was varied to 50, 100, and 150 g. The variation of the adsorbent mass shows a bed height of 5, 10, and 15 cm. The solution out from the column analyzed with UV-Vis spectrofotometer.

2.4. Adsorption Column Performance

The adsorption column performance was evaluated using the breakthrough curve obtained through C_t/C_0 versus t , where C_t and C_0 were colour concentrations of output and feed in milligrams per liter [3-5]. Where Q is the volumetric flow rate (ml/min), t_{total} is the total time of dye absorption (min), and X is the adsorbent mass in column (g).

The total weight of the adsorbed dye (q_{total}) can be calculated by the equation (1)

$$q_{total} = \frac{Q}{1000} \int_{t=0}^{t_{total}} C_{ad} dt \quad (1)$$

The total dye transferred to the column (W_{total}) can be calculated by the equation (2)

$$W_{total} = \frac{C_0 Q t_{total}}{1000} \quad (2)$$

Total adsorbate removal (% removal) can be calculated by the equation (3)

$$\% \text{ removal} = \frac{q_{total}}{W_{total}} \times 100 \quad (3)$$

The adsorption capacity (q_{eq}) can be calculated by the equation (4)

$$q_{eq}(\text{exp}) = \frac{q_{total}}{X} \quad (4)$$

2.5. Adsorption Kinetic Models

Ordinary adsorption kinetic models that developed was Thomas, Yoon-Nelson, and Adam Bohart. The description of each models and the equation referred to many articles [3, 6-9].

2.5.1. Thomas Model. This model is often used to describe fixed bed columns and parameters of a column system, this model has been described by the second law of reaction kinetics without axial dispersion. Thomas model can be seen in the following equation (5). Where C_t is the concentration of adsorbate outlet (mg/l), m is the mass of adsorbent (g), K_{th} is the Thomas kinetic coefficient (ml/min mg), Q is flowrate (ml/min), and q_0 is the adsorption capacity (mg/g). The value of K_{th} and q_0 is obtained of the plot $\ln \left[\frac{C_0}{C_t} - 1 \right]$ versus t .

$$\ln \left[\frac{C_0}{C_t} - 1 \right] = \frac{K_{th} q_0 m}{Q} - K_{th} C_0 t \quad (5)$$

2.5.2. Yoon-Nelson Model. This model is developed based on the adsorption and desorption theory, this model is based on column and data parameters, and used for system per unit of component, following equation (6). K_{YN} is Yoon-Nelson adsorption constant (min^{-1}) and τ is the time required for 50% solving of adsorbate (minutes), other physical parameters are not required for this model, K_{YN} and τ values can be obtained from plot $\ln \left[\frac{C_t}{C_0 - C_t} \right]$ versus t .

$$\ln \left[\frac{C_t}{C_0 - C_t} \right] = k_{YN} t - \tau k_{YN} \quad (6)$$

2.5.3. Adam Bohart Model. This model was chosen based on the description of the fixed bed column for the initial part of the operation, this model states that the reaction is not as fast as the surface reaction theory, the following equation (7). K_{AB} is the kinetic constant of Adam-Bohart ($\text{mg} \cdot \text{min}$), N_0 and Z is concentration in mg/l and column length (cm), respectively, U_0 represents linear velocity (cm/min) determining the calculation of excessive volumetric flow rate from area bed. The values of K_{AB} and N_0 are obtained from plot $\ln \left[\frac{C_t}{C_0} \right]$ versus t .

$$\ln \left[\frac{C_t}{C_0} \right] = K_{AB} C_0 t - \frac{K_{AB} N_0 Z}{U_0} \quad (7)$$

2.5.4. Bed Depth Service Time (BDST) Model. BDST is a simple model to predict the relationship between bed depth and time (t). In process concentration and adsorption parameters, this model is only used to describe from the initial part of the absorption curve, based on a breakpoint with 10-15% saturation point. BDST focuses on parameter estimation such maximum adsorption capacity and kinetic constant, this model assumes based on adsorption speed controlled by surface reaction between adsorbate and unused capacity of adsorbent. Where C_0 is the solute concentration (mg/l), C_B is the concentration of the solute at a time of absorption (mg/l), k_a is the value of the adsorption constant (l/mg.h), N_0 is the adsorption capacity (mg/l), H is the cm column size, u is the linear flow rate from material to bed (cm/h), t is the service time of the column below and above a condition in units (h).

$$t = \frac{H N_0}{u C_0} - \frac{\ln \left(\frac{C_0}{C_B} - 1 \right)}{k_a C_0} \quad (8)$$

3. Results and Discussion

3.1. Effect of Bed Height on Breakthrough Curve

The performance of the adsorption column can be seen from the resulting breakthrough curve data, where the breakthrough curve is the ratio of the dye concentration and the concentration of the feed dye (C_t/C_0) versus time (t). The column performance test is done by varying the height of the bed. The bed height used is 5, 10, and 15 cm; comparable to 50, 100, and 150 g of adsorbent.

Seen in Figure 1, the 5 cm height of the breakthrough bed occurs most rapidly. While at bed height 15 cm breakthrough slowest occurred with saturated time 480 minutes. The results obtained have similarities to the study of Lim et al [10] and Nidheesh et al [11] which states the higher the bed the longer the breakthrough occurs. Thus the height of bed 15 cm is the optimal variable in the operational efficiency of the column. This is because the longer the breakthrough occurs the less the replacement of the adsorbent is done.

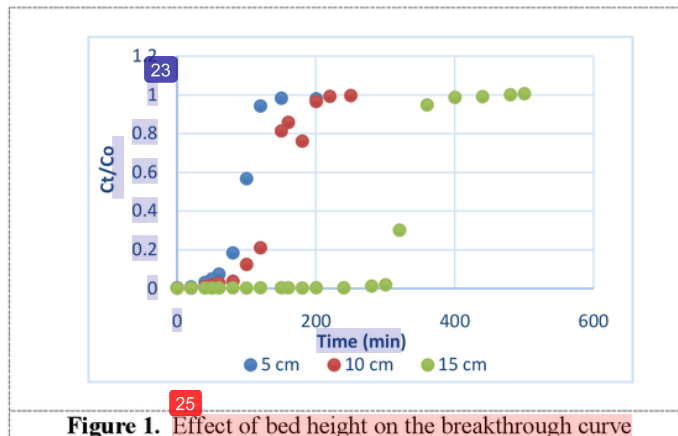


Figure 1. Effect of bed height on the breakthrough curve

3.2. Effect of Bed Height on Performance of Adsorption Column

The adsorption column parameter is one of the performance reviews of adsorption columns. The parameters reviewed are dyestuff absorption (q_{total}), total dye transferred to column (W_{total}), and maximum column capacity (q_{eq}). Of the four parameters, maximum column capacity is the most important parameter to review. This is because the maximum column capacity represents the number of solute mass attached to a certain amount of adsorbent mass.

From the calculation of column parameters (Table 1), increased bed depth increases the time and total dye absorption (q_{total}), the dyestuff that transferred to the column (W_{total}), and the total removal of dye. The increase in W_{total} value is due to an increase in adsorption time at each bed height (Table 1). The largest dye removal occurred at a bed height of 15 cm with a value of 68.17%.

Table 1. Adsorption Column Performance : Experimental Data

Bed Height (cm)	C_o (mg/L)	q_{total} (mg)	W_{total} (mg)	Dye removal (%)	$q_{exp} = q_{eq}$ (mg/g)
5	968	970.74	1936	50.14	19.41
10	968	1308.25	2420	54.06	13.08
15	968	3299.62	4840	68.17	21.99

However, in the parameters of maximum column capacity (q_{eq}), the higher the bed does not mean getting better results. This is indicated by the maximum value of column capacity at bed height 10 cm smaller than bed height 5 cm with a value of 13.08 mg/g and 19.41 mg/g respectively. The maximum value of column capacity is obtained at a bed height of 15 cm of 21.99 mg/g. The results of this study have similarities with the research Lim and Ahmad [10] in Cd(II) adsorption using dead calcareous skeletons with variations in the height of bed 1.1; 1.65; and 2.2 cm. Value (q_{eq}) at the height of bed 1.1; 1.65; and 2.2 cm respectively by 20.47; 15.68; and 26.45 mg/g.

3.3. Thomas Model

Thomas's kinetic model is a widely used adsorption kinetic model. This model aims to describe the performance of the column and predict the breakthrough curve. Thomas's model follows Langmuir's adsorption kinetics. The Thomas model ignores axial dispersions in the adsorption column during driving force following the rules of the second order reversible kinetics reaction.

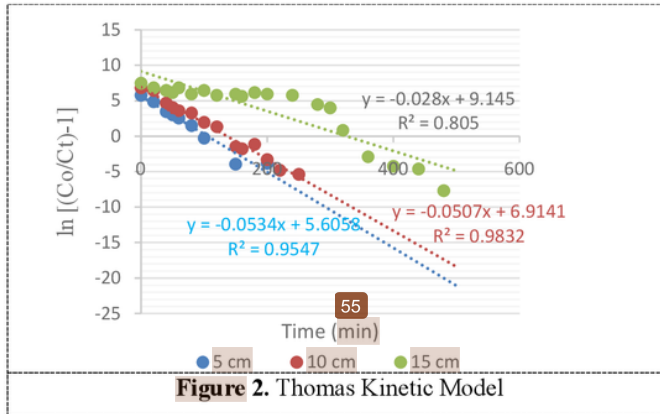


Figure 2. Thomas Kinetic Model

Based on Figure 2 Thomas model is a good modeling used in variations in bed height of 5 cm and 10 cm because it has a regression coefficient (R^2) ≥ 0.9 . While at variable height of 15 cm bed Thomas modeling is not good to use because it has regression coefficient (R^2) ≤ 0.9 . Table 2 shows the Thomas kinetics (k_{th}) getting smaller with increasing bed height.

The adsorption capacity (q_0) in the Thomas model has the same graph as the experimental result where the bed height of 15 cm has the greatest value followed by the bed height of 5 cm and 10 cm. In the study [10], the value of adsorption capacity also has the same graph between experimental data and Thomas modeling predictions. However, in the study [12], the value of adsorption capacity has unequal graphs between experimental data and predictions of Thomas models. This can be caused by the low regression coefficient value obtained that is equal to 0.818; 0.832; and 0.503 for height variations of 3, 6, and 12 cm [12]. The predicted parameter of Thomas model can be seen in Table 2.

3.4. Yoon-Nelson Model

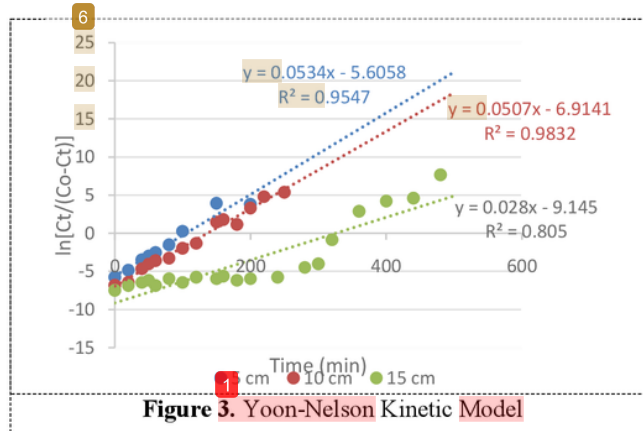


Figure 3. Yoon-Nelson Kinetic Model

Yoon-Nelson's model was developed based on the theory of adsorbate adsorption to adsorb. This modeling can be calculated directly by involving less data and column parameters. The Yoon-Nelson model can also be applied to a single component system. The k_{YN} and τ values denote Yoon-Nelson's kinetics constants (min^{-1}) and the time it takes the adsorbate to reach 50% breakthrough (min) [10].

Based on Figure 3 the value of the regression coefficient (R^2) equals the Thomas model. Therefore, Yoon-Nelson modeling is good for bed height variables of 5 cm and 10 cm and less good for height 15 cm. The Yoon-Nelson model is used to predict the time it takes the adsorbate to have 50% breakthrough (τ). Table 2 shows the estimated predictive value of time the adsorbate requires 50% breakthrough in harmony with the experimental results where the fastest breakthrough occurs in variations in bed height 5 cm, then 10 cm, and 15 cm. Meanwhile, the increase in bed height will decrease the value of Yoon-Nelson's kinetics constant (k_{YN}).

3.5. Adam Bohart Model

Adam Bohart model was chosen to describe the breakthrough curve in the initial state of operation. In the Adam-Bohart model no immediate reaction occurs such as surface reaction theory [10]. This model can be used to calculate the value of adsorption capacity (N_0) and the Adam-Bohart kinetics constant.

Figure 4 shows the resulting regression coefficient ($R^2 \leq 0.9$). The Adam-Bohart model considered imprecise to describe the adsorption kinetic. The predicted values obtained from the Adam-Bohart model show a decrease in the value of the Adam-Bohart kinetics constant (k_{AB}) and adsorption capacity (N_0) with increasing bed height (Table 2).

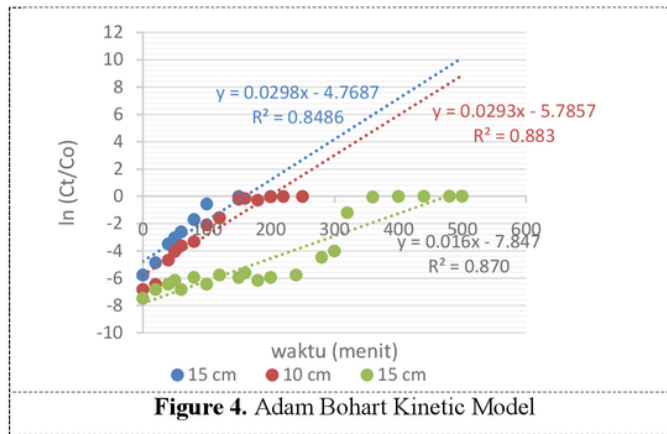



Table 2. Adsorption Kinetic Model Parameter

Tinggi Bed (cm)	Thomas		Yoon-Nelson		Adam-Bohart	
	k_{Th} (ml/min mg)	q_0 (mg/g)	k_{YN} (min^{-1})	τ (min)	k_{AB} (l/mg min)	N_0 (mg/l)
5	0.055	20.32	0.053	101.98	0,0000307	40760
10	0.052	13.35	0.050	137.78	0,00003006	39210.67
15	0.029	21.01	0.028	325.46	0,00001704	14723.33

13
3.6. Bed Depth Service Time (BDST) Model

The Bed Depth Service Time (BDST) model is a simple model to predict the relationship between bed height and service time (t) [3]. This model is only used to describe the beginning of the breakthrough curve up to 10-50% saturation. The BDST model assumes that the adsorption rate is controlled by the surface reaction between the adsorbate and the adsorbent (Goel, et al, 2005).

The value of service time on the Bed Depth Service Time (BDST) kinetics model curve (Figure 5) is the saturation point of the research. The service time data will produce prediction parameters in the form of kinetics model BDST (K_a) and adsorption capacity (N_o). From Figure 5 visible curve in the model of Bed Depth Service Time (BDST) is not good used as a model in this study because as a regression coefficient value ≤ 0.9 . The prediction of BDST kinetics value obtained is 0.0151 L / mg hour and the adsorption capacity of column is 59.18 mg/cm³. By entering a C_B value of 40% breakthrough, resulting critical height value (H_o) of 5.5 cm.

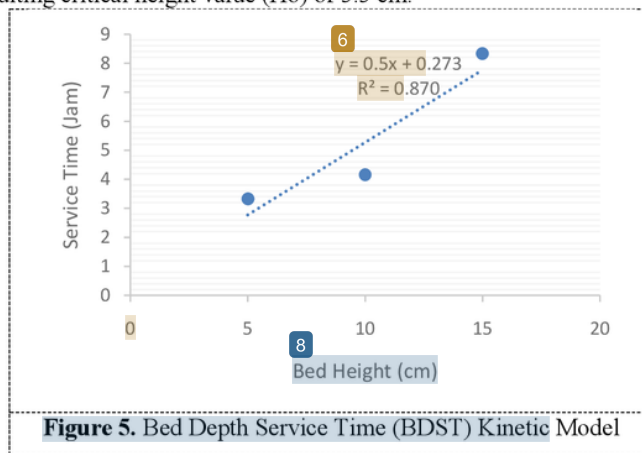


65
Table 3. Prediction Parameter of Bed Depth Service Time (BDST) Model

C_o (mg/l)	Q (ml/menit)	u (cm/jam)	N_o (mg/cm ³)	K_a (l/mg hr)	R^2	H_o (cm)
968	10	122.28	59.18	0.015	0.87	5.5


3.7. Prediction of breakthrough curve by using Kinetic Adsorption Models

10
 The prediction of the breakthrough curve can be seen in Figure 6, 7, 8 below. The prediction of the breakthrough curve is done at bed height 5 and 10 cm because both equations have the greatest regression value in all three modeling. From Figure 6 and 7, the model of Thomas and Yoon-Nelson model has almost the same value. Model Thomas and Yoon-Nelson models are also close to experimental data. This is due to the regression value of both models ≥ 0.98 . The Adam-Bohart model has a predictive value that is far from the experimental data, this may be due to the regression value in the Adam-Bohart model < 0.9 .


After viewing the model that is in accordance with the experiment, then next choose the modeling based on the existing needs. Each permoden has its own advantages. If you want to determine the maximum value of column capacity, then the appropriate Thomas model is used. The Yoon-Nelson model is used when looking for time for 50% breakthrough and the Adam-Bohart model aims to determine the value of adsorption capacity.

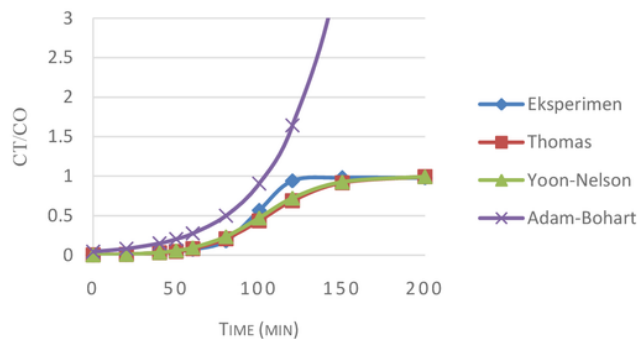

10
Figure 6. The prediction of the breakthrough curve uses the Thomas, the Yoon-Nelson, and the Adam-Bohart model at a bed height of 5 cm

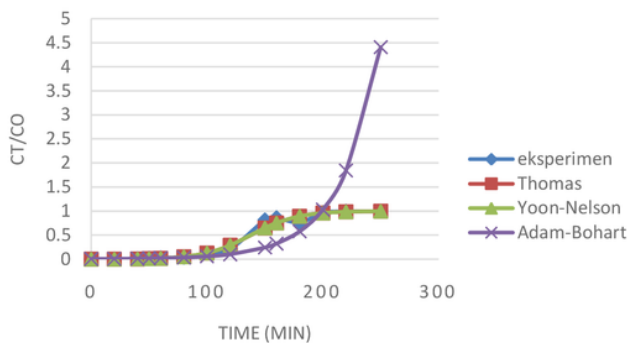

10
Figure 7. The prediction of the breakthrough curve uses the Thomas, the Yoon-Nelson, and the Adam-Bohart model at a bed height of 10 cm

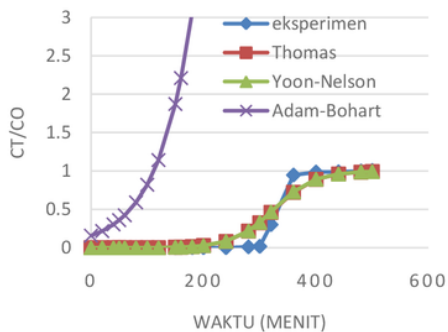

10
Figure 8. The prediction of the breakthrough curve uses the Thomas, the Yoon-Nelson, and the Adam-Bohart model at a bed height of 15 cm

Table 4. Prediction Breakthrough Curve: Regression Value Model Thomas, Yoon-Nelson, and Adam-Bohart

Tinggi Bed (cm)	R ²		
	Thomas	Yoon-Nelson	Adam-Bohart
5	0.95	0.95	0.85
10	0.98	0.98	0.88
15	0.81	0.81	0.87

4. Conclusion

The increase in bed height will slow down the breakthrough time so that longer saturation occurs. The saturation point (saturation point) is the longest obtained at bed height 15 cm with saturated time 480 minutes. The bed height of 15 cm is the optimum variable to produce maximum adsorption capacity (q_{exp}), total removal%, and total dye absorption (q_{total}) in the absorption of synthetic dye waste waste by value of 21.99 mg/g, 68.17%, and 3299.62 g.

Thomas and Yoon-Nelson kinetics models are the best modeling that can be used as a dye adsorption model using activated carbon betel nuts. Prediction of the breakthrough curve is fitted with the experimental data at bed height 5 and 10 cm with the regression coefficient (R^2) value of 0.95 and 0.98 respectively.

References

- [1] Yuliasari, N. 2011. Decreasing Chemical Oxygen Demand on Jumputan Wastewater by using Liver Moss. *Jurnal Penelitian Sains*. 14 (32).
- [2] Cundari L., Sari K.F., Anggraini L., 2018. Characteristic of betel nuts activated carbon and its application to Jumputan wastewater treatment, *IOP Conference Series: Material Science Engineering*, 345, 012041.
- [3] Han R, Wang Y, Zhao X, Wang Y, Xie F, Cheng J and Tang M 2009 *Desalination* 245 284-297.
- [4] Chowdhury. S., Yasin, M., Uddin M.T., Islam M. A. 2016. Batch and Continuous (fixed bed column) Adsorption of Methylene Blue by Rubber Leaf Powder. *International Journal of Integrated Science and Technology*. 2 (24-28).
- [5] Chowdhury. Z. Z., dkk (2012). Breakthrough Curve Analysis for Column Dynamics Sorption of Mn(II) Ions from Wastewater by Using Mangostana garcinia Peel-based Granular Activated Carbon. *Jurnal of Chemistry*. Hindawi Publishing Corporation. Volume 2013. Article ID 9959761, 8 pages.
- [6] Mahmoud, M. A. 2016. Kinetics Studies of uranium Sorption by Powdered Corn Cob in Batch and Fixed Bed System. *Journal of Advanced Research*. Elsevier. 7 (79-87).
- [7] Sugashini. S., Meera Sheriffa Begum. K. M. (2013). Column Adsorption Studies for The Removal of Cr (VI) Ions by Ethylamine Modified Chitosan Carbonized Rice Husk Composite Beads with Modelling and Optimization. *Jurnal of Chemistry*. Hindawi Publishing Corporation. Volume 2013. Article ID 460971, 11 pages.
- [8] Suksabye, J. Y., dkk. 2011. Column Study of Chromium (VI) Adsorption from Electroplating Industry by Coconut Coir Pith. *J. Hazardous Mater*. 160 (56-62).
- [9] Zhang, Wenxuan., Lei Dong, Han Yan, Haijiang Li, Ziwen Jiang, Xiaowei Kan, Hu Yang, Aimin Li, and Rongshi Cheng. "Removal of Methylene Blue from Aqueous Solutions by Straw Based Adsorbent in a fixed-bed Column." *Chemical Engineering Journal* 173, no. 2 (2011): 429-436.
- [10] Lim, A. P., dan Ahmad Z. A. 2014. Continuous Fixed-bed Column Study and Adsorption Modelling: Removal of Cadmium (II) and Lead (II) Ions in Aquous Solution by Dead Calcareous Skeletons. *Biochemical Engineering Journal*. Elsevier. 87 (50-61).

- [11] Nidheesh. P. V, Gandhimathi. R, Thanga R. S. Sarasvathy Anantha Singh. T. (2012). *Adsorption and Desorption Characteristics of Crystal Violet in Bottom Ash Column. Journal of Urban Environmental Engineering*. 6 (18-29).
- [12] Lopez-Cervantes, J. 2017. *Study of a Fixed-bed Column in the Adsorption of an Azo Dye from an Aqueous Medium Using a Chitosan-glutaraldehyde Biosorbent*. *Adsorption Science and Technology*. SAG 21 (1-18).
- [13] Mizwar, Andy, dkk. 2012. *Penyisihan Warna Pada Limbah Cair Industri Sasirangan Dengan Adsorpsi Karbon Aktif*. No. 13. Hal 11-16.

ORIGINALITY REPORT

33%

SIMILARITY INDEX

19%

INTERNET SOURCES

26%

PUBLICATIONS

30%

STUDENT PAPERS

PRIMARY SOURCES

1	Submitted to VIT University Student Paper	3%
2	Submitted to Universiti Sains Malaysia Student Paper	2%
3	link.springer.com Internet Source	2%
4	Submitted to Federal University of Technology Student Paper	2%
5	L Cundari, B D Afrah, D I Utami, N I Matondang. "Adsorption Model in Removal of Direct Synthetic Dyes in Aqueous Solution onto Tea Waste", Journal of Physics: Conference Series, 2019 Publication	2%
6	Submitted to Higher Education Commission Pakistan Student Paper	1%
7	ppjp.ulm.ac.id Internet Source	1%

8	Submitted to Curtin University of Technology Student Paper	1%
9	www.tandfonline.com Internet Source	1%
10	Submitted to Kyungpook National University Student Paper	1%
11	José Luis Sotelo, Gabriel Ovejero, Araceli Rodríguez, Silvia Álvarez, Juan García. "Removal of Atenolol and Isoproturon in Aqueous Solutions by Adsorption in a Fixed-Bed Column", Industrial & Engineering Chemistry Research, 2012 Publication	1%
12	Rokhsare Gouran-Orimi, Behruz Mirzayi, Ali Nematollahzadeh, Ali Tardast. "Competitive Adsorption of Nitrate in Fixed-Bed Column Packed with Bio-inspired Polydopamine Coated Zeolite", Journal of Environmental Chemical Engineering, 2018 Publication	1%
13	Submitted to Tshwane University of Technology Student Paper	1%
14	iwaponline.com Internet Source	1%
15	"Integrating Green Chemistry and Sustainable	1%

Engineering", Wiley, 2019

Publication

16

Submitted to Universiti Teknologi MARA

Student Paper

1%

17

www.science.gov

Internet Source

1%

18

Submitted to Cork Institute of Technology

Student Paper

1%

19

Sowmya Vilvanathan, S. Shanthakumar. " Column adsorption studies on nickel and cobalt removal from aqueous solution using native and biochar form of ", Environmental Progress & Sustainable Energy, 2017

Publication

<1%

20

opus.lib.uts.edu.au

Internet Source

<1%

21

journal.unnes.ac.id

Internet Source

<1%

22

Submitted to De La Salle University - Manila

Student Paper

<1%

23

Submitted to Institute of Chemical Technnology, Mumbai

Student Paper

<1%

24

Submitted to Khon Kaen University

Student Paper

<1%

25

Ghali, A.E.. "Preparation, characterization and application of a [copper (II)/ethylenediamine-cotton] complex for the removal of AB25 from aqueous solution in a laboratory scale column", Chemical Engineering Journal, 20111015

Publication

<1%

26

Yu-hua Wang, Hui-ping Hu, Xue-jing Qiu. "模拟氯化钴电解液深度除铜用聚氯乙烯基 2-氨基吡啶螯合树脂的动态吸附研究", Journal of Central South University, 2019

Publication

<1%

27

S. H. Hasan, Preeti Srivastava. " Biosorptive Abatement of Cd by Water Using Immobilized Biomass of Arthrobacter sp.: Response Surface Methodological Approach ", Industrial & Engineering Chemistry Research, 2011

Publication

<1%

28

Wara Dyah Pita Rengga, Achmad Chafidz, Mahmud Sudibandriyo, Mohammad Nasikin, Ahmed E. Abasaeed. "Silver nano-particles deposited on bamboo-based activated carbon for removal of formaldehyde", Journal of Environmental Chemical Engineering, 2017

Publication

<1%

29

Devi Shanmugam, Murugappan Alagappan, Rajesh Kannan Rajan. "Bench-scale packed bed sorption of Cibacron blue F3GA using

<1%

30

Submitted to International Islamic University
Malaysia

Student Paper

<1%

31

P. V Nidheesh, R Gandhimathi, S. T Ramesh, T.
S. Anantha Singh. "Modeling of Crystal Violet
Adsorption by Bottom Ash Column", Water
Environment Research, 2013

Publication

<1%

32

journals.sagepub.com

Internet Source

<1%

33

Yanhong LI, Yinian ZHU, Zongqiang ZHU,
Xuehong ZHANG, Dunqiu WANG, Liwei XIE.
"FIXED-BED COLUMN ADSORPTION OF
ARSENIC(V) BY POROUS COMPOSITE OF
MAGNETITE/HEMATITE/CARBON WITH
EUCALYPTUS WOOD MICROSTRUCTURE",
Journal of Environmental Engineering and
Landscape Management, 2018

Publication

<1%

34

C. R. Girish, V. Ramachandra Murty.
"Adsorption of Phenol from Aqueous Solution
Using Lantana camara, Forest Waste: Packed
Bed Studies and Prediction of Breakthrough
Curves", Environmental Processes, 2015

<1%

35

K.Y. Foo, B.H. Hameed. "Dynamic adsorption behavior of methylene blue onto oil palm shell granular activated carbon prepared by microwave heating", Chemical Engineering Journal, 2012

Publication

<1%

36

Kannan Radhakrishnan, Prabhakar Sivaraman, Wilson Richard Thilagaraj. "Removal of color and COD from actual textile effluent by hybrid biosorption and ultrafiltration processes", Journal of Water Reuse and Desalination, 2015

Publication

<1%

37

Submitted to National Institute of Technology Calicut

Student Paper

<1%

38

Submitted to UNESCO-IHE Institute for Water Education

Student Paper

<1%

39

Yu, Zhihui, Tao Qi, Jingkui Qu, and Yingchao Guo. "Application of mathematical models for ion-exchange removal of calcium ions from potassium chromate solutions by Amberlite IRC 748 resin in a continuous fixed bed column", Hydrometallurgy, 2015.

Publication

<1%

Gobi, K., M.D. Mashitah, and V.M. Vadivelu.

- 40 "Utilising waste activated sludge from a palm oil mill effluent treatment plant to remove methylene blue in continuous column studies", International Journal of Environmental Engineering, 2012.
Publication <1%
-
- 41 Submitted to Coventry University
Student Paper <1%
-
- 42 Submitted to University Tun Hussein Onn Malaysia
Student Paper <1%
-
- 43 Submitted to Institute of Graduate Studies, UiTM
Student Paper <1%
-
- 44 Mohamed A. Mahmoud. "Kinetics studies of uranium sorption by powdered corn cob in batch and fixed bed system", Journal of Advanced Research, 2016
Publication <1%
-
- 45 www.omicsonline.org
Internet Source <1%
-
- 46 Weihua Zou, Hongjuan Bai, Lei Zhao, Ke Li, Runping Han. "Characterization and properties of zeolite as adsorbent for removal of uranium(VI) from solution in fixed bed column", Journal of Radioanalytical and Nuclear Chemistry, 2011
Publication <1%

47 Podder, M.S., and C.B Majumder. "Fixed-bed column study for As(III) and As(V) removal and recovery by bacterial cells immobilized on Sawdust/MnFe₂O₄ composite", Biochemical Engineering Journal, 2016. <1%

Publication

48 Yolanda Patiño, Eva Díaz, Salvador Ordóñez. "Micropollutants pre-concentration using adsorption-desorption cycles: application to chlorinated paraffins and alkyl-phenol derivatives", Journal of Chemical Technology & Biotechnology, 2017 <1%

Publication

49 Submitted to University of the Philippines Los Banos <1%

Student Paper

50 Foo, K.Y., and B.H. Hameed. "Dynamic adsorption behavior of methylene blue onto oil palm shell granular activated carbon prepared by microwave heating", Chemical Engineering Journal, 2012. <1%

Publication

51 Lia Cundari, Aris Setiawan Kemit, Baharuddin Rasyid Usman. "Adsorption of Jumputan liquid waste by betel nuts activated carbon in a continuous fixed-bed adsorber", MATEC Web of Conferences, 2017 <1%

52

Submitted to University of Lancaster

Student Paper

<1%

53

Submitted to University College London

Student Paper

<1%

54

Sweta Mohan, Devendra Kumar Singh, Vijay Kumar, Syed Hadi Hasan. "Modelling of fixed bed column containing graphene oxide decorated by MgO nanocubes as adsorbent for Lead(II) removal from water", Journal of Water Process Engineering, 2017

Publication

<1%

55

tud.qucosa.de

Internet Source

<1%

56

Sinead Morris, Guiomar Garcia-Cabellos, David Ryan, Deirdre Enright, Anne-Marie Enright. "Low-cost physicochemical treatment for removal of ammonia, phosphate and nitrate contaminants from landfill leachate", Journal of Environmental Science and Health, Part A, 2019

Publication

<1%

57

Saad, Dalia M., Ewa Cukrowska, and Hlanganani Tutu. "Column adsorption studies for the removal of U by phosphonated cross-linked polyethylenimine: modelling and

<1%

optimization", Applied Water Science, 2014.

Publication

58

Singh, Neetu, and Chandrajit Balomajumder. "Continuous packed bed adsorption of phenol and cyanide onto modified rice husk: an experimental and modeling study", Desalination and Water Treatment, 2016.

Publication

59

Sharmeen Afroze, Tushar Kanti Sen. "A Review on Heavy Metal Ions and Dye Adsorption from Water by Agricultural Solid Waste Adsorbents", Water, Air, & Soil Pollution, 2018

Publication

60

Rhulani N. Ntimbani, Geoffrey S. Simate, Sehliselo Ndlovu. "Removal of copper ions from dilute synthetic solution using staple ion exchange fibres: Dynamic studies", Journal of Environmental Chemical Engineering, 2016

Publication

61

Sugashini, Sivaraju, and Kadhar Mohamed Meera Sheriffa Begum. "Performance of Fe-loaded chitosan carbonized rice husk beads (Fe-CCRB) for continuous adsorption of metal ions from industrial effluents", Environmental Progress & Sustainable Energy, 2013.

Publication

62

Submitted to Ibrahim Babangida University

<1%

<1%

<1%

<1%

<1%

63

Radhika R., Jayalatha T., Rekha Krishnan G., Salu Jacob, Rajeev R., Benny K. George.
"Adsorption performance of packed bed column for the removal of perchlorate using modified activated carbon", Process Safety and Environmental Protection, 2018

Publication

<1%

64

Radhika R., Jayalatha T., Rekha Krishnan G., Salu Jacob, Rajeev R., Benny K. George.
"Adsorption Performance of Packed Bed Column for the Removal of Perchlorate Using Modified Activated Carbon", Process Safety and Environmental Protection, 2018

Publication

<1%

65

Taty-Costodes, V.C.. "Removal of lead (II) ions from synthetic and real effluents using immobilized Pinus sylvestris sawdust: Adsorption on a fixed-bed column", Journal of Hazardous Materials, 20050831

Publication

<1%

66

Carla Albertina Demarchi, Aline Debrassi, Jacir Dal Magro, Natalia Nedelko et al. "Adsorption of Cr(VI) on crosslinked chitosan–Fe(III) complex in fixed-bed systems", Journal of Water Process Engineering, 2015

<1%

67

N. Mohanraj, P. Mohanraj, S. Bhuvaneshwari, JSS Allwin Ebinesar. "Decolorization of synthetic dye wastewater using packed bed electro-adsorption column", Chemical Engineering and Processing - Process Intensification, 2018

Publication

<1%

68

Yangzhong Zhang, Lue Xiong, Yifan Xiu, Kai Huang. "Defluoridation in fixed bed column filled with Zr(IV)-loaded garlic peel", Microchemical Journal, 2019

Publication

<1%

Exclude quotes Off

Exclude matches < 5 words

Exclude bibliography Off