

The effect of polypropylene fiber on mechanical properties of reactive powder concrete

by Saloma Hasyim

Submission date: 05-Oct-2019 11:24AM (UTC+0700)

Submission ID: 1186475946

File name: AIP_1885,_020093_2017_Saloma,_Hanafiah,_Funki_Nopreal_Putra.pdf (973.68K)

Word count: 1617

Character count: 7857

³
The effect of polypropylene fiber on mechanical properties of reactive powder concrete
Saloma, Hanafiah, and Fungki Nopreal Putra

Citation: [AIP Conference Proceedings](#) **1885**, 020093 (2017); doi: 10.1063/1.5002287

View online: <http://dx.doi.org/10.1063/1.5002287>

View Table of Contents: <http://aip.scitation.org/toc/apc/1885/1>

Published by the [American Institute of Physics](#)

A promotional banner for AIP Conference Proceedings. The left side features a blue background with a water texture. The right side is a solid yellow rectangle. Text is overlaid on both backgrounds.

SUMMER SALE!

30% OFF
ALL PRINT
PROCEEDINGS!

AIP | Conference Proceedings

ENTER COUPON CODE
SUMMER2017

3 The Effect of Polypropylene Fiber on Mechanical Properties of Reactive Powder Concrete

Saloma^{1,a)}, Hanafiah^{1,b)} and Fungki Nopreal Putra¹⁾

¹Civil Engineering Department, Faculty of Engineering, Sriwijaya University, Jl. Raya Palembang-Prabumulih Km.32 Indralaya, OI, Sumatera Selatan 30662, Indonesia

Corresponding author: ^{a)}saloma_571@yahoo.co.id
^{b)}hanafiah_dr@yahoo.com.sg

Abstract. Reactive Powder Concrete (RPC) was known as concrete with very dense in microstructure and having high value in compressive strength due to the utilization of very fine materials. One of the weakness of RPC is very brittle. To improve the ductility could used polypropylene fiber. In this research, the various weight of the polypropylene fiber used were 0.4 kg, 0.6 kg, and 0.8 kg per cubic metre of concrete. From this study, RPC mixture with 0.8 kg polypropylene fiber yielded maximum value, e.g the compressive strength was 103.253 MPa, modulus of elasticity was 45.252 MPa, splitting tensile strength was 5.91 MPa, and flexural strength was 9.56 MPa.

INTRODUCTION

Reactive Powder Concrete (RPC) is one of an advance solution in concrete technology. RPC has compact microstructure and high compressive strength ranging 150-250 MPa and low permeability [1-2]. Materials using for RPC is very fine in particle size as in submicroscopic range. Cement in the size of 0.1-0.6 μm and sand in the size of 0.125-0.500 mm. RPC also use microsilica in the size of 0.08-0.125 μm and quartz flour in the size of 0.1-0.6 μm [3-6]. One of the weakness of RPC is very brittle. For improving the ductility of RPC can use polypropylene fiber. The purpose of the research is to investigate the effect of using polypropylene fiber in various weight on RPC mechanical properties, e.g. compressive strength, modulus of elasticity, splitting tensile strength, flexural strength.

MATERIAL AND EXPERIMENTAL STUDY

The Materials used in this research were type 1 cement, silica fume, water, quartz sand in the size of 150-650 μm , quartz flour in the size 0.3-25 μm , polypropylene fiber in the diameter of 18 μm and 1.2 mm in length, and superplasticizer. The composition of RPC used can be seen in Table 1.

Materials mixing process used horizontal mixer. The first step, mixed all material e.g cement, quartz sand, quartz flour, and silica fume in dry condition for five minutes as can be seen Figure 1.a. The second step, added 85% of water and 50% of superplasticizer from the total needed at seventh minute, poured polypropylene fiber into the mixed. Then, added all the rest water and superplasticizer in the 10th minute. The mixture was stirred until homogeneous until the 20th minute as can be shown in Figure 1.b. The next step, carried out slump flow test according to ASTM C1611 as can be seen in Figure 2. Before conducting compressive strength test, modulus of elasticity test, split tensile strength test, and flexural strength test, the cylinder specimens with the size of 150 mm x 300 mm were covered using damp cloth for curing process till the day of performing the each test.

TABLE 1. The composition of RPC

Materials	Composition (kg/m ³)			
	PVA 0	PVA 0.4	PVA 0.6	PVA 0.8
Cement	750.00	750.00	750.00	750.00
Silica fume	221.29	221.29	221.29	221.29
Quartz sand	859.98	859.98	859.98	859.98
Quartz flour	201.05	201.05	201.05	201.05
Superplasticizer	25.42	25.42	25.42	25.42
water	152.00	152.00	152.00	152.00
Polypropylene	0.00	0.40	0.60	0.80
w/c	0.28	0.28	0.28	0.28



(a) The initial stage of mixing



(b) The final stages of mixing

FIGURE 1. The mixing process

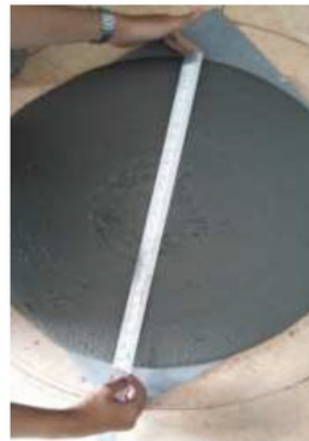


FIGURE 2. Slump flow test

RESULTS AND DISCUSSION

Slump Flow

The result of slump flow tests were shown in Figure 3. The diameter of slump flow for mixture without polypropylene fiber was 64.9 cm. And the diameter of slump flow for mixture with polypropylene addition of 0.4 kg/m³, 0.6 kg/m³, and 0.8 kg/m³ were 64.15 cm, 62.65 cm, and 58.75 cm, respectively. The more the addition of polypropylene fiber, the smaller the diameter of slump flow. But for mixture will 0.8 kg/m³ polypropylene addition showed significant decreasing of slump flow diameter.

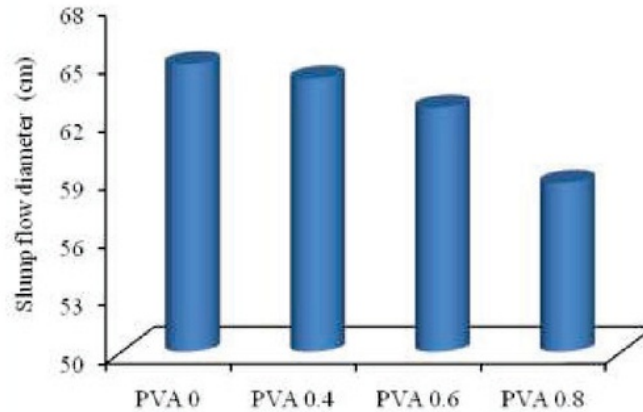


FIGURE 3. The results of slump flow test

Setting Time

The data of setting time test can be seen in Figure 4. From this figure can be explained that both initial setting time and final setting time not differ significantly from each other mixture with addition of polypropylene fiber. Its initial setting time was ranging from 150 to 158 minutes and final setting time was ranging from 240 to 248 minutes. Both initial and final setting time for each mixture were not differ significantly.

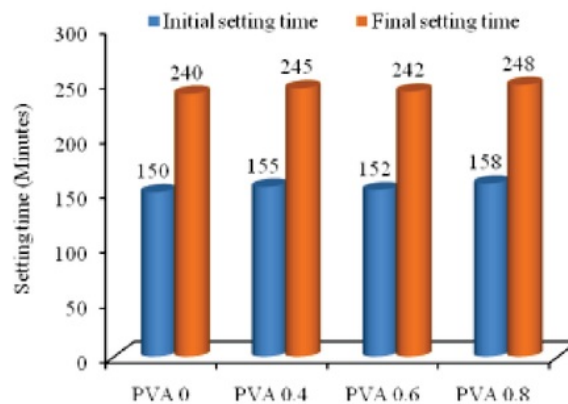


FIGURE 4. The result of setting time test

Compressive Strength

Figure 5 showed the graph of compressive strength for various of RPC mixtures for 3, 7, 14, 21, and 28 days. From this graph, can be explained that the more the addition of polypropylene fiber, the higher the compressive strength as the increasing of testing age. The highest value of compressive strength was 103.254 MPa was yielded by 0.8 kg/m³ of polypropylene fiber RPC mixture, and for RPC mixture without polypropylene fiber reached the lowest value as low as 84.939 MPa. Then the increasing percentage of compressive strength with addition 0.4 kg/m³, 0.6 kg/m³, and 0.8 kg/m³ of polypropylene fiber were 10.488%, 14.347%, and 17.737%, respectively. The increasing of compressive strength can be due to the effect of each other crossing of polypropylene fiber which acted as cross tie.

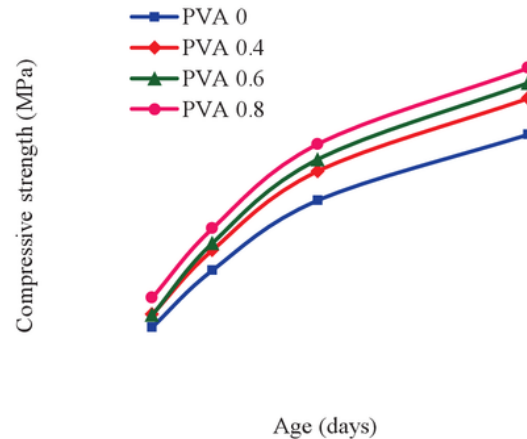


FIGURE 5. Compressive strength

Modulus of Elasticity

Figure 6 showed the modulus of elasticity values of each mixture for 28 days. It can be seen that the modulus of elasticity value would increased due to the increasing of addition of polypropylene fiber. The highest value of modulus of elasticity was 45.252 MPa given by RPC with 0.8 kg/m³ of polypropylene fiber and the lowest value was 32.053 MPa for RPC without polypropylene fiber. Based on the value of modulus elasticity of RPC without polypropylene fiber, the percentage increasing of modulus of elasticity for each addition of polypropylene fiber e.g 0.4 kg/m³, 0.6 kg/m³, and 0.8 kg/m³ were 10.183%, 14.334%, and 24.154%, respectively.

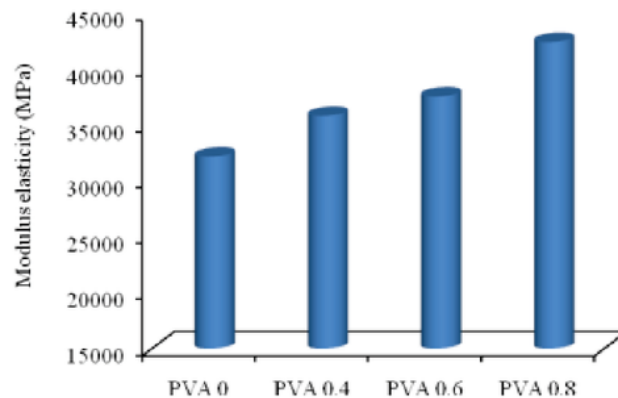


FIGURE 6. Modulus of elasticity

Splitting Tensile Strength

Figure 7 showed the results of splitting tensile strength test of each mixture for 28 days. From this figure, it can be explained that the splitting tensile strength of RPC would increase with the increasing of polypropylene fiber addition. The values are 5.01 MPa, 5.45 MPa, and 5.91 MPa for each addition of polypropylene fiber e.g. 0.4 kg/m³, 0.6 kg/m³, and 0.8 kg/m³, respectively.

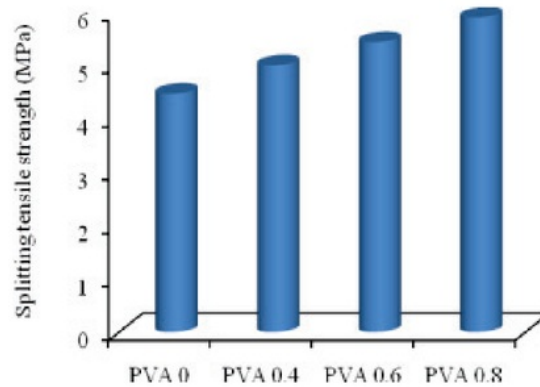


FIGURE 7. Splitting tensile strength

Flexure Strength

The result of flexure strength test for 28 days was shown in Figure 8. The more the addition of polypropylene fiber in the mixture, the greater the flexural strength was yielded. The values of flexural strength for various additions of polypropylene fiber e.g. 0.4 kg/m³, 0.6 kg/m³, and 0.8 kg/m³ were 8.51 MPa, 8.96 MPa, and 9.56 MPa, respectively.

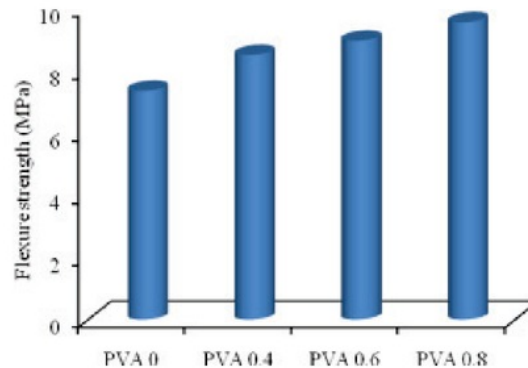


FIGURE 8. Flexure strength

CONCLUSIONS

From this study, it can be concluded as follows:

1. The smallest slump flow diameter was yielded from mixture with 0.8 kg/m³ of polypropylene fiber.
2. The initial and final setting time of each mixture were not differ significantly.
3. All the mechanical properties e.g. compressive strength, modulus of elasticity, splitting tensile strength, and flexural strength increased simultaneously with the increasing addition of polypropylene fiber in the mixture.
4. The highest values were yielded from mixture with 0.8 kg/m³ of polypropylene fiber.
5. The highest values of compressive strength, modulus of elasticity, splitting tensile strength, and flexural strength were 103.253 MPa, 45.252 MPa, 5.91 MPa, and 9.56 MPa, respectively.

ACKNOWLEDGMENTS

The research presented in this paper was supported by grant from Unggulan Kompetitif Universitas Sriwijaya, 2015.

REFERENCES

1. B.A. Graybeal, "Material Property Characterization of Ultra-High Performance Concrete" Report No. FHWA-HRT-06-103.
2. K. Ramujee, International Journal of Innovative Research in Science, Engineering and Technology 2, 3409-3413 (2013).
3. H.K.S. Eldin, H. A. Mohamed, M. Khater, S. Ahmed, International Journal of Engineering and Innovative Technology 4, 4-10 (2014).
4. T.C. Madhavi, L.S. Raju, D. Mathur, International Journal of Emerging Technology and Advanced Engineering 4, 114-119 (2014).
5. M.V. Mohod, IOSR Journal of Mechanical and Civil Engineering 12, 28-36 (2015).
6. V.M. Sounthararajan, A. Jain, A. K.Singh, S. Thirumurugan, A. Sivakumar, International Journal of Engineering and Technology 5, 1817-1828 (2013).

The effect of polypropylene fiber on mechanical properties of reactive powder concrete

ORIGINALITY REPORT

3%

SIMILARITY INDEX

%

INTERNET SOURCES

3%

PUBLICATIONS

%

STUDENT PAPERS

PRIMARY SOURCES

1

Chinnakotti Sasidhar .. "A STUDY ON THE VARIATION OF STRENGTH PROPERTIES OF CONCRETE WITH PARTIAL REPLACEMENT OF CEMENT USING NANO-SILICA (NS) AND FLY ASH (FS)", International Journal of Research in Engineering and Technology, 2016

Publication

1%

2

Ahmad, Shamsad, Ahmed Zubair, and Mohammed Maslehuddin. "Effect of key mixture parameters on flow and mechanical properties of reactive powder concrete", Construction and Building Materials, 2015.

Publication

1%

3

V. Savino, L. Lanzoni, A.M. Tarantino, M. Viviani. "An extended model to predict the compressive, tensile and flexural strengths of HPFRCs and UHPFRCs: Definition and experimental validation", Composites Part B: Engineering, 2019

Publication

1%

Exclude quotes On

Exclude bibliography On

Exclude matches < 1%