

Low-Cost Yet High-Performance Hydrochar Derived from Hydrothermal Carbonization of Duku Peel (*Lansium domesticum*) for Cr(VI) Removal from Aqueous Solution

by Risfidian Mohadi

Submission date: 22-Dec-2022 09:08PM (UTC+0700)

Submission ID: 1985868289

File name: erformance_Hydrochar_Derived_from_Hydrothermal_Carbonization.pdf (519.89K)

Word count: 5578

Character count: 27953

Low-Cost Yet High-Performance Hydrochar Derived from Hydrothermal Carbonization of Duku Peel (*Lansium domesticum*) for Cr(VI) Removal from Aqueous Solution

Risfidian Mohadi¹, Novie Juleanti², Normah Normah², Patimah Mega Syah Bahar Nur Siregar²,
Alfan Wijaya², Neza Rahayu Palapa³, and Aldes Lesbani^{1,2*}

¹Graduate School, Faculty of Mathematics and Natural Sciences, Sriwijaya University,
Jl. Palembang-Prabumulih, Km. 90-32, Ogan Ilir 30862, South Sumatra, Indonesia

²Research Center of Inorganic Materials and Complexes, Faculty of Mathematics and Natural Sciences, Sriwijaya University,
Jl. Padang Selasa Bukit Besar, Palembang 30139, South Sumatra, Indonesia

³Department of Chemistry, Faculty of Mathematics and Natural Sciences, Sriwijaya University,
Jl. Palembang-Prabumulih, Km. 90-32, Ogan Ilir 30862, South Sumatra, Indonesia

* Corresponding author:

email: aldeslesbani@pps.unsri.ac.id

Received: March 2, 2022

Accepted: October 3, 2022

DOI: 10.22146/ijc.73353

Abstract: Carbon-based adsorbent as a hydrochar (Hc) material with Duku (*Lansium domesticum*) peel precursors has been successfully synthesized as evidenced by XRD, FT-IR, BET, and SEM analysis. XRD analysis showed the presence of diffraction peaks around 16° and 22° which indicated the presence of carbonaceous material. This is confirmed by FTIR analysis which shows the presence of vibration at 2931 cm⁻¹ of cellulose. SEM data results showed that heterogeneous and has an irregular shape and surface area increased twice from Duku peel to Hc. Duku peel and Hc adsorbent materials were applied to adsorb heavy metal ions Cr(VI). Kinetic parameters of Cr(VI) using Duku peel and Hc showed that the optimum time reached was at 120 min. The adsorption kinetics model of Cr(VI) using Hc tends to follow the PFO model and Langmuir isotherm adsorption. Duku peel material used to adsorb Cr(VI) reached an adsorption capacity of 42.19 mg/g, while in Hc material there was an increase that reached 80.64 mg/g. The thermodynamic parameters of both materials show that the adsorption process is spontaneous.

Keywords: hydrothermal carbonization; hydrochar; *Lansium domesticum* peel; adsorption; Cr(VI)

INTRODUCTION

Environmental pollution is a serious problem that can be a health threat to living things and the environment [1]. The types of pollution that are mostly found are in the form of dyes, organic compounds, and heavy metal ions. Heavy metals are dangerous contaminants when they enter the environment through the water. Even heavy metal ions at low concentrations have been considered highly toxic [2]. Heavy metals can accumulate in the food chain and their resistance in the ecosystem will harm the environment. Heavy metals can come from various industrial activities such as metallurgy, textiles, batteries, mining, ceramics, and so on

[3]. Cr(VI) is one of the most common heavy metal ions in wastewater. Cr(VI) is the most dangerous oxide form of Cr. The ability of Cr(VI) to form oxoanions in highly soluble water such as chromate and dichromate can be potentially harmful to human health. Cr(VI) which is toxic and carcinogenic can cause several respiratory, liver, and kidney problems [4]. This is because Cr(VI) cannot be degraded by the body and has high solubility and mobility in the environment [5] based on these various negative impacts, an efficient method is needed to overcome heavy metal ion contamination [6]. Various existing technologies such as photodegradation, coprecipitation, electrochemical degradation, electrocoagulation, and adsorption.

Adsorption is the most widely used method. High efficiency, easy to perform, low cost, and allows the adsorbent to be regenerated, making the adsorption method the right choice [6]. The adsorbent in a solid-state has a good ability to adsorb. Several of the most widely used adsorbents are zeolite, carbon, silica gel, and biosorbents [7]. Among all adsorbents, carbon-based materials have shown several advantages over other adsorbents. Its higher resistance to moisture and good thermal stability make this material continue to be developed, one of which is the hydrothermal carbonization method [8].

The hydrothermal carbonization method produces a product in the form of hydrochar (Fig. 1). Several studies have made the hydrochar material derived from raw materials such as orange peel, rice husk, pomelo skin, pea shells, pineapple peel, coconut husk, sawdust wood, and duku (*Lansium domesticum*) peel [9]. Duku (*Lansium domesticum*) peel was chosen because it contains carbon compounds and their abundance that is easy to find. *Lansium domesticum* is a species of the Miliaceae family that can grow to 40–50 feet. The fruit is locally known as langsats, long-kong, duku, lang-sook, or langsats-khao [10]. Hua et al [11] research explains that hydrochar prepared from microbial aging can adsorb Cd(II) with an adsorption capacity of 4.19 mg/g. On the other hand, the use of hydrochar as an adsorbent from pinewood biomass showed the ability of Pb(II) adsorption with an adsorption capacity of 46.70 mg/g [12]. Research conducted by Wang et al used the skin of the pomelo fruit as an adsorbent for Cr(VI). The surface area of the pomelo skin is 3.85 m²/g with an adsorption capacity of 0.57 mg/g [13]. On the other hand, Li et al. [14] conducted a study on overcoming Cr(VI) contamination by the adsorption method using hydrochar made from bamboo sawdust. The resulting adsorption capacity of Cr(VI) reached 3.20 mg/g. The adsorption process of Cr(VI) using hydrochar has also been proven by Shi et al. [15] which uses corn cobs to have a maximum adsorption capacity of 7.23 mg/g. These data confirm that the hydrochar material has a good ability in the adsorption process due to its low-cost and efficiency than nanocomposites and synthesis materials. Therefore, this research was conducted



Fig 1. Schematic illustration of hydrochar formation using hydrothermal carbonization method

to maximize the use of Duku peel waste and its application as a waste-based adsorbent. This study proves that the development of Duku peel into hydrochar (Hc) material through the hydrothermal carbonization method has a good ability to adsorb heavy metal ions Cr(VI). Fruit peel waste is quite abundant but still lacking in utilization is Duku peel waste. According to Fig. 1, hydrothermal carbonization method is carried out as an easy and inexpensive method. This is certainly very beneficial in terms of research and utilization of a waste-based adsorbent. Shankar et al. [16] revealed that Duku peel contains phenolic compounds. The content of these compounds allows Duku peel to bond with metals. According to Lam et al. [17], the abundance of Duku peel with unique chemical content, non-toxic and usable makes Duku peel potential to be a biosorbent. The success of Hc material synthesis was characterized by XRD, FTIR, and a surface area analysis. The ability of the two materials is determined by kinetics, isotherm, and thermodynamic parameters.

EXPERIMENTAL SECTION

Materials

The chemicals used in this experiment were K₂Cr₂O₇ (Merck, 99.8%), 1,5-diphenylcarbazine (Sigma Aldrich, 98%), H₂SO₄ 37% by MallinckrodtAR°. The hydrochar source was made from *Lansium domesticum* peel. Water was obtained using a Purite® water purification system from the Research Center of Inorganic Materials and Complexes.

Instrumentation

The material characterization was performed using X-Ray Diffraction (XRD) Rigaku mini 6000, Fourier-Transform Infrared Spectroscopy (FTIR) Shimadzu Prestige-21, surface area analyzer Quantachrome Instruments, and Scanning Electron Microscopes (SEM) analyzer SU800 Series. The concentration of Cr(VI) complexed with diphenylcarbazide was analyzed using a spectrophotometer UV-Visible Biobase BK-UV 1800PC.

Procedure

Duku peel biosorbent preparation

Duku peel is cut into small pieces and washed using water until clean and dried under the sun, then oven at 100 °C for 8 h, mashed, and sieved using a 40 mesh filter.

Hydrothermal carbonization

Total of 2.5 g of duku peel and 50 mL of water were put into a 100 mL Hydrothermal Stainless-steel Autoclave, then oven at 200 °C for 12 h. After that, the Hc precipitate was cooled at room temperature for 12 h and washed with distilled water, then dried in an oven at 105 °C for 24 h to obtain the Hc product, which was further characterized using XRD, FTIR, BET, and SEM analysis.

Kinetics, isotherm and thermodynamic study

Kinetic studies were carried out to determine the adsorption kinetics model by adding 0.02 g of adsorbent to 20 mL of Cr(VI) solution with time variations 0, 10, 20, 30, 40, 50, 60, 70, 90, 120, 150, and 180 min. The effect of temperature and concentration was carried out to determine isotherm parameters and thermodynamic adsorption of Duku peel and Hc. Addition of 0.02 g of adsorbent to 20 mL of Cr(VI) solution with a concentration of 25, 50, 75, 100, and 125 ppm, then stirring for 60 minutes with temperature variations of 30, 40, 50, 60 and 70 °C. The complexation of Cr(VI)-diphenylcarbazide was carried out by Cr(VI) solution (10 mL) added diphenylcarbazide solution (2 mL, 1000 mg/L) and H₂SO₄ (1 mL, 1 M). The mixing solution was homogeneous within 5 min. Measurement of the concentration of Cr(VI)-diphenylcarbazide adsorption was carried out using a UV Vis spectrophotometer at a wavelength of 543 nm.

RESULTS AND DISCUSSION

The characteristics of the Duku peel and Hc adsorbent materials were analyzed by XRD, FTIR, BET, and SEM. XRD analysis is one of the main characterizations of the Duku peel to Hc preparation in Fig. 2. XRD analysis is used to determine changes in the crystal structure in Duku peel biomass to Hc during the hydrothermal carbonization process. Fig. 2 shows the diffractogram of the Duku peel at diffraction angles of 16.90° and 21.80°. The hydrothermal carbonization process carried out on Duku peel to produce Hc did not significantly change the XRD pattern. It is proven that Fig. 1 shows the XRD pattern of Hc which is at the diffraction angle of 16.00° and 22.47°.

According to Yadav et al [18], the peaks around 16° and 22° are specific regions for cellulose compounds. This indicates that the Hc synthesis of the Duku peel does not change the structure of cellulose. The hydrothermal carbonization process affects the intensity of the diffractogram peak of the Duku peel which tends to be amorphous but after the process it produces Hc which tends to have better crystallinity.

In addition XRD analysis, the success of Hc material synthesis is also supported by FTIR analysis in Fig. 3. This analysis is used to detect functional groups

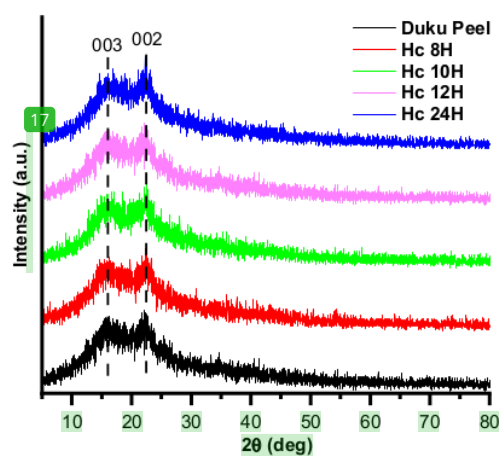


Fig 2. XRD pattern of the Duku peel and Hc

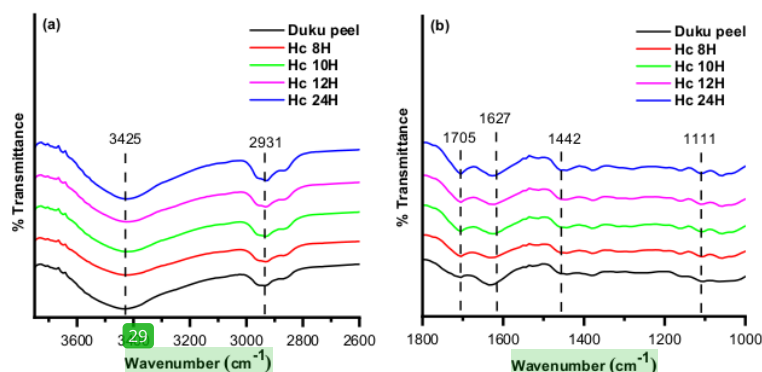


Fig 3. FTIR spectra of Duku peel and Hc at 200 °C in different times of hydrothermal process at wavenumber (a) 2600–3750 cm^{-1} and (b) 1000–1800 cm^{-1}

contained in Duku peel and Hc. Fig. 3(a) shows the spectra of the Duku peel, while Fig. 3(b) shows the Duku peel spectra that have gone through the hydrothermal carbonization process to Hc.

The spectra showed the similarity of vibrations at 3425 and 1627 cm^{-1} which indicates the -OH from hydroxyl and carbonyl groups [19] group of alcohol in both materials. Another vibration also appeared at 2931 cm^{-1} which indicated the presence of C-H cellulose [20]. The sharp vibration at 1635 cm^{-1} indicates the C=O group of the primary amide vibrations. Meanwhile, another vibration in 1442 cm^{-1} indicates C=C stretching from aromatic compounds [21]. Based on He et al. [22] it has been confirmed that there are vibrations of C=O at 1705 cm^{-1} .

One of the advantages of the hydrothermal carbonization process is that it increases the surface area of the material. To prove this, a surface area analysis was performed to measure the increase in surface area from Duku peel to Hc. This surface area analysis also displays the measurement results of pore volume and pore diameter. Surface area analysis was carried out by the N_2 adsorption-desorption process which produced the isotherm pattern in Fig. 4.

The Hc isotherm pattern in Fig. 4(b) tends to resemble the pattern of the Duku peel isotherm. According to IUPAC, Type III isotherm shows the characteristic of weak interaction between adsorbent and adsorbate, where the affinity between the adsorbent molecules is greater

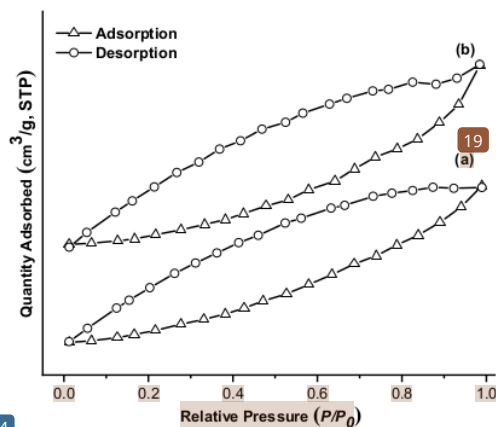


Fig 4. N_2 adsorption-desorption isotherm of the (a) Duku peel and (b) Hc

than the affinity for the surface of the adsorbent. The type III isotherm pattern is an indication that the material has low adsorption energy [23]. BET measurement data on the surface area, pore-volume, and pore diameter for both adsorbents are presented in Table 1.

The data in Table 1 shows the results of measuring the surface area of the Duku peel of 12.34 m^2/g . After the carbonization process took place, there was an increase in the surface area of the hydrochar material which almost doubled to 22.63 m^2/g . This indicates that the hydrothermal carbonization process succeeded in increasing the surface area of the material.

Table 1. BET surface area analysis

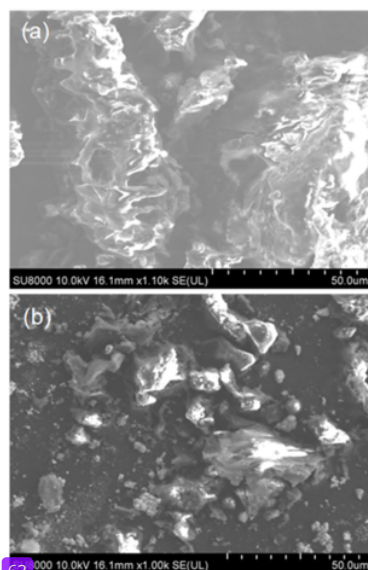
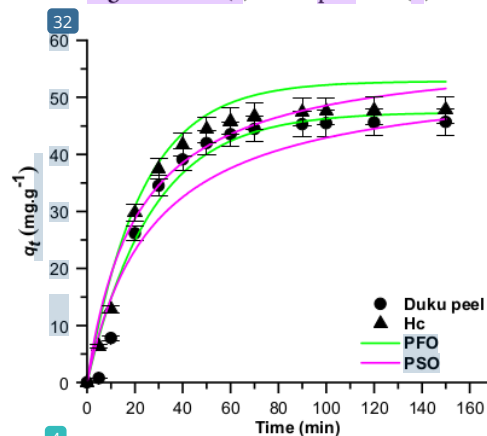
Materials	Surface area (m ² /g)	Pore size (nm), BJH	Pore volume (cm ³ /g) _{BJH}
Duku peel	12.34	0.02	2.64
Hc	22.63	0.04	2.76

Table 2. Parameter of adsorption kinetic model on Duku peel and Hc

Parameter	Adsorbent	Duku peel	
		Duku peel	Hc
1 st order	qPFO	56.46	58.23
	k ₁ (1/min)	0.05	0.05
	R ²	0.99	0.99
2 nd order	q-PSO (mg/g)	58.13	63.29
	k ₂ (mg/min)	0.001	0.001
	R ²	0.911	0.96
Elovich	a (g/mg)	386.00	25.16
	b (g/mg.min)	0.08	0.07
	R ²	0.89	0.93

Scanning Electron Microscopy (SEM) analysis is used to see the surface morphological structure, and particle size and to show the crystallographic structure of the observed material object. Fig. 5(a) presents the SEM analysis results of Duku peel adsorbents which tend to clump in the same phase or what is commonly referred to as aggregation. Fig. 5(b) shows the particle morphological pattern of the Hc adsorbent which tends to be heterogeneous and has an irregular shape: this is due to the hydrothermal carbonization treatment given, causing the particles to experience a breakdown or what is commonly known as deaggregation.

The ability of the adsorbent material was tested through the isotherm and thermodynamic parameters of adsorption. Based on the physical adsorption process, allows the adsorbent material to be regenerated because the weak bond between the adsorbent and the adsorbate is easily released so that the adsorbate is easily desorbed. The kinetics parameters were carried out by varying the adsorption contact time, the results of which were presented in Fig. 6. The graph shows that the Cr (VI) adsorption process using both adsorbents reached the optimum time of 120 min. The results of determining the kinetics of Cr(VI) adsorption parameters are presented in Table 2.

**Fig 5.** SEM of (a) Duku peel and (b) Hc**Fig 6.** The effect of variations in the adsorption time of Cr(VI)

The parameters of the kinetics model are calculated from the slope and intercept of each plot. The kinetics model was determined based on the regression coefficient R^2 [24]. Table r shows the Duku peel and Hc materials in the PFO kinetics model which are closer to 1, with values of 0.99 and 0.99, respectively. Moreover, the $Q_{e,calc}$ value of the two materials at PFO is closer to the $Q_{e,exp}$ value. This proves that the adsorption of

Cr(VI) using Duku peel and Hc follows the PFO kinetics model. According to Jiang et al. [25], the PFO kinetics model assumes the adsorption rate is influenced by the active site of the adsorbent.

Both of these parameters were determined by varying the concentration and adsorption temperature, as shown in the graph in Fig. 7. The graph explains that the Cr(VI) adsorption process using Duku peel and Hc has an increased adsorption capacity as the concentration and temperature increase. The adsorption results on the graph also show that the adsorption ability of Hc is better than Duku peel. The adsorption isotherm parameters determined were Langmuir and Freundlich isotherm models, in Table 3.

The value of the Cr(VI) adsorption capacity of the Duku peel in Table 3 reaches 42.19 mg/g, while the Hc adsorption capacity is as wide as 80.64 mg/g. This shows that the adsorbent synthesis by the hydrothermal method was successful in increasing the adsorption capacity significantly with increasing surface area which is evidenced in the N₂ adsorption-desorption analysis data in Table 1. Table 3 also shows the linear regression values of the Langmuir and Freundlich isotherm parameters.

Duku peel adsorbent material has an R² value of 0.99 in the Langmuir isotherm model and 0.891 in the Freundlich. The R² value of Hc on the Langmuir model is 0.98, while the Freundlich model is 0.96. According to Juleanti et al. [26], the determination of the adsorption

isotherm model is based on a linear regression value that is close to 1, so that the Cr(VI) adsorption process using Duku peel and Hc materials tends to follow the Langmuir isotherm model. Langmuir isotherm model is used to describe the absorption process where there is no interaction between adsorbate molecules on the side that has the same absorption energy [27]. According to Bahar Nur Siregar et al. [28], Langmuir's isotherm model is based on the interaction between the adsorbent and the thermodynamic parameter data in the form of enthalpy (ΔH), entropy (ΔS), and Gibbs free energy (ΔG) are presented in Table 4.

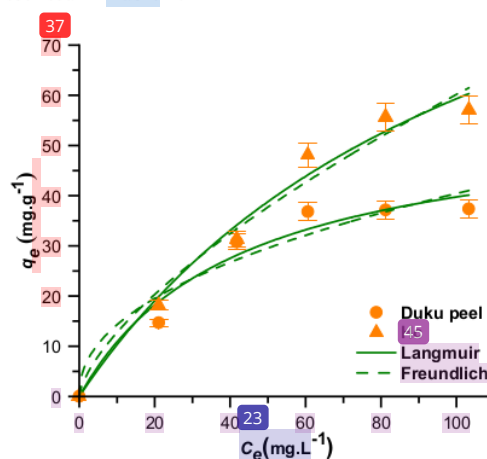


Fig 7. Effect of concentration and temperature on the adsorption of Cr(VI) onto Duku peel and Hc

Table 3. Parameter of adsorption isotherm models on Duku peel and Hc

Adsorbent	Adsorption isotherm	Adsorption constant	T (K)			
			303 K	313 K	323 K	333 K
Duku peel	Langmuir	Q _{max}	20.61	30.30	34.01	42.19
		kL	0.33	0.08	0.19	0.14
		R ²	0.99	0.98	0.99	0.98
	Freundlich	N	1.14	1.23	1.97	2.43
		kF	1.69	1.33	1.38	1.43
		R ²	0.90	0.99	0.95	0.99
Hc	Langmuir	Q _{max}	51.81	57.14	76.92	80.64
		kL	0.02	0.03	0.04	0.10
		R ²	0.98	0.99	0.99	0.99
	Freundlich	n	0.37	0.44	0.51	0.74
		kF	1.32	1.36	1.37	1.42
		R ²	0.99	0.99	0.99	0.89

Table 4. Thermodynamic parameters for adsorption of Cr(VI) on Duku peel and Hc

Material	ΔH° (kJ/mol)	ΔS° (J/mol.K)	ΔG° (kJ/mol)			
			303 K	313 K	323 K	333 K
Duku peel	51.22	0.16	2.62	1.02	-0.58	-2.18
	49.31	0.15	1.97	0.41	-1.14	-2.71
	30.12	0.09	1.58	0.64	-0.29	-1.24
	27.29	0.08	2.90	-2.09	-1.29	0.48
	24.01	0.06	3.56	-2.89	-2.22	1.54
Hc	55.52	0.18	0.61	-1.20	-3.01	-4.82
	39.95	0.12	1.09	-0.19	-1.47	-2.75
	35.17	0.11	-0.10	-1.26	-2.42	-3.59
	23.97	0.07	0.25	-0.53	-1.31	-2.09
	18.38	0.05	1.10	0.53	-0.03	-0.61

The positive value of the entropy energy (ΔS°) indicates that there is increased randomness at the solid/solution interface [29]. The enthalpy values of Duku peel which are in the range of 24.01–51.22 kJ/mol in Table 4 indicate a positive value. The same thing as Hc, the adsorption enthalpy value is around 18.38–55.52 kJ/mol with a positive value of enthalpy indicating that the adsorption process was endothermic. Palapa et al. [30] confirmed that the enthalpy range at 5–40 kJ/mol indicates the occurrence of physical adsorption, whereas if the enthalpy is more than 40 kJ/mol indicates the occurrence of chemical adsorption. Based on the enthalpy value of Duku peel and Hc, the overall adsorption process

takes place physically, but some circumstances indicate that the adsorption takes place chemically because the enthalpy value is more than 40 kJ/mol [31]. According to these data, the adsorption process of Cr(VI) by Duku peel and Hc occurred in physical and chemical sorption. For comparison, Table 5 presents data from studies on Cr(VI) adsorption using several adsorbents. Based on Table 5, the results data of Cr(VI) adsorption using Hc is better than others researchers. This assumed that Hc from Duku peel has good ability for Cr(VI) removal.

In addition, the Cr(VI) adsorption mechanism (Fig. 9) is clarified through FTIR data after adsorption which is presented in Fig. 8. The spectra before and after

Table 5. Comparison of the adsorption of Cr(VI) using several adsorbents

Adsorbent	Adsorption capacity (mg/g)	Reference
Apple peel-derived biochars	41.67	[32]
Rice husk biochar	8.14	[33]
Tea waste biochar	9.12	[33]
Activated clay biochar composite	6.10	[34]
Holey graphene	5.48	[35]
Watermelon peel	72.49	[36]
Algal-bacterial aerobic granular sludge	51	[37]
Biochar derived from bamboo residues	40	[38]
Algae <i>Sargassum bevanom</i>	39.68	[39]
Biomass of <i>Sargassum dentifolium</i> , Seaweed	41.20	[40]
HA-Cell-RH	19.39	[13]
Bamboo sawdust hydrochar	3.20	[14]
Corn cobs hydrochar	7.23	[15]
Duku peel	42.19	This Research
Hc	80.64	This Research

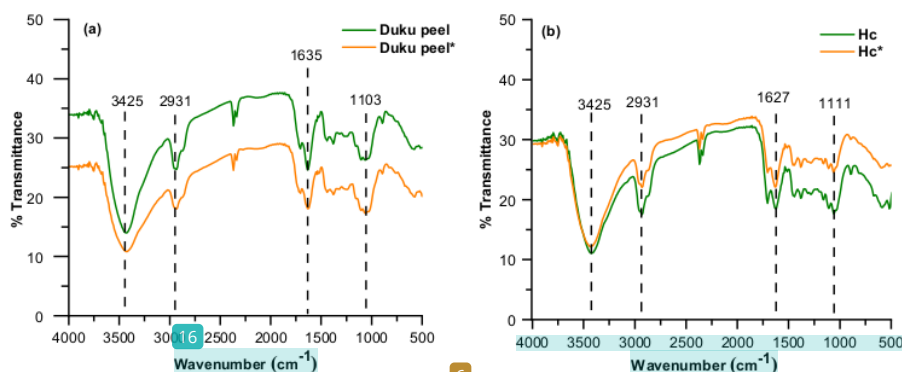


Fig 8. FTIR spectra of adsorbent after the Cr(VI) adsorption process using (a) Duku peel and (b) Hc

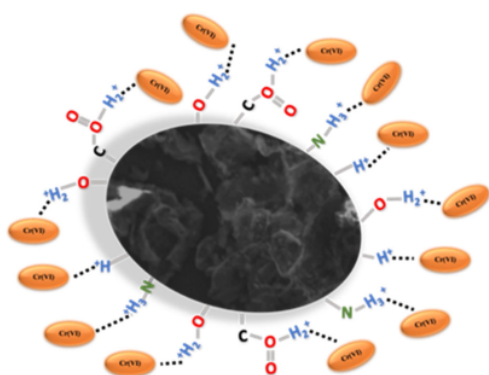


Fig 9. Illustration of the Cr(VI) adsorption mechanism

adsorption did not show much change. However, there is a band around 3700 cm^{-1} which indicates that the adsorbed Cr(VI) metal binds to the N-H group. On the other hand, the dominant band at 1600 cm^{-1} indicates that the adsorbed Cr(VI) binds to C=O. Based on the spectrochemical series which shows that C=O is a strong ligand, the chemical adsorption mechanism that dominates Cr(VI) may tend to bind with C=O compared to N-H.

CONCLUSION

The development of biosorbent material from Duku peel to Hc through the hydrothermal carbonization method has been successfully carried out. This is evidenced by the FTIR characterization data which shows the characteristic functional groups of Duku peel on Hc.

In addition, the XRD data also shows distinctive diffraction at an angle of 21.18° (002) which is a characteristic of carbon materials with heterogeneous morphology particle. The superiority of the hydrothermal carbonization method which can increase the surface area of the adsorbent is proven by the nitrogen adsorption-desorption analysis data. The surface area of the Duku peel which was initially only $12.343\text{ m}^2/\text{g}$, after going through the hydrothermal carbonization process into Hc material increased twice to $22.635\text{ m}^2/\text{g}$. Furthermore, the increase of surface area is analogous to increasing adsorption capacity. From the adsorption study, this material has good performance for adsorption, from 42.194 mg/g (Duku peel) to 80.645 mg/g (Hc); followed by PSO kinetic study, Langmuir isotherm study. Hc material which has a surface area and adsorption capacity greater than Duku peel indicates that the hydrothermal carbonization method is effective for the synthesis of the adsorbent material.

ACKNOWLEDGMENTS

We wish to express our gratitude to the research center Inorganic Materials and Complexes, Sriwijaya University for instrument analysis.

REFERENCES

- [1] Batool, A., and Valiyaveetil, S., 2021, Chemical transformation of soya waste into stable adsorbent for enhanced removal of methylene blue and

- neutral red from water, *J. Environ. Chem. Eng.*, 9 (1), 104902.
- [2] Zheng, C., Wu, Q., Hu, X., Wang, Y., Chen, Y., Zhang, S., and Zheng, H., 2021, Adsorption behavior of heavy metal ions on a polymer-immobilized amphoteric biosorbent: Surface interaction assessment, *J. Hazard. Mater.*, 403, 123801.
- [3] Rouhaninezhad, A.A., Hojati, S., and Masir, M.N., 2020, Adsorption of Cr (VI) onto micro- and nanoparticles of palygorskite in aqueous solutions: Effects of pH and humic acid, *Ecotoxicol. Environ. Saf.*, 206, 111247.
- [4] López Zavala, M.Á., Romero-Santana, H., and Monárrez-Cordero, B.E., 2020, Removal of Cr(VI) from water by adsorption using low cost clay-perlite-iron membranes, *J. Water Process Eng.*, 38, 101672.
- [5] Tadjenant, Y., Dokhan, N., Barras, A., Addad, A., Jijie, R., Szunerits, S., and Boukherroub, R., 2020, Graphene oxide chemically reduced and functionalized with KOH-PEI for efficient Cr(VI) adsorption and reduction in acidic medium, *Chemosphere*, 258 127316.
- [6] Ahmed, D.N., Naji, L.A., Faisal, A.A.H., Al-Ansari, N., and Naushad, M., 2020, Waste foundry sand/MgFe-layered double hydroxides composite material for efficient removal of Congo red dye from aqueous solution, *Sci. Rep.*, 10 (1), 2042.
- [7] Sujatha, S., and Sivarethinamohan, R., 2020, A critical review of Cr(VI) ion effect on mankind and its amputation through adsorption by activated carbon, *Mater. Today: Proc.*, 37, 1158–1162.
- [8] González, B., and Manyà, J.J., 2020, Activated olive mill waste-based hydrochars as selective adsorbents for CO₂ capture under postcombustion conditions, *Chem. Eng. Process.*, 149, 107830.
- [9] Tran, T.H., Le, A.H., Pham, T.H., Nguyen, D.T., Chang, S.W., Chung, W.J., and Nguyen, D.D., 2020, Adsorption isotherms and kinetic modeling of methylene blue dye onto a carbonaceous hydrochar adsorbent derived from coffee husk waste, *Sci. Total Environ.*, 725, 138325.
- [10] Rudiyanasyah., R., Alimuddin, A.H., Masriani, M., Muharini, R., and Proksch, P., 2018, New tetranortriterpenoids, langsatides A and B from the seeds of *Lansium domesticum* Corr. (Meliaceae), *Phytochem. Lett.*, 23, 90–93.
- [11] Hua, Y., Zheng, X., Xue, L., Han, L., He, S., Mishra, T., Feng, F., Yang, L., and Xing, B., 2020, Microbial aging of hydrochar as a way to increase cadmium ion adsorption capacity: Process and mechanism, *Bioresour. Technol.*, 300, 122708.
- [12] Madduri, S., Elsayed, I., and Hassan, E.B., 2020, Novel oxone treated hydrochar for the removal of Pb(II) and methylene blue (MB) dye from aqueous solutions, *Chemosphere*, 260, 127683.
- [13] Wang, Q., Zhou, C., Kuang, Y.J., Jiang, Z.H., and Yang, M., 2020, Removal of hexavalent chromium in aquatic solutions by pomelo peel, *Water Sci. Eng.*, 13 (1), 65–73.
- [14] Li, F., Zimmerman, A.R., Hu, X., and Gao, B., 2020, Removal of aqueous Cr(VI) by Zn- and Al-modified hydrochar, *Chemosphere*, 260, 127610.
- [15] Shi, Y., Zhang, T., Ren, H., Kruse, A., and Cui, R., 2018, Polyethylene imine modified hydrochar adsorption for chromium (VI) and nickel (II) removal from aqueous solution, *Bioresour. Technol.*, 247, 370–379.
- [16] Shankar, S., Jaiswal, L., Aparna, R.S.L., and Prasad, R.G.S.V., 2014, Synthesis, characterization, *in vitro* biocompatibility, and antimicrobial activity of gold, silver and gold silver alloy nanoparticles prepared from *Lansium domesticum* fruit peel extract, *Mater. Lett.*, 137, 75–78.
- [17] Lam, Y.F., Lee, L.Y., Chua, S.J., Lim, S.S., and Gan, S., 2016, Insights into the equilibrium, kinetic and thermodynamics of nickel removal by environmental friendly *Lansium domesticum* peel biosorbent, *Ecotoxicol. Environ. Saf.*, 127, 61–70.
- [18] Yadav, S., Tyagiand, D.K., and Yadav, O.P., 2011, Equilibrium and kinetic studies on adsorption of Congo red dye from aqueous solution onto rice husk carbon, *Nat. Environ. Pollut. Technol.*, 10 (4), 551–558.
- [19] Palapa, N.R., Juleanti, N., Normah, N., Taher, T., and Lesbani, A., 2020, Unique adsorption properties of malachite green on interlayer space of

- Cu-Al and Cu-Al-SiW₁₂O₄₀ layered double hydroxides, *Bull. Chem. React. Eng. Catal.*, 15 (3), 653–661.
- [20] Bamroongwongdee, C., Suwannee, S., and Kongsomsaksiri, M., 2019, Adsorption of Congo red from aqueous solution by surfactant-modified rice husk: Kinetic, isotherm and thermodynamic analysis, *Songklanakarin J. Sci. Technol.*, 41 (5), 1076–1083.
- [21] Batool, F., Akbar, J., Iqbal, S., Noreen, S., and Bukhari, S.N.A., 2018, Study of isothermal, kinetic, and thermodynamic parameters for adsorption of cadmium: an overview of linear and nonlinear approach and error analysis, *Bioinorg. Chem. Appl.*, 2018, 3463724.
- [22] He, H., Zhang, N., Chen, N., Lei, Z., Shimizu, K., and Zhang, Z., 2019, Efficient phosphate removal from wastewater by MgAl-LDHs modified hydrochar derived from tobacco stalk, *Bioresour. Technol. Rep.*, 8, 100348.
- [23] Liu, Y., Zhu, X., Qian, F., Zhang, S., and Chen, J., 2014, Magnetic activated carbon prepared from rice straw-derived hydrochar for triclosan removal, *RSC Adv.*, 4 (109), 63620–63626.
- [24] Belete, Y.Z., Ziemann, E., Gross, A., and Bernstein, R., 2020, Facile activation of sludge-based hydrochar by Fenton oxidation for ammonium adsorption in aqueous media, *Chemosphere*, 273, 128526.
- [25] Jiang, Y.H., Li, A.Y., Deng, H., Ye, C.H., and Li, Y., 2019, Phosphate adsorption from wastewater using ZnAl-LDO-loaded modified banana straw biochar, *Environ. Sci. Pollut. Res.*, 26 (18), 18343–18353.
- [26] Juleanti, N., Palapa, N.R., Taher, T., Hidayati, N., Putri, B.I., and Lesbani, A., 2021, The capability of biochar-based CaAl and MgAl composite materials as adsorbent for removal Cr(VI) in aqueous solution, *Sci. Technol. Indones.*, 6 (3), 196–203.
- [27] Wijaya, A., Bahar Nur Siregar, P.M.S., Priambodo, A., Palapa, N.R., Taher, T., and Lesbani, A., 2021, Innovative modified of Cu-Al/C (C = biochar, graphite) composites for removal of procion red from aqueous solution, *Sci. Technol. Indones.*, 6 (4), 228–234.
- [28] Bahar Nur Siregar, P.M.S., Palapa, N.R., Wijaya, A., Fitri, E.S., and Lesbani, A., 2021, Structural stability of Ni/Al layered double hydroxide supported on graphite and biochar toward adsorption of Congo red, *Sci. Technol. Indones.*, 6 (2), 85–95.
- [29] Sahmoune, M.N., 2019, Evaluation of thermodynamic parameters for adsorption of heavy metals by green adsorbents, *Environ. Chem. Lett.*, 17 (2), 697–704.
- [30] Palapa, N.R., Juleanti, N., Mohadi, R., Taher, T., Rachmat, A., and Lesbani, A., 2020, Copper aluminum layered double hydroxide modified by biochar and its application as an adsorbent for procion red, *J. Water Environ. Technol.*, 18 (6), 359–371.
- [31] Palapa, N.R., Mohadi, R., Rachmat, A., and Lesbani, A., 2020, Adsorption study of malachite green removal from aqueous solution using Cu/M³⁺ (M³⁺ = Al, Cr) layered double hydroxide, *Mediterr. J. Chem.*, 10 (1), 33–45.
- [32] Shakya, A., and Agarwal, T., 2019, Removal of Cr(VI) from water using pineapple peel derived biochars: Adsorption potential and re-usability assessment, *J. Mol. Liq.*, 293, 111497.
- [33] Khalil, U., Bilal Shakoor, M., Ali, S., Rizwan, M., Nasser Alyemeni, M., and Wijaya, L., 2020, Adsorption-reduction performance of tea waste and rice husk biochars for Cr(VI) elimination from wastewater, *J. Saudi Chem. Soc.*, 24 (11), 799–810.
- [34] Qhubu, M.C., Mgidlana, L.G., Madikizela, L.M., and Pakade, V.E., 2021, Preparation, characterization and application of activated clay biochar composite for removal of Cr(VI) in water: Isotherms, kinetics and thermodynamics, *Mater. Chem. Phys.*, 260, 124165.
- [35] Suvarna, K.S., and Binitha, N.N., 2020, Graphene preparation by jaggery assisted ball-milling of graphite for the adsorption of Cr(VI), *Mater. Today: Proc.*, 25, 236–240.
- [36] El-Nemr, M.A., Ismail, I.M.A., Abdelmonem, N.M., El Nemr, A., and Ragab, S., 2020, Amination of biochar surface from watermelon peel for toxic

- chromium removal enhancement, *Chin. J. Chem. Eng.*, 36, 199–222.
- [37] Yang, X., Zhao, Z., Yu, Y., Shimizu, K., Zhang, Z., Lei, Z., and Lee, D.J., 2020, Enhanced biosorption of Cr(VI) from synthetic wastewater using algal-bacterial aerobic granular sludge: Batch experiments, kinetics and mechanisms, *Sep. Purif. Technol.*, 251, 117323.
- [38] Zhang, H., Xiao, R., Li, R., Ali, A., Chen, A., and Zhang, Z., 2020, Enhanced aqueous Cr(VI) removal using chitosan-modified magnetic biochars derived from bamboo residues, *Chemosphere*, 261, 127694.
- [39] Javadian, H., Ahmadi, M., Ghiasvand, M., Kahrizi, S., and Katal, R., 2013, Removal of Cr(VI) by modified brown algae *Sargassum bevanom* from aqueous solution and industrial wastewater, *J. Taiwan Inst. Chem. Eng.*, 44 (6), 977–989.
- [40] Husien, S., Labena, A., El-Beley, E.F., Mahmoud, H.M., and Hamouda, A.S., 2019, Adsorption studies of hexavalent chromium [Cr (VI)] on micro-scale biomass of *Sargassum dentifolium*, Seaweed, *J. Environ. Chem. Eng.*, 7 (6), 103444.

Low-Cost Yet High-Performance Hydrochar Derived from Hydrothermal Carbonization of Duku Peel (*Lansium domesticum*) for Cr(VI) Removal from Aqueous Solution

ORIGINALITY REPORT

29%
SIMILARITY INDEX

19%
INTERNET SOURCES

23%
PUBLICATIONS

7%
STUDENT PAPERS

PRIMARY SOURCES

1	www.ecoeet.com Internet Source	3%
2	Submitted to Sriwijaya University Student Paper	2%
3	link.springer.com Internet Source	1%
4	www.mdpi.com Internet Source	1%
5	Submitted to School of Business and Management ITB Student Paper	1%
6	N. Normah, N. Juleanti, N. R. Palapa, T. Taher, P. M. S. B. N. Siregar, A. Wijaya, A. Lesbani. " Hydrothermal carbonization of rambutan peel () as a Green and low-cost adsorbent for Fe(II) removal from aqueous solutions ", Chemistry and Ecology, 2022 Publication	1%

7	journal.ugm.ac.id Internet Source	1 %
8	Arini Fousty Badri, Novie Juleanti, Neza Rahayu Palapa, Yuliza Hanifah, Risfidian Mohadi, Mardiyanto Mardiyanto, Aldes Lesbani. "Oxalate Intercalated Mg/Cr Layered Double Hydroxide as Adsorbent of Methyl Red and Methyl Orange From Aqueous Solution", Ecological Engineering & Environmental Technology, 2021 Publication	1 %
9	jurnal.ugm.ac.id Internet Source	1 %
10	www.jeeng.net Internet Source	1 %
11	ujcontent.uj.ac.za Internet Source	1 %
12	geomatejournal.com Internet Source	1 %
13	www.researchgate.net Internet Source	1 %
14	Rudiyansyah, Andi Hairil Alimuddin, Masriani, Rini Muharini, Peter Proksch. "New tetranortriterpenoids, langsungides A and B from the seeds of Lansium domesticum Corr. (Meliaceae)", Phytochemistry Letters, 2018	1 %

15

Yimin Huang, Bing Wang, Jiapei Lv, Yingnan He, Hucai Zhang, Wenyan Li, Yongtao Li, Thomas Wågberg, Guangzhi Hu. "Facile synthesis of sodium lignosulfonate/polyethyleneimine/sodium alginate beads with ultra-high adsorption capacity for Cr(VI) removal from water", *Journal of Hazardous Materials*, 2022

Publication

<1 %

16

eprints.whiterose.ac.uk

Internet Source

<1 %

17

Submitted to IIT Delhi

Student Paper

<1 %

18

Qun Jiang, Weiling Xie, Siyue Han, Yifan Wang, Ying Zhang. "Enhanced adsorption of Pb(II) onto modified hydrochar by polyethyleneimine or H₃PO₄: An analysis of surface property and interface mechanism", *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2019

Publication

<1 %

19

Submitted to University of Hong Kong

Student Paper

<1 %

20

koreascience.kr

Internet Source

<1 %

scholarhub.ui.ac.id

21

Internet Source

<1 %

22

"Applied Water Science", Wiley, 2021

Publication

<1 %

23

**Submitted to Higher Education Commission
Pakistan**

Student Paper

<1 %

24

repository.najah.edu

Internet Source

<1 %

25

**Risfidian Mohadi, Radja Nardo Purba, Dedi
Rohendi, Aldes Lesbani. " Kinetics and
Thermodynamics Interaction Between
Bentonite Inserted Organometallic
Compounds [Cr O(OOCH) (H O)](NO) With
Methylene Blue Dye In Aqueous Medium ",
IOP Conference Series: Materials Science and
Engineering, 2018**

Publication

<1 %

26

**Volkan Ugraskan, Birol Isik, Ozlem Yazici, Fatih
Cakar. "Removal of Safranin T by a highly
efficient adsorbent (Cotinus Coggyria
leaves): Isotherms, kinetics, thermodynamics,
and surface properties", Surfaces and
Interfaces, 2022**

Publication

<1 %

27

Submitted to University of KwaZulu-Natal

Student Paper

<1 %

28 Wei Zhang, Anlin Long, Ji Ou, Xin Zeng et al. "Enhanced removal of hexavalent chromium from aqueous solution by functional polymer-wrapped gamma-alumina composite adsorbent", Environmental Technology & Innovation, 2021
Publication <1 %

29 hal-centralesupelec.archives-ouvertes.fr
Internet Source <1 %

30 www.tandfonline.com
Internet Source <1 %

31 Risfidian Mohadi, Patimah Mega Syah Bahar Nur Siregar, Neza Rahayu Palapa, Tarmizi Taher, Aldes Lesbani. "Layered Double Hydroxide/Chitosan Composite (Mg-Al/CT) as a Selective Adsorbent in Congo Red Adsorption from Aqueous Solution", Ecological Engineering & Environmental Technology, 2022
Publication <1 %

32 dspace.unipampa.edu.br
Internet Source <1 %

33 www.hindawi.com
Internet Source <1 %

34 Bakri Rio Rahayu, Tarmizi Taher, Poedji Loekitowati Hariani, Aldes Lesbani. "Congo red and direct yellow dye removal from

aqueous solution by Zn/Cr layered double hydroxides", AIP Publishing, 2018

Publication

35

Sheng Cao, Shao-zhong Hu, Dan Luo, Ting Huang, Nan Zhang, Yan-zhou Lei, Yong Wang. "Bio-inspired one-step structure adjustment and chemical modification of melamine foam toward highly efficient removal of hexavalent chromium ions", Separation and Purification Technology, 2021

Publication

<1 %

36

[mdpi-res.com](https://www.mdpi-res.com)

Internet Source

<1 %

37

www.scribd.com

Internet Source

<1 %

38

Aida H. Shobier, Manal M. El-Sadaawy, Ghada F. El-Said. "Removal of hexavalent chromium by ecofriendly raw marine green alga *Ulva fasciata*: Kinetic, thermodynamic and isotherm studies", The Egyptian Journal of Aquatic Research, 2020

Publication

<1 %

39

Melantina Oktrianty, Neza Palapa, Risfidian Mohadi, Aldes Lesbani. "Effective Removal of Iron (II) from Aqueous Solution by Adsorption using Zn/Cr Layered Double Hydroxides Intercalated with Keggin Ion", Journal of Ecological Engineering, 2020

<1 %

40

Ming Ao, Xiaoting Chen, Tenghaobo Deng, Shengsheng Sun, Yetao Tang, Jean Louis Morel, Rongliang Qiu, Shizhong Wang. "Chromium biogeochemical behaviour in soil-plant systems and remediation strategies: A critical review", *Journal of Hazardous Materials*, 2022

Publication

<1 %

41

Preeyanghaa Mani, Youngae Kim, Sandeep Kumar Lakhera, B. Neppolian, Heechul Choi. "Complete Arsenite Removal from Groundwater by UV Activated Potassium Persulfate and Iron Oxide Impregnated Granular Activated Carbon", *Chemosphere*, 2021

Publication

<1 %

42

Yulong Wang, Hupeng Liu, Shaofeng Wang, Xuhui Li, Xin Wang, Yongfeng Jia. "Simultaneous removal and oxidation of arsenic from water by δ -MnO₂ modified activated carbon", *Journal of Environmental Sciences*, 2020

Publication

<1 %

43

Zhao, Yingxin, Shengjiong Yang, Dahu Ding, Jie Chen, Yingnan Yang, Zhongfang Lei, Chuanping Feng, and Zhenya Zhang. "Effective adsorption of Cr (VI) from aqueous

<1 %

solution using natural Akadama clay", Journal of Colloid and Interface Science, 2013.

Publication

44

coek.info

Internet Source

<1 %

45

lutpub.lut.fi

Internet Source

<1 %

46

media.neliti.com

Internet Source

<1 %

47

opac.ll.chiba-u.jp

Internet Source

<1 %

48

Anastasia Memetova, Inderjeet Tyagi, Rama Rao Karri, Suhas et al. "Synthesis of carbon energized materials with directed regulation of specific surface and pore structure as potential adsorbent for methane mitigation", Journal of Environmental Chemical Engineering, 2022

Publication

<1 %

49

Asmaa K. Mohamed. " Magnetic Metal–Organic Frameworks Embedded in a Reduced Graphene Oxide Hydrogel Network as a Promising Hybrid Nanocomposite for Cr(VI) and -Nitrophenol Removal ", Journal of Chemical & Engineering Data, 2021

Publication

<1 %

50

Cindy Samet, Suresh Valiyaveetil. "Fruit and Vegetable Peels as Efficient Renewable Adsorbents for Removal of Pollutants from Water: A Research Experience for General Chemistry Students", Journal of Chemical Education, 2018

Publication

<1 %

51

He Li, Wei Li, Hui Yang, Wenjiang Li, Zhihao Yuan, Minfang Chen, Carla Bittencourt, Rony Snyders. "Photocatalytic properties of MoS₂ nanoflakes vertically assembled on reduced graphene oxide", Thin Solid Films, 2018

Publication

<1 %

52

Peng Gao, Yujie Feng, Zhaohan Zhang, Ce Wang, Junfeng Liu, Nanqi Ren. "Kinetic and Thermodynamic Studies of Phenolic Compounds' Adsorption on River Sediment", Soil and Sediment Contamination: An International Journal, 2012

Publication

<1 %

53

Prangya Ranjan Rout, Puspendu Bhunia, Rajesh Roshan Dash. "A mechanistic approach to evaluate the effectiveness of red soil as a natural adsorbent for phosphate removal from wastewater", Desalination and Water Treatment, 2014

Publication

<1 %

54

Sandipan Bhattacharya, Papita Das, Avijit Bhowal, Abhijit Saha. "Thermal, Chemical and ultrasonic assisted synthesis of carbonized Biochar and its application for reducing Naproxen: Batch and Fixed bed study and subsequent optimization with response surface methodology (RSM) and artificial neural network (ANN)", *Surfaces and Interfaces*, 2021

Publication

<1 %

55

Shella Permatasari Santoso, Alfin Kurniawan, Artik Elisa Angkawijaya, Hardy Shuwanto et al. "Removal of heavy metals from water by macro-mesoporous calcium alginate-exfoliated clay composite sponges", *Chemical Engineering Journal*, 2023

Publication

<1 %

56

Wen-bo Tan, Dan Luo, Wei Song, Yan-yan Lu, Nuo Cheng, Jia-bin Zhang, Ting Huang, Yong Wang. "Polydopamine-assisted polyethyleneimine grafting on electrospun cellulose acetate/TiO₂ fibers towards highly efficient removal of Cr(VI)", *European Polymer Journal*, 2022

Publication

<1 %

57

biocharproject.org

Internet Source

<1 %

58

Internet Source

<1 %

59

journal.gnest.org

Internet Source

<1 %

60

waset.org

Internet Source

<1 %

61

www.ukm.my

Internet Source

<1 %

62

K. Rambabu, G. Bharath, Abdul Hai, Shaohong Luo, Kin Liao, Mohammad Abu Haija, Fawzi Banat, Mu. Naushad. "Development of watermelon rind derived activated carbon/manganese ferrite nanocomposite for cleaner desalination by capacitive deionization", Journal of Cleaner Production, 2020

Publication

<1 %

63

Mohamed A. El-Nemr, Ibrahim M.A. Ismail, Nabil M. Abdelmonem, Ahmed El Nemr, Safaa Ragab. "Amination of biochar surface from watermelon peel for toxic chromium removal enhancement", Chinese Journal of Chemical Engineering, 2020

Publication

<1 %

64

P. Senthil Kumar, R. Gayathri, B. Senthil Rathi. "A review on adsorptive separation of toxic metals from aquatic system using biochar

<1 %

produced from agro-waste", Chemosphere, 2021

Publication

65

Abhishek Kumar, Tanushree Bhattacharya, Wasim Akram Shaikh, Arpita Roy, Santanu Mukherjee, Manish Kumar. "Performance evaluation of crop residue and kitchen waste-derived biochar for eco-efficient removal of arsenic from soils of the Indo-Gangetic plain: A step towards sustainable pollution management", Environmental Research, 2021

Publication

<1 %

66

Ali Khadir, Mahsa Motamedi, Ebrahim Pakzad, Mika Sillanpää, Shreya Mahajan. "The prospective utilization of Luffa fibres as a lignocellulosic bio-material for environmental remediation of aqueous media: a Review", Journal of Environmental Chemical Engineering, 2020

Publication

<1 %

67

Anyu Li, Yue Zhang, Wenzhan Ge, Yutong Zhang, Lihu Liu, Guohong Qiu. "Removal of heavy metals from wastewaters with biochar pyrolyzed from MgAl-layered double hydroxide-coated rice husk: Mechanism and application", Bioresource Technology, 2021

Publication

<1 %

68

Ozdemir, E.. "Process optimization for Cr(VI) adsorption onto activated carbons by experimental design", Chemical Engineering Journal, 20110801

Publication

<1 %

69

Wei Zhang, Ji Ou, Meiyi Tang, Qiulai He et al. "Physically-crosslinked activated CaCO₃/polyaniline-polypyrrole-modified GO/alginate hydrogel sorbent with highly efficient removal of copper(II) from aqueous solution", Chemical Engineering Journal, 2021

Publication

<1 %

70

Yuvaraj Palani, Raghava Rao Jonnalagadda, Nishad Fathima Nishter. "Adsorption on activated carbon derived from tannery fleshing waste: Adsorption isotherms, thermodynamics, and kinetics", Environmental Progress & Sustainable Energy, 2017

Publication

<1 %

Exclude quotes Off

Exclude matches Off

Exclude bibliography On