



catalysts

an Open Access Journal by MDPI

IMPACT
FACTOR
4.501

CITESCORE
5.5

Affiliated Societies:

| **Romanian Catalysis Society (RCS)**



Academic Open Access Publishing
since 1996



catalysts

an Open Access Journal by MDPI









Editor-in-Chief

Prof. Dr. Keith Hohn

Message from the Editor-in-Chief

Catalysts impact the world through the production of fuels to power our economies, by the synthesis of materials that improve our lives, and by the destruction of harmful pollutants. Cutting-edge research in catalysis pushes forward our understanding of how catalysts work, ultimately leading to better catalytic processes and greater impacts on society. *Catalysts* offers you the opportunity to publish your research in an open access format, providing scholars with quick access to your research. Please consider publishing in *Catalysts* when preparing your next paper.

Author Benefits

-  **Open Access** Unlimited and free access for readers
-  **No Copyright Constraints** Retain copyright of your work and free use of your article
-  **Thorough Peer-Review**
-  **2021 Impact Factor: 4.501 (Journal Citation Reports - Clarivate, 2022)**
-  **Discounts on Article Processing Charges (APC)** If you belong to an institute that participates with the MDPI Institutional Open Access Program (IOAP)
-  **No Space Constraints, No Extra Space or Color Charges** No restriction on the length of the papers, number of figures or colors
-  **Coverage by Leading Indexing Services** Science Citation Index Expanded (Web of Science), Scopus (2021 CiteScore: 5.5) and other databases
-  **Rapid Publication** First decision provided to authors approximately 13 days after submission; acceptance to publication is undertaken in 2.7 days (median values for papers published in this journal in the first half of 2022)

IMPACT
FACTOR
4.501

CITESCORE
5.5

Aims and Scope

Catalysts (ISSN 2073-4344) is an international open access journal of catalysts and catalyzed reactions. *Catalysts* publishes reviews, regular research papers (articles) and short communications. Our aim is to encourage scientists to publish their experimental and theoretical results in as much detail as possible, therefore, there is no restriction on the length of the papers. The full experimental details must be provided so that the results can be reproduced.

Photocatalysis

Electrocatalysis

Environmental catalysis

Biocatalysis, enzymes, enzyme catalysis

Catalysis for biomass conversion

Organocatalysis, catalysis in organic and polymer chemistry

Nanostructured Catalysts

Catalytic materials

Computational catalysis

Kinetics of catalytic reactions

Catalytic Reaction Engineering

Section Editors-in-Chief

Catalytic Materials
Dr. Leonarda Francesca Liotta

Environmental Catalysis
Prof. Dr. Jean-François Lamonier

Photocatalysis
Prof. Dr. Detlef W. Bahnemann

Electrocatalysis
Dr. Vincenzo Baglio

Nanostructured Catalysts
Prof. Dr. Adam F. Lee

Catalysis in Organic and Polymer Chemistry
Prof. Dr. Kotohiro Nomura

Biocatalysis
Dr. Evangelos Topakas

Biomass Catalysis
Dr. Juan J. Bravo-Suarez

Computational Catalysis
Prof. Dr. C. Heath Turner

Catalytic Reaction Engineering
Prof. Dr. Hugo de Lasa

Industrial Catalysis
Prof. Dr. Russell R. Chianelli

Catalysis for Sustainable Energy
Prof. Dr. Maria A. Goula

Catalysis for Pharmaceuticals
Prof. Dr. Andres R. Alcantara

Editorial Office

Catalysts Editorial Office
catalysts@mdpi.com
MDPI, St. Alban-Anlage 66
4052 Basel, Switzerland
Tel: +41 61 683 77 34
www.mdpi.com
mdpi.com/journal/catalysts

MDPI is a member of



Affiliated Societies



Follow Us

 facebook.com/MDPIOpenAccessPublishing

 twitter.com/MDPIOpenAccess

 linkedin.com/company/mdpi

 weibo.com/mdpicn

 Wechat: MDPI-China

 blog.mdpi.com



www.mdpi.com

mdpi.com/journal/catalysts

See www.mdpi.com for a full list of offices and contact information. MDPI is a company registered in Basel, Switzerland, No. CH-270.3.014.334-3, whose registered office is at St. Alban-Anlage 66, CH-4052 Basel, Switzerland.

Basel, July 2022



[Submit to Catalysts](#)
[Review for Catalysts](#)

[Share](#)

Journal Menu

- [Catalysts Home](#)
- [Aims & Scope](#)
- [Editorial Board](#)
- [Reviewer Board](#)
- [Topical Advisory Panel](#)
- [Instructions for Authors](#)
- [Special Issues](#)
- [Topics](#)
- [Sections & Collections](#)
- [Article Processing Charge](#)
- [Indexing & Archiving](#)
- [Editor's Choice Articles](#)
- [Most Cited & Viewed](#)
- [Journal Statistics](#)
- [Journal History](#)
- [Journal Awards](#)
- [Society Collaborations](#)
- [Conferences](#)
- [Editorial Office](#)

Journal Browser

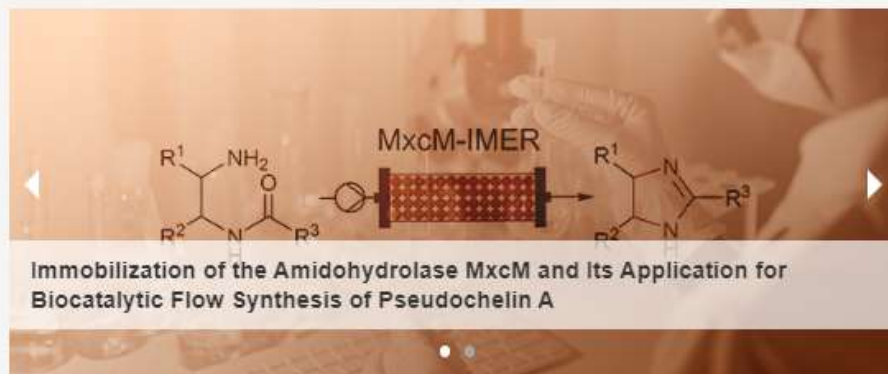

Immobilization of the Amidohydrolase MxcM and Its Application for Biocatalytic Flow Synthesis of Pseudocheilin A

Catalysts

Catalysts is a peer-reviewed open access journal of catalysts and catalyzed reactions published monthly online by MDPI. The Romanian Catalysis Society (RCS) are partners of *Catalysts* journal and its members receive a discount on the article processing charge.

- Open Access** — free for readers, with article processing charges (APC) paid by authors or their institutions.
- High Visibility:** indexed within Scopus, SCIE (Web of Science), Inspec, CAPlus / SciFinder, CAB Abstracts, and other databases.
- Journal Rank:** JCR - Q2 (*Chemistry, Physical*) / CiteScore - Q1 (*General Environmental Science*)
- Rapid Publication:** manuscripts are peer-reviewed and a first decision is provided to authors approximately 12.7 days after submission; acceptance to publication is undertaken in 3.3 days (median values for papers published in this journal in the second half of 2022).
- Recognition of Reviewers:** reviewers who provide timely, thorough peer-review reports receive vouchers entitling them to a discount on the APC of their next publication in any MDPI journal, in appreciation of the work done.

Impact Factor: 4.501 (2021); 5-Year Impact Factor: 4.641 (2021)

[Imprint Information](#) [Journal Flier](#) [Open Access](#) ISSN: 2073-4344

E-Mail Alert

Add your e-mail address to receive forthcoming issues of this journal:

News

31 March 2023

Meet Us at the 7th Conference on New Energy and New Chemical Materials Cum National Symposium on Energy Conversion and Storage Materials, 7–9 April 2023, Wuhan, China



[View PDF](#)

13 March 2023

MDPI's Newly Launched Journals in December 2022

7 March 2023

Displaying Co-Authors' Email Addresses on the Webpage of Published Papers


[Submit to Catalysts](#)
[Review for Catalysts](#)

Journal Menu

- [Catalysts Home](#)
- [Aims & Scope](#)
- [Editorial Board](#)
- [Reviewer Board](#)
- [Topical Advisory Panel](#)
- [Instructions for Authors](#)
- [Special Issues](#)
- [Topics](#)
- [Sections & Collections](#)
- [Article Processing Charge](#)
- [Indexing & Archiving](#)
- [Editor's Choice Articles](#)
- [Most Cited & Viewed](#)
- [Journal Statistics](#)
- [Journal History](#)
- [Journal Awards](#)
- [Society Collaborations](#)
- [Conferences](#)
- [Editorial Office](#)

Journal Browser

Editorial Board

- Catalytic Materials Section
- Environmental Catalysis Section
- Photocatalysis Section
- Electrocatalysis Section
- Nanostructured Catalysts Section
- Catalysis in Organic and Polymer Chemistry Section
- Biocatalysis Section
- Biomass Catalysis Section
- Computational Catalysis Section
- Catalytic Reaction Engineering Section
- Industrial Catalysis Section
- Catalysis for Sustainable Energy Section
- Catalysis for Pharmaceuticals Section

Members (616)

Prof. Dr. Keith Hohn [Website](#)

Editor-in-Chief

Chemical, Paper, and Biomedical Engineering Department, Miami University, Oxford, OH 45056, USA

Interests: catalysis and reaction engineering; natural gas conversion; oxidative dehydrogenation of light hydrocarbons; millisecond contact time reactors; nanoparticle catalysts; biomass conversion

Special Issues, Collections and Topics in MDPI journals



Dr. Enrique Sastre [Website](#)

Section Associate Editor

Molecular Sieves Group, Instituto de Catálisis y Petroleoquímica, ICP-CSIC, C/ Marie Curie, 2, 28049 Madrid, Spain

Interests: catalytic applications of nanoporous materials; zeolites; zeotypes; thermal analyses; MTO; MTA; MTH



Prof. Dr. Andres R. Alcantara [Website](#)

Section Editor-in-Chief

Department of Chemistry in Pharmaceutical Sciences, Faculty of Pharmacy, Complutense University, Plaza De Ramon y Cajal, S/N University City, Madrid, Spain



FACTOR
4.501

CITESCORE
5.5



- Journal History
- Journal Awards
- Society Collaborations
- Conferences
- Editorial Office

Journal Browser

- > Forthcoming issue
- > Current issue

Vol. 13 (2023)	Vol. 6 (2016)
Vol. 12 (2022)	Vol. 5 (2015)
Vol. 11 (2021)	Vol. 4 (2014)
Vol. 10 (2020)	Vol. 3 (2013)
Vol. 9 (2019)	Vol. 2 (2012)
Vol. 8 (2018)	Vol. 1 (2011)
Vol. 7 (2017)	

Thanks
A Million
to the
2,700,000
authors

Molecular Sieves Group, Instituto de Catalisis y Petroleoquimica, ICP-CSIC, C/ Manacore, 2, 28049 Madrid, Spain

Interests: catalytic applications of nanoporous materials; zeolites; zeotypes; thermal analyses; MTO; MTA; MTH



Prof. Dr. Andres R. Alcantara [Website](#)

Section Editor-in-Chief

Department of Chemistry in Pharmaceutical Sciences, Faculty of Pharmacy, Complutense University, Plaza De Ramon y Cajal, S/N University City, Madrid, Spain

Interests: enzymatic synthesis of drugs and bioactive compounds; sustainable processes; biocatalyst upgrading; pharmaceutical industry; organic chemistry; pharmaceutical chemistry
Special Issues, Collections and Topics in MDPI journals



Dr. Vincenzo Baglio * [Website](#)

Section Editor-in-Chief

CNR-ITAE Institute for Advanced Energy Technologies "N. Giordano", Via Salita S. Lucia sopra Contesse 5, 98126 Messina, Italy

Interests: polymer electrolyte fuel cells; direct alcohol fuel cells; water electrolysis; metal-air batteries; dye-sensitized solar cells; photo-electrolysis; carbon dioxide electro-reduction

* Section: Electrocatalysis

Special Issues, Collections and Topics in MDPI journals



Prof. Dr. Detlef W. Bahnemann * [Website1](#) [Website2](#)

Section Editor-in-Chief

Laboratory of Photoactive Nanocomposite Materials, Saint-Petersburg State University, Ulyanovskaya Str. 1, Peterhof, 198504 Saint-Petersburg, Russia

Interests: photocatalysis; self-cleaning; superhydrophilic; antibacterial surfaces; metal and semiconductor particles; nanocrystalline transparent coatings; functional test according to DIN; CEN and ISO

* Section: Photocatalysis

Special Issues, Collections and Topics in MDPI journals



Dr. Juan J. Bravo-Suarez * [Website](#)

Section Editor-in-Chief

Chemical & Petroleum Engineering Department, The University of Kansas, Lawrence, KS 66045, USA

Interests: heterogeneous catalysis; advanced catalyst synthesis; in situ/operando spectroscopy and spectrokineitics; reaction kinetics; biomass and alternative feedstock conversion; oxidation reactions; fuels and chemicals

* Section: Biomass Catalysis



[Back to Top](#)



Search for Articles:

Title / Keyword

Author / Affiliation / Email

Catalysts

All Article Types

Search

Advanced

Journals / Catalysts / Volume 12 / Issue 12

IMPACT FACTOR
4.501

CITESCORE
5.5




Submit to Catalysts

Review for Catalysts

Journal Menu

- Catalysts Home
- Aims & Scope
- Editorial Board
- Reviewer Board
- Topical Advisory Panel
- Instructions for Authors
- Special Issues
- Topics
- Sections & Collections
- Article Processing Charge
- Indexing & Archiving
- Editor's Choice Articles
- Most Cited & Viewed

Catalysts, Volume 12, Issue 12 (December 2022) – 188 articles

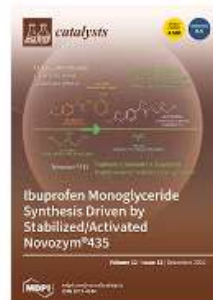

Cover Story (view full-size image): With the increase in biodiesel production in recent years, excess production of glycerol is a reality. Glycerol is now a platform chemical that can be transformed into various chemical intermediates, including prodrugs of NSAIDs such as ibuprofen, reducing the adverse effects of their chronic administration. Their production by mild esterification with lipases is a possibility, while the development of continuous or flow processes based on multiphase systems in the pharma industry is key for process intensification and product quality. For the first time, we show that the appropriate selection of cosolvents such as glycerol, toluene, and water and of process conditions leads to high stability and activity of the commercial preparation Novozym[®]435, an immobilised biocatalyst based on lipase B from *Candida antarctica*. View this paper

- Issues are regarded as officially published after their release is announced to the table of contents alert mailing list.
- You may sign up for e-mail alerts to receive table of contents of newly released issues.
- PDF is the official format for papers published in both, html and pdf forms. To view the papers in pdf format, click on the "PDF Full-text" link, and use the free Adobe Reader [to](#) open them.

View PDF

- Conferences
- Editorial Office

Journal Browser

volume

issue

Go

- > Forthcoming issue
- > Current issue

- | | |
|----------------|---------------|
| Vol. 13 (2023) | Vol. 6 (2016) |
| Vol. 12 (2022) | Vol. 5 (2015) |
| Vol. 11 (2021) | Vol. 4 (2014) |
| Vol. 10 (2020) | Vol. 3 (2013) |
| Vol. 9 (2019) | Vol. 2 (2012) |
| Vol. 8 (2018) | Vol. 1 (2011) |
| Vol. 7 (2017) | |

Show export options

Open Access Article

Preparation of CuS/PbS/ZnO Heterojunction Photocatalyst for Application in Hydrogen Production

by Ming-Huan Chiu, Cheng-Ching Kuo, Chao-Wei Huang and Wein-Duo Yang
Catalysts 2022, 12(12), 1677; <https://doi.org/10.3390/catal12121677> - 19 Dec 2022
Cited by 1 | Viewed by 759

Abstract A hexagonal wurtzite ZnO photocatalyst was prepared via a precipitation method. CuS nanoparticles (NPs) and PbS quantum dots (QDs) were loaded onto ZnO via a hydrothermal method to obtain a CuS/PbS/ZnO heterojunction photocatalyst. The CuS/PbS/ZnO photocatalyst obtained via the abovementioned method has significant [...] Read more.
(This article belongs to the Special Issue Structured Semiconductors in Photocatalysis)

Show Figures

Open Access Article

Integrated Adsorption-Photocatalytic Decontamination of Oxytetracycline from Wastewater Using S-Doped TiO₂/WS₂/Calcium Alginate Beads

by Rajeev Kumar, Mohammad Omaish Ansari, Md Abu Taleb, Mohammad Oves, Mohamed A. Barakat, Mansour A. Alghamdi and Naief H. Al Makishah
Catalysts 2022, 12(12), 1676; <https://doi.org/10.3390/catal12121676> - 19 Dec 2022
Viewed by 707

Abstract Integrated wastewater treatment processes are needed due to the inefficient removal of emerging pharmaceuticals by single methods. Herein, an adsorbent-photocatalyst integrated material was fabricated by coupling calcium alginate with sulfur-doped TiO₂/tungsten disulfide (S-TiO₂/WS₂/alginate beads) for the removal [...] Read more.
(This article belongs to the Special Issue Nanomaterials-Based Catalysts for Degradation of Pollutants)

Show Figures

Open Access Article

Electrochemical Detection of Sulfite by Electroreduction Using a Carbon Paste Electrode Binder with N-octylpyridinium Hexafluorophosphate Ionic Liquid

by Maicol Bustos Villalobos, José Ibarra, Leyla Gidi, Valentina Cavieres, María Jesús Aquirre,



>> View PDF

Back to Top

Open Access Article

Photocatalytic Degradation of 4-tert-butylphenol Using Solar Light Responsive Ag_2CO_3

by Saule Mergenbayeva, Timur Sh. Atabaev, John Vakros, Dionissios Mantzavinos and Stavros G. Pouloupoulos

Catalysts 2022, 12(12), 1523; <https://doi.org/10.3390/catal12121523> - 26 Nov 2022

Cited by 3 | Viewed by 565

Abstract In this work, Ag_2CO_3 was prepared via a solution-based method and was further characterized by XRD, Raman spectroscopy, SEM/EDS analysis, and UV-VIS spectroscopy. SEM results revealed the formation of micro-sized particles with a rectangular shape. The photocatalytic activity of the [...] [Read more.](#)

(This article belongs to the Special Issue Photoactive Materials for the Catalytic Decomposition of Water Pollutants)

► Show Figures

Open Access Article

Facile Fabrication of SiO_2/Zr Assisted with EDTA Complexed-Impregnation and Templated Methods for Crude Palm Oil to Biofuels Conversion via Catalytic Hydrocracking

by Hasanudin Hasanudin, Wan Ryan Asri, Zainal Fanani, Selvi Julpani Adisti, Fitri Hadiah, Roni Maryana, Muhammad Al Muttaqii, Zongyuan Zhu and Nelio Teixeira Machado

Catalysts 2022, 12(12), 1522; <https://doi.org/10.3390/catal12121522> - 25 Nov 2022

Cited by 2 | Viewed by 802

Abstract Zr-containing SiO_2 and their parent catalysts were fabricated with different methods using EDTA chelation and template-assist. The activity of the catalysts was explored in crude palm oil (CPO) hydrocracking, conducted under a continuous system micro-cylindrical reactor. The conversion features and the selectivity [...] [Read more.](#)

(This article belongs to the Section Biomass Catalysis)

► Show Figures

Open Access Article

Cobalt-Doped Iron Phosphate Crystal on Stainless Steel Mesh for Corrosion-Resistant Oxygen Evolution Catalyst

by Jaun An, Hyebin Choi, Keunyoung Lee and Ki-Young Kwon

Catalysts 2022, 12(12), 1521; <https://doi.org/10.3390/catal12121521> - 25 Nov 2022

Viewed by 551

Abstract We report an oxygen evolution reaction (OER) catalyst prepared by the incorporation of cobalt-doped iron phosphate on



» View PDF

Back to Top



Search for Articles:

Title / Keyword

Author / Affiliation / Email

Catalysts

All Article Types

Search

Advanced

Journals / Catalysts / Volume 12 / Issue 12 / 10.3390/catal12121522




Submit to this Journal

Review for this Journal

Edit a Special Issue

Article Menu

Academic Editor



Subscribe SciFeed

Related Info Link

More by Authors Links

IK

Order Article Reprints



Open Access Article

Facile Fabrication of SiO₂/Zr Assisted with EDTA Complexed-Impregnation and Templated Methods for Crude Palm Oil to Biofuels Conversion via Catalytic Hydrocracking

by Hasanudin Hasanudin^{1,2,*}, Wan Ryan Asri^{1,2}, Zainal Fanani^{1,2}, Selvi Julpani Adisti^{1,2}, Fitri Hadiah³, Roni Maryana⁴, Muhammad Al Muttaqii⁴, Zongyuan Zhu⁵ and Nelio Teixeira Machado⁶

- ¹ Department of Chemistry, Faculty of Mathematics and Natural Science, Universitas Sriwijaya, Inderalaya 30662, South Sumatra, Indonesia
- ² Biofuel Research Group, Faculty of Mathematics and Natural Science, Universitas Sriwijaya, Inderalaya 30662, South Sumatra, Indonesia
- ³ Department of Chemical Engineering, Faculty of Engineering, Universitas Sriwijaya, Inderalaya 30662, South Sumatra, Indonesia
- ⁴ Research Center for Chemistry, Indonesian Institute of Sciences, Building 452 Kawasan PUSPIPTEK, Serpong, Tangerang Selatan 15311, Banten, Indonesia
- ⁵ School of Energy and Power, Jiangsu University of Science and Technology, Zhenjiang 212000, China
- ⁶ Faculty of Sanitary and Environmental Engineering, Campus Profissional-UFPA, 17 Universidade Federal do Pará, Rua Corrêa N° 1, Belém 66075-900, Brazil

Recommended Articles

Related Info Link

More by Authors Links

Article Views 806

Citations 2

Table of Contents

- Abstract
- Introduction
- Results and Discussion
- Materials and Methods
- Conclusions
- Author Contributions
- Funding
- Data Availability Statement
- Acknowledgments
- Conflicts of Interest
- References



K

Order Article Reprints



Faculty of Chemistry and Environmental Engineering, Campus I, Universidade Federal do Pará, Rua Corrêa N° 1, Belém 66075-900, Brazil

* Author to whom correspondence should be addressed.

Catalysts **2022**, *12*(12), 1522; <https://doi.org/10.3390/catal12121522>

Received: 19 October 2022 / Revised: 10 November 2022 / Accepted: 21 November 2022 /

Published: 25 November 2022

(This article belongs to the Section Biomass Catalysis)

Download

Browse Figures

Review Reports

Versions Notes

Abstract

Zr-containing SiO₂ and their parent catalysts were fabricated with different methods using EDTA chelation and template-assist. The activity of the catalysts was explored in crude palm oil (CPO) hydrocracking, conducted under a continuous system micro-cylindrical reactor. The conversion features and the selectivity towards biofuel products were also examined. The physicochemical of catalysts, such as structure phase, functional groups, surface morphologies, acidity features, and particle size, were investigated. The study showed that the template method promoted the crystalline porous catalysts, whereas the chelate method initiated the non-porous structure. The catalysts' acidity features of SiO₂ and SiO₂/Zr were affected by the preparation, which revealed that the EDTA chelate-assisted method provided higher acidity features compared with the template method. The CPO hydrocracking study showed that the SiO₂/Zr-CEDTA provided the highest catalytic activity towards the hydrocracking process, with 87.37% of conversion attained with 66.29% wt of liquid product. This catalyst exhibited selectivity towards bio-jet (36.88%), bio-diesel (31.43%), and bio-gasoline (26.80%). The reusability study revealed that the SiO₂/Zr-CEDTA had better stability towards CPO conversion compared with SiO₂/Zr-CEDTA, with a low decrease in catalyst performance at three consecutive runs.

Keywords: EDTA; SiO₂; SiO₂/Zr; crude palm oil; hydrocracking; biofuel



Share



Help



Cite



Discuss in SciProfiles



Endorse



Comment

>> View PDF

Back to Top

Article

Facile Fabrication of SiO₂/Zr Assisted with EDTA Complexed-Impregnation and Templated Methods for Crude Palm Oil to Biofuels Conversion via Catalytic Hydrocracking

Hasanudin Hasanudin ^{1,2,*}, Wan Ryan Asri ^{1,2}, Zainal Fanani ^{1,2}, Selvi Julpani Adisti ^{1,2}, Fitri Hadiah ³, Roni Maryana ⁴, Muhammad Al Muttaqii ⁴, Zongyuan Zhu ⁵ and Nelio Teixeira Machado ⁶

¹ Department of Chemistry, Faculty of Mathematics and Natural Science, Universitas Sriwijaya, Inderalaya 30662, South Sumatra, Indonesia

² Biofuel Research Group, Faculty of Mathematics and Natural Science, Universitas Sriwijaya, Inderalaya 30662, South Sumatra, Indonesia

³ Department of Chemical Engineering, Faculty of Engineering, Universitas Sriwijaya, Inderalaya 30662, South Sumatra, Indonesia

⁴ Research Center for Chemistry, Indonesian Institute of Sciences, Building 452 Kawasan PUSPIPTEK, Serpong, Tangerang Selatan 15311, Banten, Indonesia

⁵ School of Energy and Power, Jiangsu University of Science and Technology, Zhenjiang 212000, China

⁶ Faculty of Sanitary and Environmental Engineering, Campus Profissional-UFFPA, 17 Universidade Federal do Pará, Rua Corrêa N° 1, Belém 66075-900, Brazil

* Correspondence: hasanudin@mipa.unsri.ac.id

Citation: Hasanudin, H.; Asri, W.R.; Fanani, Z.; Adisti, S.J.; Hadiah, F.; Maryana, R.; Al Muttaqii, M.; Zhu, Z.; Machado, N.T. Facile Fabrication of SiO₂/Zr Assisted with EDTA Complexed-Impregnation and Templated Methods for Crude Palm Oil to Biofuels Conversion via Catalytic Hydrocracking. *Catalysts* **2022**, *12*, 1522. <https://doi.org/10.3390/catal12121522>

Academic Editor: S. David Jackson

Received: 19 October 2022

Accepted: 21 November 2022

Published: 25 November 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

Abstract: Zr-containing SiO₂ and their parent catalysts were fabricated with different methods using EDTA chelation and template-assist. The activity of the catalysts was explored in crude palm oil (CPO) hydrocracking, conducted under a continuous system micro-cylindrical reactor. The conversion features and the selectivity towards biofuel products were also examined. The physicochemical of catalysts, such as structure phase, functional groups, surface morphologies, acidity features, and particle size, were investigated. The study showed that the template method promoted the crystalline porous catalysts, whereas the chelate method initiated the non-porous structure. The catalysts' acidity features of SiO₂ and SiO₂/Zr were affected by the preparation, which revealed that the EDTA chelate-assisted method provided higher acidity features compared with the template method. The CPO hydrocracking study showed that the SiO₂/Zr-CEDTA provided the highest catalytic activity towards the hydrocracking process, with 87.37% of conversion attained with 66.29%.wt of liquid product. This catalyst exhibited selectivity towards bio-jet (36.88%), bio-diesel (31.43%), and bio-gasoline (26.80%). The reusability study revealed that the SiO₂/Zr-CEDTA had better stability towards CPO conversion compared with SiO₂/Zr-CEDTA, with a low decrease in catalyst performance at three consecutive runs.

Keywords: EDTA; SiO₂; SiO₂/Zr; crude palm oil; hydrocracking; biofuel

1. Introduction

The availability of sustainable and clean energy is currently a considerable concern [1]. The dominant conventional energy source is gradually utilized over time, resulting in a deracination of the fuel supply [2,3]. Furthermore, the emission of greenhouse gases, such as CO_x, SO_x, NO_x, and other poisonous gases from the exhaustion of conventional fuels, is a critical concern because it is counterproductive to human health and the environment [4]. Amidst this obstacle, the courageous concept of developing alternative energy sources, such as biofuels, bravely emerged [5]. Biofuels are known to be renewable, eco-friendly, and sustainable, and designate their potential for substitution while

reducing reliance on fossil fuels [6,7]. Depending on the number of carbon atoms, these fuels are classified into numerous fractions, such as gasoline, kerosene, and diesel [8].

Methods regarding the production of biofuels have been explored extensively. Among the methods that have been employed, the catalytic cracking and hydrocracking methods seem to be the preferred processes as they produce a wide range of hydrocarbons, with particular boiling points that may be directly applied as fuels [9]. This technology offers several advantages, including a lower operating temperature than the pyrolysis method, a more straightforward operating route, and a high conversion feature, with a high calorific value and oxygen-free output [10–12]. In this operation, the double bonds in triglycerides as raw material are cracked down into smaller compound hydrocarbon molecules in the presence of hydrogen and a coherently suitable catalyst [13].

The feedstock of the catalytic hydrocracking reaction is an essential consideration in the production of biofuels. Numerous triglycerides feedstocks, such as algae oil, nyamplung oil, palm oil, soybean, safflower, jatropha, and soybean, have been progressively utilized in the hydrocracking process [6,14–19]. Specifically, the use of crude palm oil (CPO) as a biofuel feedstock is propitious, considering the massive production previously reported [20]. CPO has an extortionate yield per hectare compared to other vegetable oils [21]. For instance, Indonesia has 14 million hectares of oil palm and delivers 85% of the world's palm oil [22]. CPO has a high hydrocarbon chain content with nitrogen and sulfur-free, respectively [23,24]. Considering its chemical nature, readily abundance, and especially its contribution to the Indonesian economy, CPO as a feedstock for producing biofuels via catalytic hydrocracking is reasonably profitable and sustainable.

The development of sufficient catalysts for the vegetable oils' catalytic hydrocracking into biofuels is an essential thing and one of the critical parameters. Among the available catalysts, SiO₂ is one of the catalysts that has enchanted attention due to its high thermal/hydrothermal stability, which results in adequate selectivity for biofuel products and encourages increased oil yields [25]. SiO₂ has been widely expanded due to its chemical stability, vast surface area, non-toxicity, relatively inexpensive, and eco-friendly [26].

In recent decades, metal-support catalytic systems have been explored due to their resistance to catalyst poisoning and deactivation. Currently, SiO₂ has been used as a supported catalyst in many active species such as Ni-Zr [27], Cu [28,29], Ni [30,31], ZnO [32], Ag₂O, Na₂O and K₂O [33], NiP [34], CrO_x [35], and Ru [36]. In particular, active zirconia-based-catalysts have fascinated researchers, in which exhibiting Lewis acid behavior and high catalytic features have been recognized as relatively inexpensive, low toxicity, green, and efficient catalysts for various major organic transformations [37]. Zirconia has both acidic and metallic features, high surface area, remarkable chemical stability, and exceptional surface chemical activity, which can be exploited for the enhancement of oxygen-containing chemicals such as vegetable oil [38]. Zhao et al. [39] adapts the silica with zirconium sites to produce a material with well-defined features. The study report that the hydrogenation catalytic activity and selectivity features were remarkably enhanced by the Zr modification of the silica support compared to Co/SiO₂. Therefore, there is a reasonable impulsion for SiO₂/Zr to explore their potential as an effective cracking reaction catalyst.

Nowadays, the modulation of the physicochemical properties of the catalyst can be conducted by various approaches. The use of chelating agents [40–45] and templates [46–48] has recently captivated attention because they can modify or tune the catalyst's surface, structural, and textural properties, depending on the purpose of the application. Many complexing agents have been employed to enhance the physicochemical properties of various types of catalysts, including citric acid [40–42], L-arginine [43], EDTA-citric acid [44], glycinate [45], ethylene diamine and acetic acid [40]. The effects of these chelating compounds on the catalysts Ni/SBA-16, Ni/ZrO₂, mesoporous Sm/Ce, Ni/SiO₂, Ni/alumina, and Ni/SBA-15 have all been investigated. Notably, the use of EDTA chelating agent has been reported considerably improved the Co/SiO₂ nano spring catalyst as well as their catalytic activity on Fischer-Tropsch CO hydrogenation and catalyst selectivity. This chelating agent's ability to promote Co₃O₄ dispersion on the support surface has been

investigated [49]. The modification of SiO₂/Zr using several techniques, such as templating and chelating methods, and comparing their respective effects on the catalytic activity of hydrocracking, have not been studied yet. Furthermore, neither exploration nor report has been made for fabricating the SiO₂/Zr using an EDTA species as chelating and templating agents. Within this frame of reference, the use of EDTA has the potential as a SiO₂ template or chelating agent, considering that these species are capable of complex binding to zirconium, and calcination at high temperatures will cause EDTA to be removed, allowing changes in the physicochemical properties of SiO₂/Zr.

This work presents a simple facile route for the synthesis of SiO₂/Zr through the complexed-impregnation method. The effect of EDTA as a chelating agent and template method on the physicochemical features of Zr/SiO₂ will be explored and assessed using multiple characterization techniques such as PSA, SEM-EDS mapping, N₂ physisorption, XRD, FTIR, FTIR-absorbed pyridine, as well as the total and the surface acidity features using the gravimetric method. The catalytic activity of these as-prepared catalysts will be examined through the catalytic hydrocracking of CPO toward biofuels.

2. Results and Discussion

2.1. Characterization of Catalysts

A series of SiO₂, SiO₂/Zr catalysts, and their counterparts were prepared using different methods by employing an EDTA template and chelate agents. Their physicochemical properties were assessed using various characterizations. Figure 1 represented the diffractograms of SiO₂, SiO₂/Zr, and their modification using EDTA as a template and chelate as well. The SiO₂ diffractogram revealed a broad peak at 23°, which was assigned to the amorphous silica (ICDD No. 39-1425) [50]. Another study also observed this typical peak when preparing SiO₂ using the sol-gel method [51]. Notably, the 2θ peaks at 30.11°, 34.76°, 50.30°, and 60.10° which was attributed to the single tetragonal zirconia phase (ICDD No. 80-2155) [52]. Some studies reported that the zirconia also had monoclinic, cubic, and mixed crystal structure phases [53,54], which depend on the catalyst's preparation. The amorphous silica phase was still presented on SiO₂/Zr, which indicated that the amorphous silica structure was preserved [55].

As seen in Figure 1, the EDTA chelate and template-assisted method promoted a significantly different crystal structure towards SiO₂/Zr. These results indicate that the EDTA species employed with different methods, i.e., chelate and template, positively affected the SiO₂/Zr structure. The SiO₂/Zr-CEDTA revealed an amorphous structure with no zirconia phase were discerned, which suggested that the Zr species was finely dispersed towards the silica surface and relatively diminutive to be identified by the XRD [40]. This result was also reported by Nadia et al. [56] when preparing NiMo/silica induced by different species such as NaHCO₃, whereby the Mo species was not distinguishable after being loaded onto silica. Rubab et al. [48] reported that there was no discernible crystal structure in SiO₂/NiO, which might be attributed to the integration of NiO into the SiO₂ matrix, as well as its amorphous nature and slighter crystallite size. This result also suggests that the EDTA chelate-assisted method was changing the tetragonal phase zirconia to the amorphous structure, which was presumably due to the robust bonded interaction between the EDTA and Zr through the complex bond, thus leading to the inefficient Zr crystallization. By contrast, the SiO₂ prepared by the EDTA template-assisted method (SiO₂-TEDTA) enhanced the silica structure to be crystalline, as indicated, and new peaks were formed, which attributed to the mixed phase, such as quartz (ICDD No. 71-5334) and cristobalite (ICDD No. 89-3606). During the calcination process, the EDTA species was removed and presumably generated highly ordered silica, thus leading to crystalline phase structure. Similarly, the SiO₂/Zr prepared by the template-assisted method also appeared a crystalline structure. Moreover, the additional peaks at 26.76° in SiO₂/Zr-TEDTA suggested the presence of a monoclinic zirconia phase [52], whereas the unobservable, other monoclinic phase presumably due to the overlapping peaks between

crystalline silica. The relative shift of the tetragonal zirconia phase occurred, likely due to the effect of EDTA species as a templating agent.

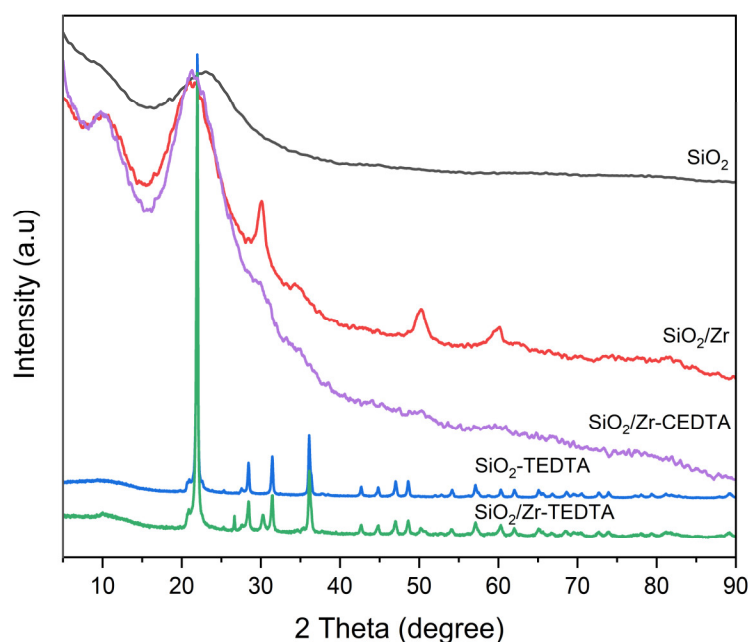


Figure 1. XRD diffraction of SiO_2 , SiO_2/Zr , $\text{SiO}_2/\text{Zr-CEDTA}$, $\text{SiO}_2\text{-TEDTA}$, and $\text{SiO}_2/\text{Zr-TEDTA}$.

The FTIR spectra of SiO_2 , SiO_2/Zr , and their modification are depicted in Figure 2. The absorption band at 1003 and 890 cm^{-1} on the SiO_2 catalyst (Figure 2a) were attributed to the asymmetric and symmetric Si-O stretching vibration [57], whereas the bending mode of Si-O-Si and O-Si-O bonds were observed at 738 and 421 cm^{-1} , respectively [58]. These peaks also appeared in SiO_2 prepared by the EDTA template (Figure 2c) with a relatively shifted towards the lower wavelength, which suggested the local bonding structure change of O and Si atoms promoted by the EDTA template. Meanwhile, the silanol absorption bands were relatively unobserved on the SiO_2/Zr catalyst (Figure 2b), which was presumably due to the intensive band of silanol groups, thus overlapping the zirconia groups bands.

As shown in Figure 2, since catalysts involved the same functional groups, there was no appreciable peak change of SiO_2/Zr prepared by the chelate method compared with the parent SiO_2/Zr , whereas there was a slightly different absorption band at a low wavelength when the template method was employed. This condition suggested that the template and chelate methods affected how the functional groups of silanol as well as zirconia groups bonded in the SiO_2/Zr catalyst. The absorption band at 3650 cm^{-1} and 1556 cm^{-1} corresponded to the Si-OH and -OH groups, respectively [55,59], which were maintained for all catalysts.

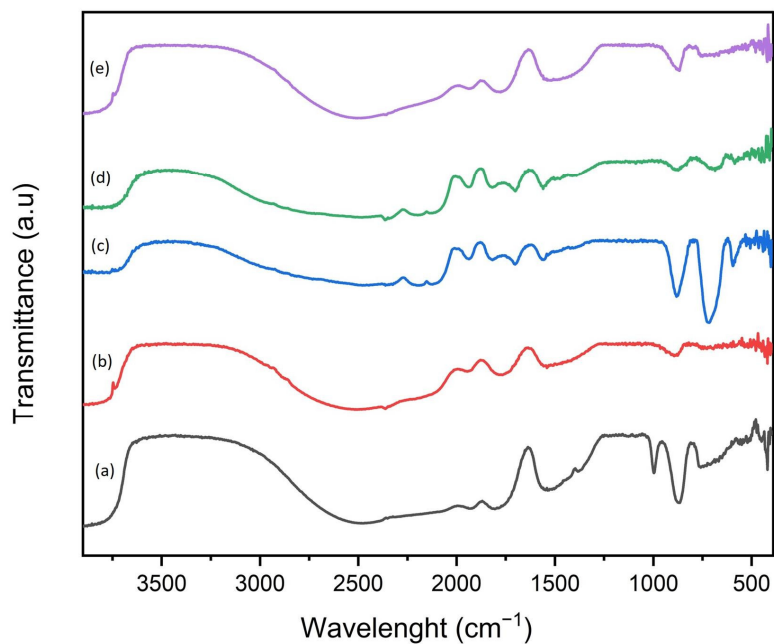


Figure 2. FTIR spectra of (a) SiO₂ (b) SiO₂/Zr (c) SiO₂-TEDTA (d) SiO₂/Zr-TEDTA and (e) SiO₂/Zr-CEDTA.

The SEM micrographs of modified SiO₂, SiO₂/Zr, and their parent catalysts are presented in Figure 3. SiO₂ catalyst (Figure 3a) had a tiny particle distributed uniformly, and after being loaded by the Zr species (Figure 3b), the agglomerated silica was formed which acted as the support for the Zr species.

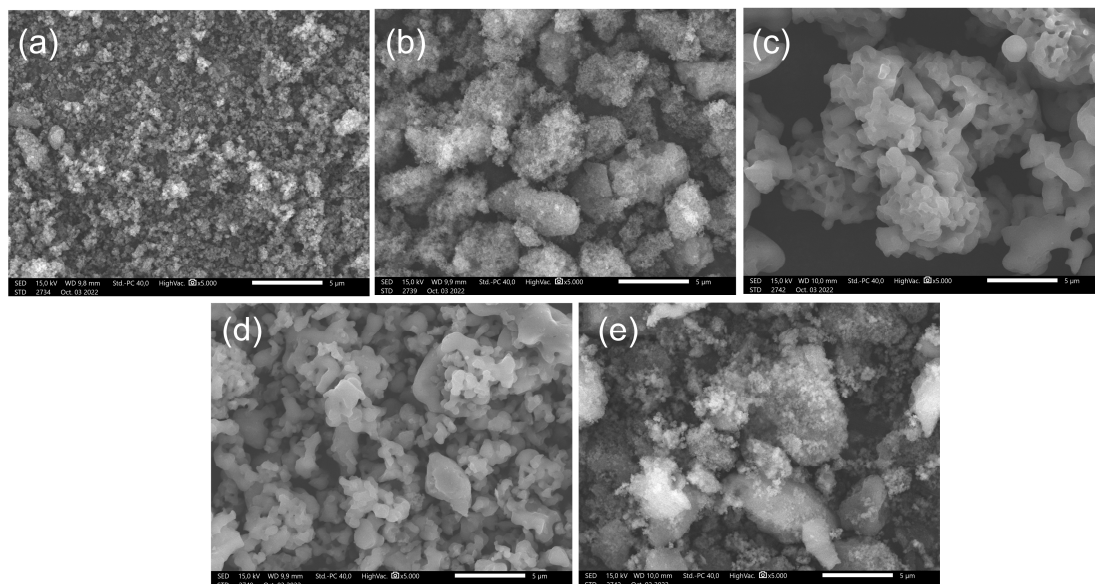


Figure 3. SEM micrographs of (a) SiO₂ (b) SiO₂/Zr (c) SiO₂-TEDTA (d) SiO₂/Zr-TEDTA and (e) SiO₂/Zr-CEDTA.

Remarkably, the SiO₂/Zr prepared by the EDTA template method (Figure 3c) displayed a high porous structure allocated uniformly, the same as the SiO₂/Zr-TEDTA (Figure 3d) but with a less uniformly expanded porous structure. Meanwhile, the SiO₂/Zr prepared by the EDTA chelate method revealed an uneven non-porous structure. These

results suggested that the EDTA template-assisted method promoted the crystalline porous structure, whereas the EDTA chelate-assisted method led to the non-porous and amorphous structure.

The EDX mapping of all catalysts is presented in Figure 4. The expected elements of all catalysts, such as Si, O, and Zr, exist in Figure 4a–e. It can be seen that there was an adequate homogenous zirconium species dispersion towards the surface of the SiO_2 , which could promote the metal-support interaction [60]. However, the distribution of SiO_2 as catalyst support was displayed differently depending on their preparation, which suggested that the EDTA chelate and template method positively affected the catalysts' morphological surface by promoting the enhancement of Zr dispersion.

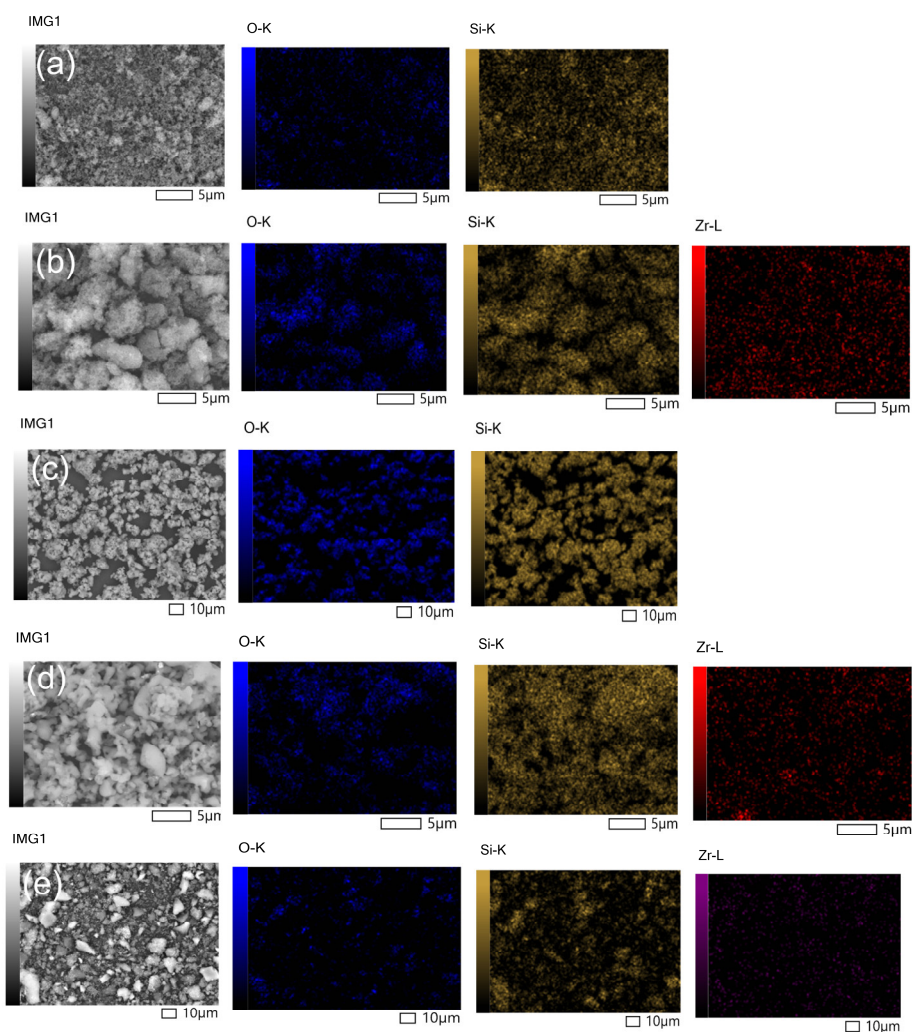



Figure 4. EDX mapping of (a) SiO_2 (b) SiO_2/Zr (c) $\text{SiO}_2\text{-TEDTA}$ (d) $\text{SiO}_2/\text{Zr-TEDTA}$ and (e) $\text{SiO}_2/\text{Zr-CEDTA}$.

The EDX elemental analysis is shown in Table 1. It can be seen that the Zr content was presented correspondingly over SiO_2/Zr , and their counterparts, with no impurities. These results suggested that the SiO_2/Zr catalysts were successfully prepared.

Table 1. EDX results of SiO₂, SiO₂/Zr, and their modification.

Catalyst	Atomic (wt.%)		
	Si	O	Zr
SiO ₂	18.68	81.33	
SiO ₂ /Zr	21.6	78.14	0.26
SiO ₂ -TEDTA	28.43	71.57	
SiO ₂ /Zr-TEDTA	26.18	73.43	0.39
SiO ₂ /Zr-CEDTA	21.6	77.85	0.55

The N₂ physisorption of SiO₂, SiO₂/Zr, and their modification using chelate and template methods are presented in Figure 5. Based on the IUPAC categorization, it was apparent that all the catalysts had a type IV isotherm with a hysteresis loop of type H4, which suggested that the catalysts were mesoporous. Furthermore, the H4 hysteresis loop was related to the micropores with narrow slits feature [56].

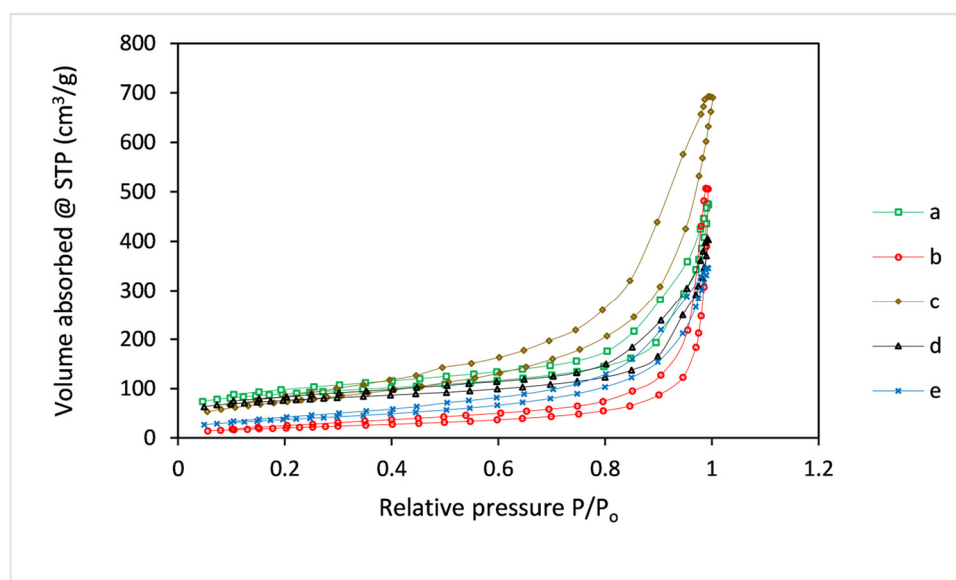
**Figure 5.** N₂ physisorptions of (a) SiO₂ (b) SiO₂/Zr (c) SiO₂-TEDTA (d) SiO₂/Zr-TEDTA (e) SiO₂/Zr-CEDTA.

The textural features of all catalysts are shown in Table 2. The surface area of SiO₂ significantly decreased after being loaded by the Zr species, presumably due to the pore blocking of Zr species [61]. It can be seen that the SiO₂/Zr-KEDTA and SiO₂/Zr-CEDTA had higher surface area compared with the parent SiO₂/Zr catalyst, whereas the SiO₂ prepared by the template method relatively decreased the surface area of the catalyst but increased the total pore volume as well as the average pore radius of the catalysts. This condition indicated that the template and chelate method affected the textural properties of catalysts. The porous structure generated by the EDTA template method enhanced the pore volume of catalysts, whereas the EDTA chelate method reduced the total pore volume of SiO₂/Zr-CEDTA.

Table 2. Textural features of catalysts.

Catalyst	Surface Area (m ² /g)	Total Pore Volume (cm ³ /g)	Average Pore Radius (Å)
SiO ₂	294	0.73	49.76
SiO ₂ /Zr	76.43	0.78	20.48
SiO ₂ -TEDTA	268	0.81	60.44
SiO ₂ /Zr-TEDTA	220.5	0.83	75.37
SiO ₂ /Zr-CEDTA	134	0.53	79.58

The average particle size distribution of all catalysts is presented in Figure 6. It can be seen that the SiO₂ catalyst (Figure 6a) had a relatively uniform particle distribution and subsequently led to a non-uniform particle size distribution after being loaded by the Zr species (Figure 6b). SiO₂-TEDTA catalyst (Figure 6c) had narrow particle size distribution with better uniformity compared with SiO₂. In contrast, surprising results were obtained on the SiO₂/Zr catalyst, both prepared using the template and the chelate methods (Figure 6c,d), as it revealed a non-uniform particle size distribution. However, SiO₂/Zr-CEDTA showed a higher non-uniform particle size distribution than SiO₂/Zr-TEDTA.

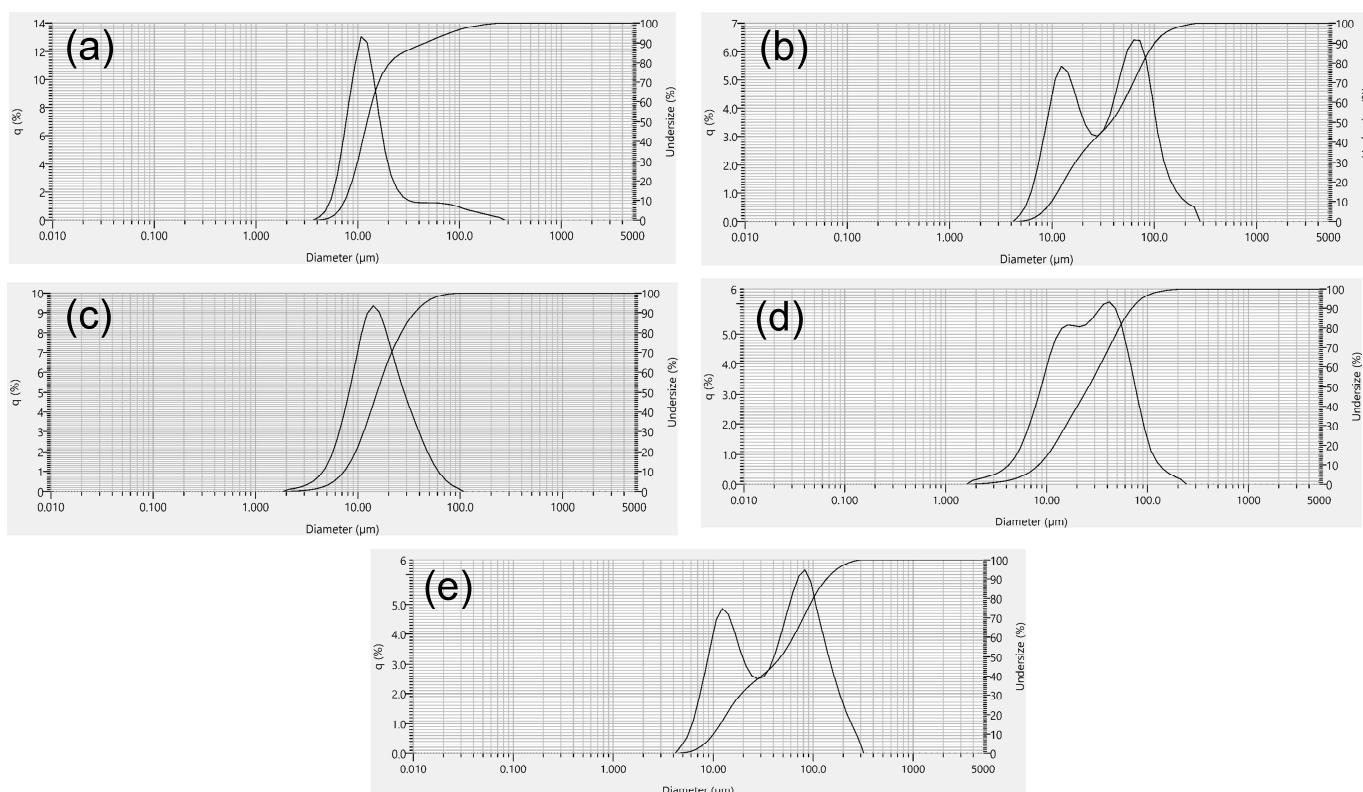**Figure 6.** Particle size distribution of (a) SiO₂ (b) SiO₂/Zr (c) SiO₂-TEDTA (d) SiO₂/Zr-TEDTA and (e) SiO₂/Zr-CEDTA.

The average particle size of all catalysts is presented in Table 3. It can be seen that the average particle size of SiO₂/Zr was higher than the parent SiO₂, presumably due to the effect of Zr impregnation towards the SiO₂ catalyst, which generated aggregate particles. By employing the EDTA template method, the average particle size of SiO₂ tended to decrease, likely due to the porous structure formation, which reduced the average particle size. Regarding SiO₂/Zr catalyst, similarly, employing the template method decreased the average particle size of the catalyst, whereas the chelate method promoted conversely. The strong interaction of metal species with the EDTA through the chelate method likely

provided a dense structure, thus leading to the increase in the catalyst's average particle size.

Table 3. Average particle size (μm) of SiO_2 , SiO_2/Zr , and their modification.

Catalyst	Average Particle Size (μm)
SiO_2	21.66 ± 0.32
SiO_2/Zr	48.39 ± 0.05
$\text{SiO}_2\text{-TEDTA}$	19.08 ± 0.07
$\text{SiO}_2/\text{Zr-TEDTA}$	34.26 ± 0.16
$\text{SiO}_2/\text{Zr-CEDTA}$	61.45 ± 0.07

The total, surface, and pore acidity of all catalysts are presented in Figure 7. It was distinctly seen that the SiO_2 had a low acidity feature when compared to SiO_2/Zr . This low acidity feature was correlated to the Si^{4+} ions, which acted as Lewis acid sites [55], and gradually increased due to the existence of Zr species that contribute to the increase in SiO_2 acidity [62]. The catalyst prepared by the template method seemed to decrease the catalysts' acidity features for both SiO_2 and SiO_2/Zr , whereas SiO_2/Zr prepared by the chelate method promoted an increase in total and surface acidity as well. The low acidity of $\text{SiO}_2\text{-TEDTA}$ and $\text{SiO}_2/\text{Zr-TEDTA}$ was presumably due to the porous structure of the catalyst. The interrelatedness of many active sites on the catalyst surface with one another could happen, thus leading to overlapping between active groups in the catalyst, thereby prompting non-optimal probe absorption [63]. It also can be seen from Figure 7 that the active catalyst site of SiO_2 and SiO_2/Zr was likely generated from the catalysts' pores rather than the surface, whereas the catalyst prepared by the chelate method enhanced the catalyst acidity surface, which consequently decreased the pore acidity. This condition suggested that the template and chelate methods generated different acidity features of the prepared catalyst.

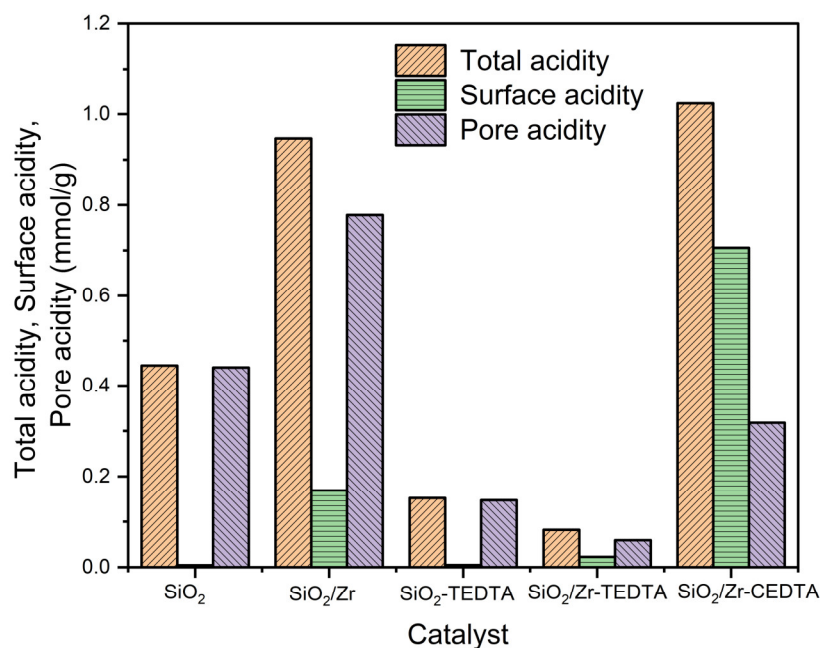


Figure 7. Total, surface, and pore acidity of the catalyst.

The FTIR-pyridine absorbed of SiO_2/Zr and their modification is presented in Figure 8. It can be seen that the intensity of SiO_2/Zr and $\text{SiO}_2/\text{Zr-CEDTA}$ at specific

wavelengths were increased after pyridine was absorbed, whereas SiO₂/Zr-TEDTA showed no appreciable intensity change, which is consistent with the gravimetric analysis, as reported earlier. The broad absorption band at ca. 1630 cm⁻¹ was attributed to the Bronsted acid site initiated by the pyridinium ion [12], whereas the Lewis acid site was observed at ca. 1450 cm⁻¹ absorption band [56]. The strong intensity of the Lewis acid site was noticed on the SiO₂/Zr-CEDTA, suggesting that the chelate method promoted a high catalyst acidity.

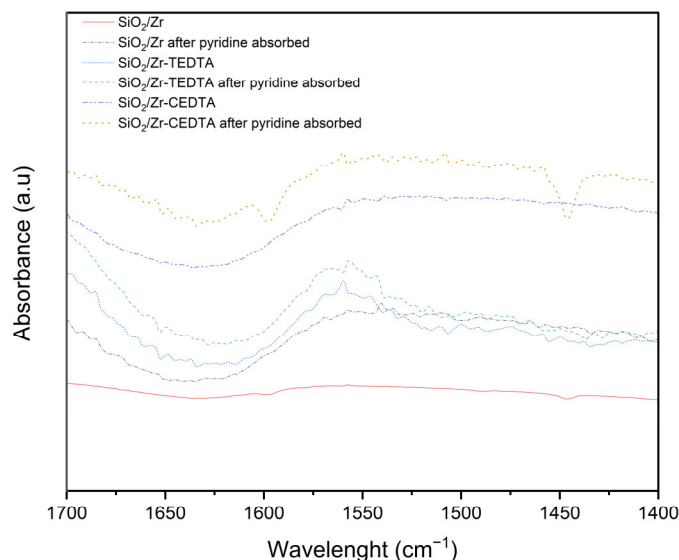


Figure 8. FTIR spectra of SiO₂/Zr, SiO₂/Zr-TEDTA, and SiO₂/Zr-CEDTA before and after pyridine adsorption.

2.2. Hydrocracking Test

The catalytic activity of all catalysts was evaluated for CPO hydrocracking by using a catalyst weight of 0.5 g, a hydrogen flow rate of 30 mL/min, a feed flow rate of 20 mL/h, and a hydrocracking temperature of 500 °C for 1 hr. The conversion and product yield of the hydrocracking process are presented in Table 4.

Table 4. Conversion and product yield from CPO hydrocracking with various catalysts.

Catalyst	Conversion (%)	Yield (%.wt)			
		Liquid	Gas	Coke	Residue
SiO ₂	77.10	53.44	17.971	0.09	28.58
SiO ₂ /Zr	82.75	45.93	40.23	0.21	13.63
SiO ₂ -TEDTA	60.33	62.84	12.99	0.02	24.15
SiO ₂ /Zr-TEDTA	62.17	47.45	38.43	0.12	14
SiO ₂ /Zr-CEDTA	87.73	66.29	23.33	0.34	10.04

It can be seen that the SiO₂/Zr generated a much higher conversion compared to SiO₂. The presence of Lewis acid from Zr species presumably promoted the increase of hydrocracking conversion. Similar findings were also reported by Alisha et al. [64], which showed that the addition of metal species on the support (Mo/SBA-15) promoted the conversion of waste palm cooking oil to hydrocarbon. The low conversion of triglycerides through the hydrocracking process catalyzed by silica was also reported by other studies [55]. Meanwhile, the catalyst prepared by the EDTA template method likely decreases the

conversion of both, SiO₂ and SiO₂/Zr catalysts. On the contrary, SiO₂/Zr prepared by the chelate method promoted high conversion up to 87.73%. These results indicated that the acidity of the catalyst affected the hydrocracking conversion, whereby the chelate method preparation promoted the synergetic effect towards high conversion. Based on Table 3, all catalysts relatively generated high yields due to high-temperature hydrocracking. The SiO₂/Zr had the lowest liquid yield with high gas yield compared with other catalysts. The high gas produced over the SiO₂/Zr catalyst was presumably due to high pore acidity, which promoted the excessive hydrocracking process, thereby increasing the gas yield. The gas product commonly consists of the uncondensable gas such as CO, CO₂, and other C₁–C₅ hydrocarbons. It seemed that the SiO₂/Zr prepared by the template and chelate method higher the liquid yield and reduced the gas yield as well, with pronounced activity observed by the SiO₂/Zr -CEDTA catalyst. Similarly, the SiO₂-TEDTA had a higher liquid yield compared with the parent SiO₂. The porous structure of the catalyst prepared by this method assumably promoted the high liquid yield rather than its acidity. According to these results, the SiO₂/Zr-CEDTA generated the highest liquid compared with another catalyst. SiO₂ catalyst had low coke due to the low acidity of the catalyst, whereas the SiO₂/Zr-CEDTA generated high coke yield compared with others. Wijaya et al. [55] stated that high catalyst acidity could induce coke formation. Based on Table 4, the residue yield of the hydrocracking process for all catalysts ranges from 10.04–28.58%. The residue product consists of the unreacted triglyceride, and the lowest residue yield (10.04%) was achieved by the SiO₂/Zr-CEDTA, which suggested that the SiO₂/Zr prepared by the chelate method was the most effective for CPO hydrocracking compared with other prepared catalysts.

Table 5 shows the selectivity product towards bio-gasoline and bio-aviation with different catalysts. It can be seen that the SiO₂ catalyst provided high selectivity towards the bio-diesel product, with the lowest bio-gasoline fraction. The lowest bio-gasoline fraction was generated, presumably due to low catalyst acidity [55]. Compared with the parent SiO₂, the SiO₂/Zr catalyst increased the bio-gasoline and bio-jet selectivity and decreased the bio-diesel selectivity. Furthermore, the bio-jet selectivity increased after the SiO₂ catalyst was prepared by the template method. This condition suggested that the porous structure of SiO₂-TEDTA provided effective diffusion towards the bio-jet product. During the CPO hydrocracking process, triglycerides and hydrogen gas diffused to the surface or pores of the catalyst and were followed by adsorption to the active site of the catalyst. This step would crack the triglycerides into carbon atoms with lower chains forming the bio-fuel fraction and some gases. After that, the product was desorbed from the surface of the catalyst and subjected to diffusion into the gas phase. Meanwhile, the selectivity of bio-jet, as well as bio-diesel, is relatively the same when employing the SiO₂/Zr-TEDTA catalyst. Moreover, the SiO₂/Zr prepared by the template and chelate method generated no significant change in the bio-gasoline selectivity.

Table 5. Biofuel product selectivity from CPO hydrocracking over various catalysts.

Catalyst	Selectivity (%)		
	Bio-gasoline	Bio-jet	Bio-diesel
SiO ₂	23.13	31.64	45.23
SiO ₂ /Zr	24.58	34.47	40.95
SiO ₂ -TEDTA	27.23	44.67	28.1
SiO ₂ /Zr-TEDTA	26.94	36.88	36.18
SiO ₂ /Zr-CEDTA	26.80	41.77	31.43

The reusability study of catalysts was evaluated to understand the catalyst's stability towards CPO conversion. Table 6 compares the reusability performance of SiO₂/Zr-TEDTA and SiO₂/Zr-CEDTA toward CPO conversion. As can be seen in Table 2, the catalytic performance of SiO₂/Zr-TEDA after the second run decreased up to 8.73%, and

continually decreased up to 21.28% compared with the first run. Meanwhile, only 11.79% of the decrease in catalytic performance was observed when employing the SiO₂/Zr-KEDTA, which suggested that the chelate method provides a relatively stable conversion towards CPO. The decrease in the conversion during the consecutive run was presumably due to coke deposition [7]. It has been known that the catalyst could deactivate through coke formation. This coke blocked the catalyst's active site to initiate the reaction, thereby reducing the catalyst's performance [62].

Table 6. Reusability study of SiO₂/Zr-TEDTA and SiO₂/Zr-CEDTA catalysts.

Catalyst	Conversion (%)		
	1st run	2nd run	3rd run
SiO ₂ /Zr-TEDTA	61.25	56.12	48.21
SiO ₂ /Zr-CEDTA	85.63	82.23	75.53

3. Materials and Methods

3.1. Preparation of SiO₂/Zr Using EDTA Template-Assisted

All chemicals are earned from Merck and utilized without purification. In this typical procedure, tetraethyl orthosilicate (25 mL) was mixed with ethanol (50 mL) and stirred for 15 min at RT. Afterward, sodium ethylenediaminetetraacetic solution (10%, 20 mL) was added, and the ammonium hydroxide solution was gradually dripped (28%, 2 mL) and stirred for 3 hrs. The gel was left at RT for 30 min and subsequently dried in the oven at 85 °C for 24 hrs. The dried powder was later calcined in the muffle furnace at 850 °C for 3 hrs. under an oxygen atmosphere (30 mL/h). The as-prepared catalyst was denoted as SiO₂-TEDTA. The SiO₂-TEDTA was repeatedly washed with deionized water through centrifugation (3500 rpm) for 10 min until the pH reached 7. The solution was later heated to evaporate the water and subsequently dried at 120 °C for 24 hrs. Finally, the dried SiO₂-EDTA powder was mixed with the ZrOCl₂·8H₂O solution (200 mL, 0.04 mol/L) and stirred for 1 hr. at RT. The temperature was gradually increased up to 80 °C for 3 hrs. The paste was dried at 120 °C for 3 hrs. and was later calcined at 850 °C for 3 hrs. under an oxygen atmosphere (30 mL/h) and reduced at 600 °C for 3 hrs. under a hydrogen atmosphere (30 mL/h). The as-prepared catalyst was denoted as SiO₂/Zr-TEDTA. The SiO₂/Zr and SiO₂ without an EDTA template-assisted were also prepared.

3.2. Preparation of SiO₂/Zr Using EDTA Chelated-Assisted

In this procedure, the Zr precursor with the chelating agent is reacted by forming a complex bond. Briefly, ethanol (50 mL) was mixed with TEOS (25 mL) and stirred for 15 min at RT. Next, the solution containing ZrOCl₂·8H₂O (2.578 g) and sodium EDTA (10%, 20 mL) was mixed with the as-prepared previous solution and stirred for 3 hrs. Afterward, the ammonium hydroxide solution (28%, 2 mL) was gradually added. The gel was left at RT for 30 min and subsequently dried in the oven at 85 °C for 24 hrs. The dried powder was later calcined in the muffle furnace at 850 °C for 3 hrs. under an oxygen atmosphere (30 mL/h). The SiO₂/ZrO₂-EDTA was washed until the pH reached 7. The solution was later heated to evaporate the water and subsequently dried at 120 °C for 24 h. The powder was later calcined at 850 °C for 3 hrs. under an oxygen atmosphere (30 mL/h) and reduced at 600 °C for 3 hrs. under a hydrogen atmosphere (30 mL/h). The as-prepared catalyst was denoted as SiO₂/Zr-CEDTA.

3.3. Characterization of Catalyst

The particle sizes of the catalysts (ranging from 0.01 µm to 5000 µm) were analyzed using Horiba Partica LA-960 equipped with a static light scattering method. The diffractograms of catalysts were assessed using a Rigaku SmartLab X-ray diffractometer. SEM-EDX mapping analysis was employed using JSM-IT200. The functional groups of catalysts

were investigated using Shimadzu FT1R-8201PC Infrared Spectrophotometer. The textural features of catalysts were evaluated using N₂ physisorptions by NOVA Quantachrome. The total and surface acidity were determined using the gravimetric method with pyridine and ammonia as a probe [65], respectively, whereas the pore acidity was calculated using the subtraction of total acidity with surface acidity. The pyridine-adsorbed catalysts were also analyzed using FTIR.

3.4. Catalytic Hydrocracking Test

Catalytic hydrocracking was carried out in a continuous system micro-cylindrical reactor with an inner diameter of 2.5 cm, a length of 40 cm, and a capacity of 196.43 cm³ [66]. Prior to the hydrocracking process, the reactor is saturated with hydrogen gas. CPO feed (38% of palmitic acid and 45.16% of oleic acid) is injected using a syringe pump into the reactor with a feed flow rate of 20 mL/h. 0.5 g of catalyst was employed, and the hydrocracking was conducted at 500 °C for 1 hr. with an H₂ flow rate of 30 mL/h. The product was then analyzed using GCMS. The product was then analyzed using GCMS (Thermo Scientific (Waltham, MA, USA)), equipped with TG-5MS columns. The products analysis was calculated according to the Equations (1)–(6):

$$\beta_L (\%.wt) = \frac{\alpha_L}{\alpha_F} \times 100\% \quad (1)$$

$$\beta_R (\%.wt) = \frac{\alpha_R}{\alpha_F} \times 100\% \quad (2)$$

$$\beta_C (\%.wt) = \frac{\alpha_C}{\alpha_F} \times 100\% \quad (3)$$

$$Y_G (\%.wt) = 100\% - (\beta_L + \beta_R + \beta_C)\%.wt \quad (4)$$

$$S_L (\%) = \frac{\% \text{ GCMS } C_X - C_Y \text{ fraction area}}{\% \text{ GCMS total area}} \times 100\% \quad (5)$$

$$C_T (\%.wt) = \frac{\alpha_L - \alpha_R}{\alpha_F} \times 100\% \quad (6)$$

where β_L , β_R , β_C , and β_G are liquid, residue, coke, and gas yield, respectively, whereas S_L and C_T are the biofuel product selectivity and the total conversion, respectively. α_L is the weight of liquid, α_R is the weight of residue, α_C is the coke, and α_F is the weight of the feed. To investigate the stability of the catalyst towards CPO conversion, the spent catalyst was washed with hexane. The catalyst was dried at 105 °C for 1 hr., and subsequently calcinated and followed the reduction, as the same method with the fresh catalyst.

4. Conclusions

The preparation of SiO₂/Zr with different methods, i.e., chelate and template-assisted methods, was successfully conducted. These catalysts were employed for the crude palm oil (CPO) conversion to biofuels via hydrocracking. Different preparation revealed different physicochemical properties of catalysts, leading to different catalytic activities towards the CPO hydrocracking process. Among the catalysts evaluated, SiO₂/Zr-CEDTA showed the highest performance towards the CPO hydrocracking. This catalyst was able to attain a CPO conversion of 87.73% with a liquid yield of 66.29%.wt. The highest selectivity towards bio-jet was achieved up to 41.77%, followed by bio-diesel (31.43%) and bio-gasoline (26.80%). The SiO₂/Zr-CEDTE provided sufficient stability toward CPO conversion compared with SiO₂/Zr-TEDTA, as indicated by only an 11% decrease in the catalyst performance of CPO conversion after three runs.

Author Contributions: Conceptualization, H.H.; methodology, H.H.; validation, H.H.; formal analysis, Z.F., and F.H.; investigation, W.R.A., and S.J.A.; resources, H.H.; data curation, H.H., W.R.A.; writing—original draft preparation, W.R.A.; writing—review and editing, H.H.; Z.Z. and N.T.M.; visualization, R.M., and M.A.M.; supervision, H.H.; funding acquisition, H.H. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by DRPM Ministry of Education, Culture, Research and Technology, Indonesia PDUPT Research grant SPPK No. 245/E5/PG.02.00.PT/2022 (as Research Contract Number: 0214/UN9.3.1/PL/2022).

Data Availability Statement: The data will be available at the request of the corresponding author.

Acknowledgments: This research was funded by DRPM Ministry of Education, Culture, Research and Technology, Indonesia PDUPT Research grant SPPK No. 245/E5/PG.02.00.PT/2022 (as Research Contract Number: 0214/UN9.3.1/PL/2022). The authors thank Badan Riset dan Inovasi Nasional (BRIN) for supplying the catalyst characterization instruments.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Rajesh, K.; Natarajan, M.P.; Devan, P.K.; Ponnuvel, S. Coconut Fatty Acid Distillate as Novel Feedstock for Biodiesel Production and Its Characterization as a Fuel for Diesel Engine. *Renew. Energy* **2021**, *164*, 1424–1435. <https://doi.org/10.1016/j.renene.2020.10.082>.
2. Sari, E.P.; Wijaya, K.; Trisunaryanti, W.; Syoufian, A.; Hasanudin, H.; Saputri, W.D. The Effective Combination of Zirconia Superacid and Zirconia-Impregnated CaO in Biodiesel Manufacturing: Utilization of Used Coconut Cooking Oil (UCCO). *Int. J. Energy Environ. Eng.* **2022**, *13*, 967–978. <https://doi.org/10.1007/s40095-021-00439-4>.
3. Mahdi, H.I.; Bazargan, A.; McKay, G.; Azelee, N.I.W.; Meili, L. Catalytic Deoxygenation of Palm Oil and Its Residue in Green Diesel Production: A Current Technological Review. *Chem. Eng. Res. Des.* **2021**, *174*, 158–187. <https://doi.org/10.1016/j.cherd.2021.07.009>.
4. Hassan, S.N.; Sani, Y.M.; Abdul Aziz, A.R.; Sulaiman, N.M.N.; Daud, W.M.A.W. Biogasoline: An out-of-the-Box Solution to the Food-for-Fuel and Land-Use Competitions. *Energy Convers. Manag.* **2015**, *89*, 349–367. <https://doi.org/10.1016/j.enconman.2014.09.050>.
5. Istadi, I.; Riyanto, T.; Buchori, L.; Anggoro, D.D.; Pakpahan, A.W.S.; Pakpahan, A.J. Biofuels Production from Catalytic Cracking of Palm Oil Using Modified Hy Zeolite Catalysts over a Continuous Fixed Bed Catalytic Reactor. *Int. J. Renew. Energy Dev.* **2021**, *10*, 149–156. <https://doi.org/10.14710/ijred.2021.33281>.
6. Melo-Banda, J.A. Catalytic Hydrocracking of Vegetable Oil for Agrofuels Production Using Ni-Mo, Ni-W, Pt and TFA Catalysts Supported on SBA-15. *Catal. Today* **2011**, *166*, 102–110. <https://doi.org/10.1016/j.cattod.2011.01.026>.
7. Hasanudin, H.; Asri, W.R.; Said, M.; Hidayati, P.T.; Purwaningrum, W.; Novia, N.; Wijaya, K. Hydrocracking Optimization of Palm Oil to Bio-Gasoline and Bio-Aviation Fuels Using Molybdenum Nitride-Bentonite Catalyst. *RSC Adv.* **2022**, *12*, 16431–16443. <https://doi.org/10.1039/D2RA02438A>.
8. Scaldaferrì, C.A.; Pasa, V.M.D. Production of Jet Fuel and Green Diesel Range Biohydrocarbons by Hydroprocessing of Soybean Oil over Niobium Phosphate Catalyst. *Fuel* **2019**, *245*, 458–466. <https://doi.org/10.1016/j.fuel.2019.01.179>.
9. Ameen, M.; Azizan, M.T.; Yusup, S.; Ramli, A.; Yasir, M. Catalytic Hydrodeoxygenation of Triglycerides: An Approach to Clean Diesel Fuel Production. *Renew. Sustain. Energy Rev.* **2017**, *80*, 1072–1088. <https://doi.org/10.1016/j.rser.2017.05.268>.
10. Arun, N.; Sharma, R.V.; Dalai, A.K. Green Diesel Synthesis by Hydrodeoxygenation of Bio-Based Feedstocks: Strategies for Catalyst Design and Development. *Renew. Sustain. Energy Rev.* **2015**, *48*, 240–255. <https://doi.org/10.1016/j.rser.2015.03.074>.
11. Wang, S.; Guo, Z.; Cai, Q.; Guo, L. Catalytic Conversion of Carboxylic Acids in Bio-Oil for Liquid Hydrocarbons Production. *Biomass Bioenergy* **2012**, *45*, 138–143. <https://doi.org/10.1016/j.biombioe.2012.05.023>.
12. Hasanudin, H.; Asri, W.R.; Zulaikha, I.S.; Ayu, C.; Rachmat, A.; Riyanti, F.; Hadiah, F.; Zainul, R.; Maryana, R. Hydrocracking of Crude Palm Oil to a Biofuel Using Zirconium Nitride and Zirconium Phosphide-Modified Bentonite. *RSC Adv.* **2022**, *12*, 21916–21925. <https://doi.org/10.1039/d2ra03941a>.
13. Srihanun, N.; Dujanutat, P.; Muanruksa, P.; Kaewekannetra, P. Biofuels of Green Diesel–Kerosene–Gasoline Production from Palm Oil: Effect of Palladium Cooperated with Second Metal on Hydrocracking Reaction. *Catalysts* **2020**, *10*, 241. <https://doi.org/10.3390/catal10020241>.
14. Liu, Y.; Murata, K.; Inaba, M. Hydrocracking of Algae Oil to Aviation Fuel-Ranged Hydrocarbons over NiMo-Supported Catalysts. *Catal. Today* **2019**, *332*, 115–121. <https://doi.org/10.1016/j.cattod.2018.07.047>.
15. Rasyid, R.; Malik, R.; Kusuma, H.S.; Roesyadi, A.; Mahfud, M. Triglycerides Hydrocracking Reaction of Nyamplung Oil with Non-Sulfided CoMo/ γ -Al₂O₃ Catalysts. *Bull. Chem. React. Eng. Catal.* **2018**, *13*, 196–203. <https://doi.org/10.9767/bcrec.13.2.734.196-203>.
16. Li, T.; Cheng, J.; Huang, R.; Yang, W.; Zhou, J.; Cen, K. Hydrocracking of Palm Oil to Jet Biofuel over Different Zeolites. *Int. J. Hydrog. Energy* **2016**, *41*, 21883–21887. <https://doi.org/10.1016/j.ijhydene.2016.09.013>.

17. Ishihara, A.; Fukui, N.; Nasu, H.; Hashimoto, T. Hydrocracking of Soybean Oil Using Zeolite-Alumina Composite Supported NiMo Catalysts. *Fuel* **2014**, *134*, 611–617. <https://doi.org/10.1016/j.fuel.2014.06.004>.
18. Anand, M.; Farooqui, S.A.; Kumar, R.; Joshi, R.; Kumar, R.; Sibi, M.G.; Singh, H.; Sinha, A.K. Optimizing Renewable Oil Hydrocracking Conditions for Aviation Bio-Kerosene Production. *Fuel Process. Technol.* **2016**, *151*, 50–58. <https://doi.org/10.1016/j.fuproc.2016.05.028>.
19. Zandonai, C.H.; Yassue-Cordeiro, P.H.; Castellã-Pergher, S.B.; Scaliante, M.H.N.O.; Fernandes-Machado, N.R.C. Production of Petroleum-like Synthetic Fuel by Hydrocracking of Crude Soybean Oil over ZSM5 Zeolite-Improvement of Catalyst Lifetime by Ion Exchange. *Fuel* **2016**, *172*, 228–237. <https://doi.org/10.1016/j.fuel.2015.12.059>.
20. Schmidt, J.; De Rosa, M. Certified Palm Oil Reduces Greenhouse Gas Emissions Compared to Non-Certified. *J. Clean. Prod.* **2020**, *277*, 124045. <https://doi.org/10.1016/j.jclepro.2020.124045>.
21. Kuss, V.V.; Kuss, A.V.; Da Rosa, R.G.; Aranda, D.A.G.; Cruz, Y.R. Potential of Biodiesel Production from Palm Oil at Brazilian Amazon. *Renew. Sustain. Energy Rev.* **2015**, *50*, 1013–1020. <https://doi.org/10.1016/j.rser.2015.05.055>.
22. Purnomo, H.; Okarda, B.; Dermawan, A.; Ilham, Q.P.; Pacheco, P.; Nurfatriani, F.; Suhendang, E. Reconciling Oil Palm Economic Development and Environmental Conservation in Indonesia: A Value Chain Dynamic Approach. *For. Policy Econ.* **2020**, *111*, 102089. <https://doi.org/10.1016/j.forpol.2020.102089>.
23. Istadi, I.; Riyanto, T.; Khofiyandita, E.; Buchori, L.; Anggoro, D.D.; Sumantri, I.; Putro, B.H.S.; Firnanda, A.S. Low-Oxygenated Biofuels Production from Palm Oil through Hydrocracking Process Using the Enhanced Spent RFCC Catalysts. *Bioresour. Technol. Rep.* **2021**, *14*, 100677. <https://doi.org/10.1016/j.biteb.2021.100677>.
24. Šimáček, P.; Kubička, D. Hydrocracking of Petroleum Vacuum Distillate Containing Rapeseed Oil: Evaluation of Diesel Fuel. *Fuel* **2010**, *89*, 1508–1513. <https://doi.org/10.1016/j.fuel.2009.09.029>.
25. Li, J.; Fang, X.; Bian, J.; Guo, Y.; Li, C. Microalgae Hydrothermal Liquefaction and Derived Biocrude Upgrading with Modified SBA-15 Catalysts. *Bioresour. Technol.* **2018**, *266*, 541–547. <https://doi.org/10.1016/j.biortech.2018.07.008>.
26. Nasserri, M.A.; Sadeghzadeh, M. Multi-Component Reaction on Free Nano-SiO₂ Catalyst: Excellent Reactivity Combined with Facile Catalyst Recovery and Recyclability. *J. Chem. Sci.* **2013**, *125*, 537–544. <https://doi.org/10.1007/s12039-013-0403-0>.
27. Yao, L.; Shi, J.; Xu, H.; Shen, W.; Hu, C. Low-Temperature CO₂ Reforming of Methane on Zr-Promoted Ni/SiO₂ Catalyst. *Fuel Process. Technol.* **2016**, *144*, 1–7. <https://doi.org/10.1016/j.fuproc.2015.12.009>.
28. Tu, Y.J.; Chen, Y.W. Effects of Alkali Metal Oxide Additives on Cu/SiO₂ Catalyst in the Dehydrogenation of Ethanol. *Ind. Eng. Chem. Res.* **2001**, *40*, 5889–5893. <https://doi.org/10.1021/ie010272q>.
29. Lomate, S.; Sultana, A.; Fujitani, T. Effect of SiO₂ Support Properties on the Performance of Cu-SiO₂ Catalysts for the Hydrogenation of Levulinic Acid to Gamma Valerolactone Using Formic Acid as a Hydrogen Source. *Catal. Sci. Technol.* **2017**, *7*, 3073–3083. <https://doi.org/10.1039/c7cy00902j>.
30. Shu, R.; Xu, Y.; Chen, P.; Ma, L.; Zhang, Q.; Zhou, L.; Wang, C. Mild Hydrogenation of Lignin Depolymerization Products over Ni/SiO₂ Catalyst. *Energy Fuels* **2017**, *31*, 7208–7213. <https://doi.org/10.1021/acs.energyfuels.7b00934>.
31. Wu, C.; Williams, P.T. A Novel Nano-Ni/SiO₂ Catalyst for Hydrogen Production from Steam Reforming of Ethanol. *Environ. Sci. Technol.* **2010**, *44*, 5993–5998. <https://doi.org/10.1021/es100912w>.
32. Giniyatova, S.; Dauletbekova, A.; Baimukhanov, Z.; Vlasukova, L.; Akilbekov, A.; Usseinov, A.; Kozlovskiy, A.; Akylbekova, A.; Seitbayev, A.; Karipbayev, Z. Structure, Electrical Properties and Luminescence of ZnO Nanocrystals Deposited in SiO₂/Si Track Templates. *Radiat. Meas.* **2019**, *125*, 52–56. <https://doi.org/10.1016/j.radmeas.2019.04.001>.
33. Wang, H.; Chen, Z.; Chen, D.; Yu, Q.; Yang, W.; Zhou, J.; Wu, S. Facile, Template-Free Synthesis of Macroporous SiO₂ as Catalyst Support towards Highly Enhanced Catalytic Performance for Soot Combustion. *Chem. Eng. J.* **2019**, *375*, 121958. <https://doi.org/10.1016/j.cej.2019.121958>.
34. Zhu, Q.; Zhang, H.; Zhang, S.; Wang, G.; Zhu, X.; Li, C. Dehydrogenation of Isobutane over a Ni-P/SiO₂ Catalyst: Effect of P Addition. *Ind. Eng. Chem. Res.* **2019**, *58*, 7834–7843. <https://doi.org/10.1021/acs.iecr.9b00032>.
35. Mashkin, M.; Tedeeva, M.; Fedorova, A.; Vasiliev, A.; Egorov, A.; Pribytkov, P.; Kalmykov, K.; Kapustin, G.; Morozov, I.; Kustov, L.; et al. CrOx/SiO₂ Mesoporous Catalysts Prepared Using Beta-Cyclodextrin as a Template and Their Catalytic Properties in Propane Oxidative Dehydrogenation in the Presence of Carbon Dioxide. *Microporous Mesoporous Mater.* **2022**, *338*, 111967. <https://doi.org/10.1016/j.micromeso.2022.111967>.
36. Vasiliadou, E.S.; Lemonidou, A.A. Parameters Affecting the Formation of 1,2-Propanediol from Glycerol over Ru/SiO₂ Catalyst. *Org. Process Res. Dev.* **2011**, *15*, 925–931. <https://doi.org/10.1021/op2000173>.
37. Peng, L.; Zhao, Y.; Yang, T.; Tong, Z.; Tang, Z.; Orita, A.; Qiu, R. Zirconium-Based Catalysts in Organic Synthesis. *Top. Curr. Chem.* **2022**, *380*, 41. <https://doi.org/10.1007/s41061-022-00396-4>.
38. Liu, Y.; Liu, X.; Li, M.; Meng, Y.; Li, J.; Zhang, Z.; Zhang, H. Recyclable Zr/Hf-Containing Acid-Base Bifunctional Catalysts for Hydrogen Transfer Upgrading of Biofurans: A Review. *Front. Chem.* **2021**, *9*, 1090. <https://doi.org/10.3389/fchem.2021.812331>.
39. Zhao, Y.; Sohn, H.; Hu, B.; Niklas, J.; Poluektov, O.G.; Tian, J.; Delferro, M.; Hock, A.S. Zirconium Modification Promotes Catalytic Activity of a Single-Site Cobalt Heterogeneous Catalyst for Propane Dehydrogenation. *ACS Omega* **2018**, *3*, 11117–11127. <https://doi.org/10.1021/acsomega.8b00862>.
40. Zhang, Q.; Long, K.; Wang, J.; Zhang, T.; Song, Z.; Lin, Q. A Novel Promoting Effect of Chelating Ligand on the Dispersion of Ni Species over Ni/SBA-15 Catalyst for Dry Reforming of Methane. *Int. J. Hydrog. Energy* **2017**, *42*, 14103–14114. <https://doi.org/10.1016/j.ijhydene.2017.04.090>.

41. Ren, H.P.; Hao, Q.Q.; Ding, S.Y.; Zhao, Y.Z.; Zhu, M.; Tian, S.P.; Ma, Q.; Song, W.Q.; Miao, Z.; Liu, Z.T. A High-Performance Ni/SiO₂ Prepared by the Complexed-Impregnation Method with Citric Acid for Carbon Dioxide Reforming of Methane. *Ind. Eng. Chem. Res.* **2018**, *57*, 16257–16263. <https://doi.org/10.1021/acs.iecr.8b03897>.
42. Bian, Z.; Xin, Z.; Meng, X.; Tao, M.; Lv, Y.H.; Gu, J. Effect of Citric Acid on the Synthesis of CO Methanation Catalysts with High Activity and Excellent Stability. *Ind. Eng. Chem. Res.* **2017**, *56*, 2383–2392. <https://doi.org/10.1021/acs.iecr.6b04027>.
43. Li, W.; Zhao, Z.; Ding, F.; Guo, X.; Wang, G. Syngas Production via Steam-CO₂ Dual Reforming of Methane over LA-Ni/ZrO₂ Catalyst Prepared by l-Arginine Ligand-Assisted Strategy: Enhanced Activity and Stability. *ACS Sustain. Chem. Eng.* **2015**, *3*, 3461–3476. <https://doi.org/10.1021/acssuschemeng.5b01277>.
44. Ran, R.; Guo, Y.; Zheng, Y.; Wang, K.; Shao, Z. Well-Crystallized Mesoporous Samaria-Doped Ceria from EDTA-Citrate Complexing Process with in Situ Created NiO as Recyclable Template. *J. Alloy. Compd.* **2010**, *491*, 271–277. <https://doi.org/10.1016/j.jallcom.2009.10.129>.
45. Rodríguez-González, V.; Marceau, E.; Beaunier, P.; Che, M.; Train, C. Stabilization of Hexagonal Close-Packed Metallic Nickel for Alumina-Supported Systems Prepared from Ni(II) Glycinate. *J. Solid State Chem.* **2007**, *180*, 22–30. <https://doi.org/10.1016/j.jssc.2006.09.015>.
46. Kaplin, I.Y.; Lokteva, E.S.; Golubina, E.V.; Lunin, V.V. Template Synthesis of Porous Ceria-Based Catalysts for Environmental Application. *Molecules* **2020**, *25*, 4242. <https://doi.org/10.3390/molecules25184242>.
47. Purwaningsih, H.; Ervianto, Y.; Pratiwi, V.M.; Susanti, D.; Purniawan, A. Effect of Cetyl Trimethyl Ammonium Bromide as Template of Mesoporous Silica MCM-41 from Rice Husk by Sol-Gel Method. *IOP Conf. Ser. Mater. Sci. Eng.* **2019**, *515*, 012051. <https://doi.org/10.1088/1757-899X/515/1/012051>.
48. Rubab, R.; Ali, S.; Rehman, A.U.; Khan, S.A.; Khan, A.M. Templated Synthesis of NiO/SiO₂ Nanocomposite for Dye Removal Applications: Adsorption Kinetics and Thermodynamic Properties. *Colloids Surf. A Physicochem. Eng. Asp.* **2021**, *615*, 126253. <https://doi.org/10.1016/j.colsurfa.2021.126253>.
49. Koizumi, N.; Ibi, Y.; Hongo, D.; Hamabe, Y.; Suzuki, S.; Hayasaka, Y.; Shindo, T.; Yamada, M. Mechanistic Aspects of the Role of Chelating Agents in Enhancing Fischer-Tropsch Synthesis Activity of Co/SiO₂ Catalyst: Importance of Specific Interaction of Co with Chelate Complex during Calcination. *J. Catal.* **2012**, *289*, 151–163. <https://doi.org/10.1016/j.jcat.2012.02.003>.
50. Wijaya, K.; Malau, L.L.M.; Utami, M.; Mulijani, S.; Patah, A.; Wibowo, A.C.; Chandrasekaran, M.; Rajabathar, J.R.; Al-Lohedan, H.A. Synthesis, Characterizations and Catalysis of Sulfated Silica and Nickel Modified Silica Catalysts for Diethyl Ether (DEE) Production from Ethanol towards Renewable Energy Applications. *Catalysts* **2021**, *11*, 1511. <https://doi.org/10.3390/catal11121511>.
51. Aneu, A.; Wijaya, K.; Syoufian, A. Silica-Based Solid Acid Catalyst with Different Concentration of H₂SO₄ and Calcination Temperature: Preparation and Characterization. *Silicon* **2021**, *13*, 2265–2270. <https://doi.org/10.1007/s12633-020-00741-6>.
52. Kumar, S.; Bhunia, S.; Ojha, A.K. Effect of Calcination Temperature on Phase Transformation, Structural and Optical Properties of Sol-Gel Derived ZrO₂ Nanostructures. *Phys. E Low-Dimens. Syst. Nanostructures* **2015**, *66*, 74–80. <https://doi.org/10.1016/j.physe.2014.09.007>.
53. Rauta, P.R.; Manivasakan, P.; Rajendran, V.; Sahu, B.B.; Panda, B.K.; Mohapatra, P. Phase Transformation of ZrO₂ Nanoparticles Produced from Zircon. *Phase Transit.* **2012**, *85*, 13–26. <https://doi.org/10.1080/01411594.2011.619698>.
54. Utami, M.; Safitri, R.; Fajar Pradipta, M.; Wijaya, K.; Woong Chang, S.; Ravindran, B.; Ovi, D.; Rajabathar, J.R.; Poudineh, N.; Moonsamy Gengan, R. Enhanced Catalytic Conversion of Palm Oil into Biofuels by Cr-Incorporated Sulphated Zirconia. *Mater. Lett.* **2022**, *309*, 131472. <https://doi.org/10.1016/j.matlet.2021.131472>.
55. Wijaya, K.; Nadia, A.; Dinana, A.; Pratiwi, A.F.; Tikoalu, A.D.; Wibowo, A.C. Catalytic Hydrocracking of Fresh and Waste Frying Oil over Ni- and Mo-Based Catalysts Supported on Sulfated Silica for Biogasoline Production. *Catalysts* **2021**, *11*, 1150. <https://doi.org/10.3390/catal11101150>.
56. Nadia, A.; Wijaya, K.; Falah, I.I.; Sudiono, S.; Budiman, A. Self-Regeneration of Monodisperse Hierarchical Porous NiMo/Silica Catalyst Induced by NaHCO₃ for Biofuel Production. *Waste Biomass Valorization* **2021**, *13*, 2335–2347. <https://doi.org/10.1007/s12649-021-01634-4>.
57. Tran, T.N.; Pham, T.V.A.; Le, M.L.P.; Nguyen, T.P.T.; Tran, V.M. Synthesis of Amorphous Silica and Sulfonic Acid Functionalized Silica Used as Reinforced Phase for Polymer Electrolyte Membrane. *Adv. Nat. Sci. Nanosci. Nanotechnol.* **2013**, *4*, 045007. <https://doi.org/10.1088/2043-6262/4/4/045007>.
58. Gobara, H.M.; Hassan, S.A.; Betiha, M.A. The Interaction Characteristics Controlling Dispersion Mode-Catalytic Functionality Relationship of Silica-Modified Montmorillonite-Anchored Ni Nanoparticles in Petrochemical Processes. *Mater. Chem. Phys.* **2016**, *181*, 476–486. <https://doi.org/10.1016/j.matchemphys.2016.06.084>.
59. Badoga, S.; Mouli, K.C.; Soni, K.K.; Dalai, A.K.; Adjaye, J. Beneficial Influence of EDTA on the Structure and Catalytic Properties of Sulfided NiMo/SBA-15 Catalysts for Hydrotreating of Light Gas Oil. *Appl. Catal. B Environ.* **2012**, *125*, 67–84. <https://doi.org/10.1016/j.apcatb.2012.05.015>.
60. Zaki, T.; Mukhtarova, G.S.; Al-Sabagh, A.M.; Soliman, F.S.; Betiha, M.A.; Mahmoud, T.; Abd El-Raouf, M.; Afandiyeva, N.K.; Alizade, A.; Hasanova, A.B.; et al. Slurry-Phase Catalytic Hydrocracking of Mazut (Heavy Residual Fuel Oil) Using Ni-Bentonite. *Pet. Sci. Technol.* **2018**, *36*, 1559–1567. <https://doi.org/10.1080/10916466.2018.1490762>.
61. Hasanudin, H.; Asri, W.R.; Andini, L.; Riyanti, F.; Mara, A.; Hadiyah, F.; Fanani, Z. Enhanced Isopropyl Alcohol Conversion over Acidic Nickel Phosphate-Supported Zeolite Catalysts. *ACS Omega* **2022**, *7*, 38923–38932. <https://doi.org/10.1021/acsomega.2c04647>.

62. Hasanudin, H.; Asri, W.R.; Putri, Q.U.; Fanani, Z.; Agustina, T.E.; Wijaya, K. Montmorillonite-Zirconium Phosphate Catalysts for Methanol Dehydration. *Iran. J. Catal.* **2022**, *12*, 389–397. <https://doi.org/10.30495/IJC.2022.1960655.1942>.
63. Wijaya, K.; Kurniawan, M.A.; Saputri, W.D.; Trisunaryanti, W.; Mirzan, M.; Hariani, P.L.; Tikoalu, A.D. Synthesis of Nickel Catalyst Supported on ZrO₂/SO₄ pillared Bentonite and Its Application for Conversion of Coconut Oil into Gasoline via Hydrocracking Process. *J. Environ. Chem. Eng.* **2021**, *9*, 105399. <https://doi.org/10.1016/j.jece.2021.105399>.
64. Alisha, G.D.; Trisunaryanti, W.; Syoufian, A. Hydrocracking of Waste Palm Cooking Oil into Hydrocarbon Compounds over Mo Catalyst Impregnated on SBA-15. *Silicon* **2022**, *14*, 2309–2315. <https://doi.org/10.1007/s12633-021-01035-1>.
65. Aziz, I.T.A.; Saputri, W.D.; Trisunaryanti, W.; Sudiono, S.; Syoufian, A.; Budiman, A.; Wijaya, K. Synthesis of Nickel-Loaded Sulfated Zirconia Catalyst and Its Application for Converting Used Palm Cooking Oil to Gasoline via Hydrocracking Process. *Period. Polytech. Chem. Eng.* **2022**, *66*, 101–113. <https://doi.org/10.3311/PPch.18209>.
66. Hasanudin, H.; Rachmat, A.; Said, M.; Wijaya, K. Kinetic Model of Crude Palm Oil Hydrocracking over Ni/Mo ZrO₂ -Pillared Bentonite Catalyst. *Period. Polytech. Chem. Eng.* **2020**, *64*, 238–247. <https://doi.org/10.3311/PPch.14765>.