

## Experimental Investigation on Thermophysical and Stability Properties of TiO<sub>2</sub>/Virgin Coconut Oil Nanofluids

Barlin Oemar<sup>1\*</sup>, Amir Arifin<sup>1</sup>, David Bahrin<sup>2</sup>, Astuti<sup>1</sup>, Dwiki Ramadhan<sup>1</sup>, Muhammad Abil Rifqy<sup>1</sup>, Muhammad Reza Tinambunan<sup>1</sup>

<sup>1</sup>Department of Mechanical Engineering, Faculty of Engineering, Universitas Sriwijaya, Palembang, 30139, Indonesia

<sup>2</sup>Department of Chemical Engineering, Faculty of Engineering, Universitas Sriwijaya, Palembang, 30139, Indonesia

\*Corresponding author: barlin@ft.unsri.ac.id

### Abstract

This paper shows experimental study results on the thermophysical and stability of nanofluids of Titanium oxide (TiO<sub>2</sub>) dispersed in high-purity of Virgin Coconut Oil (VCO). Nanofluid samples that functioned as a lubricant were prepared by a two-step preparation method at different volume fractions (0.1, 0.3, and 0.5 vol.%) and different temperatures (28, 40, and 100°C). The dynamic viscosity and density were performed using Falling Ball Viscometer and Pycnometer, respectively. The sedimentation photograph method using a digital camera was applied to analyze the stability. A maximum dynamic viscosity enhancement of 62.78% was recorded for TiO<sub>2</sub>/VCO nanofluid with 0.5% nanoparticle volume fraction and at the temperature of 100°C). Whereas, the highest density improvement was recorded for TiO<sub>2</sub>/VCO nanofluid with 0.5% nanoparticle volume fraction. Freshly prepared nanofluids did not show any significant change in stability. However, a trivial phase separation appeared in the samples after 8 days. The results indicated that adding TiO<sub>2</sub> nanoparticles increased the dynamic viscosity and density. It can be concluded that the volume in fraction has the effect to enhance the thermophysical stability of TiO<sub>2</sub>/VCO nanofluids.

### Keywords

Nanofluid, Stability, Thermophysical, Titanium Oxide, Virgin Coconut Oil

Received: -, Accepted: -

<https://doi.org/10.26554/sti.2023.8.2.17-24>

## 1. INTRODUCTION

Nanofluids are part of one the most intensive research area since no optimal combination was accomplished concerning thermophysical and stability properties (Ali and Salam, 2020; Bhogare and Kothawale, 2013; Kong et al., 2017). It has been found that the thermophysical (such as viscosity and density) of nanofluid is mostly dependent on the volume fraction. The viscosity of the nanofluid is higher than the base fluid due to an increase in energy dissipation and aggregation.

Nanofluids show excellent properties, the most important issue in producing lubricant-based nanoparticles is the dispersion and stability of nanoparticles in nanofluids. It has been seen that nanofluids can be considered a potential candidate for lubricants.

A few researchers focused on the synthesis of mineral oil-based lubricants. There have been limited studies concerned with the synthesis of nanofluids-based lubricants (Azizie and Hussin, 2020; Shafi and Charoo, 2018; Kotia et al., 2018; Shahnazar et al., 2016; Zawawi et al., 2018). In preparing the nanofluid-based nano lubricant, the type, mass, and volume fraction of nanoparticles are the main challenge due to these


effects on the thermophysical and stability of nano lubricant.

Stability is the main challenge of nanofluid which is crucial in its application as a lubricant. Some techniques/methods have been adopted to enhance the stability of nanofluid such as surfactant addition, pH value controlling, ultrasonic and magnetic steering, ball milling, electrostatic and electrosteric stabilization. The optimum time for sonication and stirring has not been optimized yet. Moreover, the type of nanoparticle and volume fraction on the thermophysical and stability properties are not determined yet (Harish and Rao, 2020; Huminic and Huminic, 2018; Sidik et al., 2015). Therefore, this research is aimed to investigate the thermophysical properties (dynamic viscosity and density) and stability of TiO<sub>2</sub>/VCO nanofluids which functioned as nano lubricants.

## 2. EXPERIMENTAL SECTION

### 2.1 Materials

Metal oxide material is chosen as nanoparticles which are dispersed in the base fluid because of its chemical stability (Darmineh et al., 2017; Deepak and Ram, 2021; Salimon et al., 2010). Titanium oxide (TiO<sub>2</sub>) nanoparticle calcined 99% extra

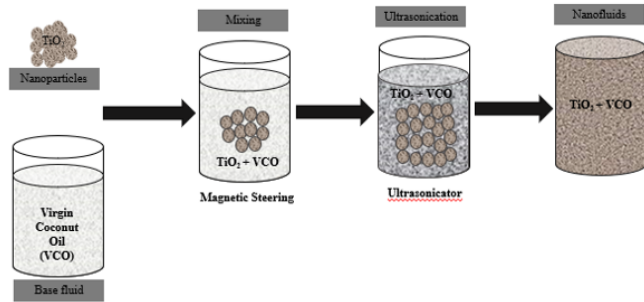

**Figure 1.** Schematic of The Two-Step Method in The Synthesis Process of  $\text{TiO}_2/\text{VCO}$  Nanofluids

pure supplied by Loba Chemie Pvt. Ltd, India. Commercially “BACO” Virgin Coconut Oil (VCO) produced by Kulaku Indonesia ([www.kulakuindonesia.com](http://www.kulakuindonesia.com)) was used as the base fluid for lubricant.

## 2.2 Methods

### 2.2.1 Synthesis of $\text{TiO}_2/\text{VCO}$ Nanofluids

The samples were prepared to utilize the two-step method, which is a widely used method in the preparation of nanofluids for the research (Aberoumand and Jafarimoghaddam, 2017; Ahmadi et al., 2013; Giwa et al., 2021; Katpatal et al., 2017; Su et al., 2016). Three different volume fractions i.e., 0.1, 0.3, and 0.5 vol.% were varied in this study due to the lower cost of nanoparticles. For preparing the sample, the first step involves the weighing of the  $\text{TiO}_2$  nanoparticles with a high precision electronic balance of  $\pm 0.001$  g accuracy and pouring VCO basefluid into beakers. The next step is mixing process by dispersing the nanoparticles in the base fluid by applying a magnetic stirrer for 60 min at 2500 rpm. After stirring, most of the particles remain agglomerated. To ensure that a uniform nanoparticle dispersion and enhance the stability was obtained, the nanofluid samples were sonicated with an ultrasonicator (BAKU BK-1200) at the frequency of 40 kHz for 3 hours. To investigate the effect of the volume fraction of nanoparticles, nanofluid with different volume fractions were prepared as depicted in Table 1. The sketch of the two-step method in this study is shown in Figure 1.

The volume in fractions of  $\text{TiO}_2/\text{VCO}$  nanofluids was calculated based on the mass fraction of the dispersion as:

$$\phi = \frac{m_{np} / \rho_{np}}{m_{np} / \rho_{np} + m_{bf} / \rho_{bf}} \times 100 \quad (1)$$

where  $m_{np}$ ,  $m_{bf}$ ,  $\rho_{np}$ ,  $\rho_{bf}$  are the mass and density of nanoparticle and base fluid, respectively. While  $\phi$  is volume concentration in fractions.

### 2.2.2 Characterization of $\text{TiO}_2/\text{VCO}$ Nanofluids

The HAAKE Falling Ball Viscometer D-1080 manufactured by Thermo Fisher Scientific has been employed to measure the

dynamic viscosity of the  $\text{TiO}_2/\text{VCO}$  nanofluids. This viscometer is equipped with an integrated temperature control system to control the temperature of the samples. The viscosity values of nanofluids were measured over different volume fractions (0.1, 0.3, and 0.5 vol%) at temperature ranges of 28, 40, and 100 °C.

The dynamic viscosity was calculated based on the equation:

$$\mu = K(\rho - \rho')t \quad (2)$$

where  $\mu$ ,  $t$ , and  $K$  are dynamic viscosity (mPa.s), time (s), and constant of falling ball (mPa.s.cm<sup>3</sup>/g.s), while  $\rho$  and  $\rho'$  are the density of the falling ball (g/cm<sup>3</sup>) and nanofluid (g/cm<sup>3</sup>).

$$\rho = \frac{m}{v} \quad (3)$$

where,  $m$  and  $v$  are the mass (g) and volume (cm<sup>3</sup>) of the pycnometer tube, while  $\rho$  is density (g/cm<sup>3</sup>).

Nanofluid stability was investigated by using the photographic method or visual sedimentation method using a Canon digital camera of 24.4 Mega Pixel, EOS M3 Series, 5x Optical Zoom Cyber-shot. This method has been employed to observe the forming of sediment in nanofluids as the effect of volume infraction. The nanofluids were kept in a static condition and their photographs are captured one to 7 days after preparation. Based on the Stokes law, the sedimentation velocity of nanofluids is calculated as:

$$V = \frac{(2gr^2(\rho - \rho_1))}{9\mu} \quad (4)$$

where  $V$ ,  $g$ ,  $r$  are sedimentation velocity (m/s), gravitation constant (m/s<sup>2</sup>), and radius of the nanoparticle. While  $\mu$ ,  $\rho$ , and  $\rho_1$  are the viscosity of nanofluid (kg/m.s), the density of nanoparticle, and base fluid (g/cm<sup>3</sup>).

## 3. RESULT AND DISCUSSION


### 3.1 Thermophysical Properties of $\text{TiO}_2/\text{VCO}$ Nanofluids

Thermophysical properties of nanofluids included dynamic viscosity and density. Figures 2 and 3 showed the dynamic viscosity and density curves at different volume fractions and temperatures).

As is shown in Figure 2, the trend of viscosity for all the samples decreased with the increase in volume fraction. With increasing volume fraction of  $\text{TiO}_2$ , the viscosity found an ascending trend. When  $\text{TiO}_2$  agglomerate and create particles, which prevent the movement of VCO on each other, hence, the viscosity will increase. From the experimental results, it was found that nanofluid shows a higher value of viscosity compared to the base fluid. The increasing viscosity is predominant at a lower temperature. The highest viscosity was observed at 28°C of temperature i.e 6.1514 to 7.4687 mPa.s. The volume fraction is the most important parameter which affects the viscosity of nanofluids. The viscosity of nanofluids effect due to


**Table 1.** The Prepared Sample for Experimental

Sample No.	Nanoparticle	Base Fluid	Volume in Fraction, $\phi$ , vol.%	Mass of TiO <sub>2</sub> (gr)	Volume VCO (mL)
1	TiO <sub>2</sub>	VCO	0.1 vol.% TiO <sub>2</sub>	1.0575	250
2	TiO <sub>2</sub>	VCO	0.3 vol.% TiO <sub>2</sub>	3.1715	250
3	TiO <sub>2</sub>	VCO	0.5 vol.% TiO <sub>2</sub>	5.2975	250

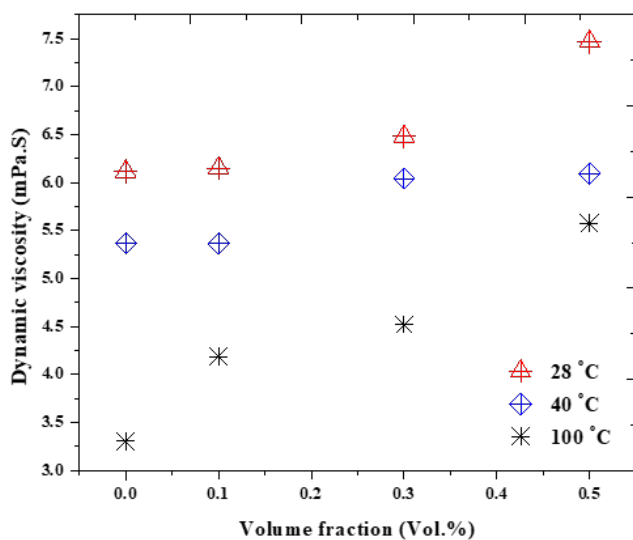**Figure 2.** Viscosity of Nanofluid at A different Volume Fraction

the wt% of nanoparticles. It increases with the increase in particle volume fraction (Moldoveanu et al., 2018; Mukherjee et al., 2021). The more volume fraction, the more difficult to move out of the contact zone in the lubrication area. Moreover, the addition of TiO<sub>2</sub> nanoparticles to VCO increases the frictional shear stress between TiO<sub>2</sub> and VCO molecules due to which the viscosity of nanofluids increases. Therefore, the dispersion of more nanoparticles in base fluids increases the viscosity of nanofluids at the increasing volume fraction.

Figure 3 shows the effect of temperature on the viscosity of TiO<sub>2</sub>/VCO nanofluids and their base fluid. The measurement was taken at temperatures from 28°C to 100°C and volume fractions of 0.1 vol%, 0.3 vol%, and 0.5 vol%. From the graph, it can be observed that the viscosity of the TiO<sub>2</sub>/VCO nanofluids decreases with the temperature increment. The increased interaction between nanoparticles and base fluid molecules is due to the restriction of oil layer movement and Vanderwall's force between the molecules. The reduction of viscosity at high temperatures is due to the weakening of the intermolecular forces between TiO<sub>2</sub> nanoparticles and base fluid (VCO). The results showed a significant reduction in viscosity for all samples at the temperature increased from 28°C to 100°C. The viscosity of nanofluids shows an exponential decrease with temperature rise (Wanatasanappan et al., 2020). The maximum reduction of viscosity is observed for TiO<sub>2</sub>/VCO nanofluid with a volume

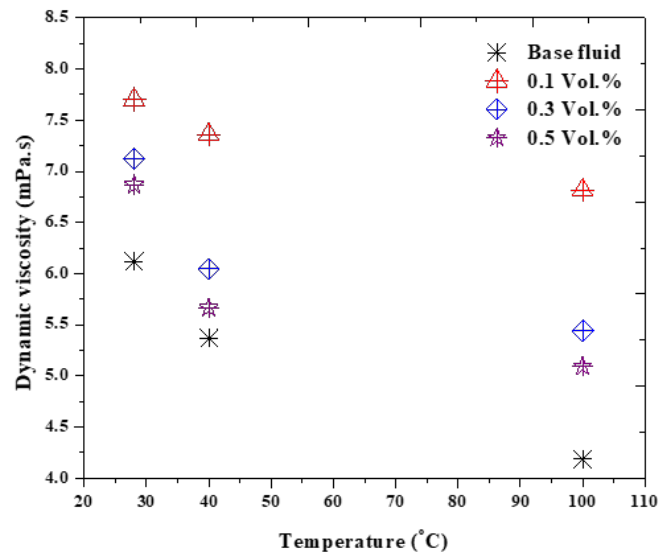**Figure 3.** Viscosity of Nanofluid at Different Temperatures


fraction of 0.1 vol% with a reduction of approximately 62% (7.669 to 6,8145 mPa.S). Therefore, the dispersion of more nanoparticles in base fluids decreases the viscosity of nanofluids at increasing temperatures.

In Figure 4, the density is linearly increased with the increase of volume fraction. The density value for each volume fraction is 0.943, 0.983, and 0.995 g/cm<sup>3</sup>. The density increased by 2.3%, 6.6%, and 7.9% at 0.1, 0.3, and 0.5% of volume fraction, respectively. The density improved due to the addition of nanoparticles in pure virgin coconut oil. The higher the volume fraction, the more nanoparticles are in the pure base fluid (Kedzierski et al., 2017; Kedzierski, 2013). The more nanoparticle in VCO, the higher density of TiO<sub>2</sub>/VCO nanofluids.


### 3.2 Stability of TiO<sub>2</sub>/VCO Nanofluids

The photograph results of each sample were taken at equal intervals of time (just eight days after preparation). Sedimentation level indicates the degree of stability. It is seen from Figure 5 doesn't show the visible sedimentation of TiO<sub>2</sub> nanoparticles. It means that the prepared nanofluids are stable just after preparation. The stability is indicated with no sedimentation occurring. To evaluate the degree of stability, these pictures were compared after eight days.


Figures 5 and 6 describe the photographs just after prepara-

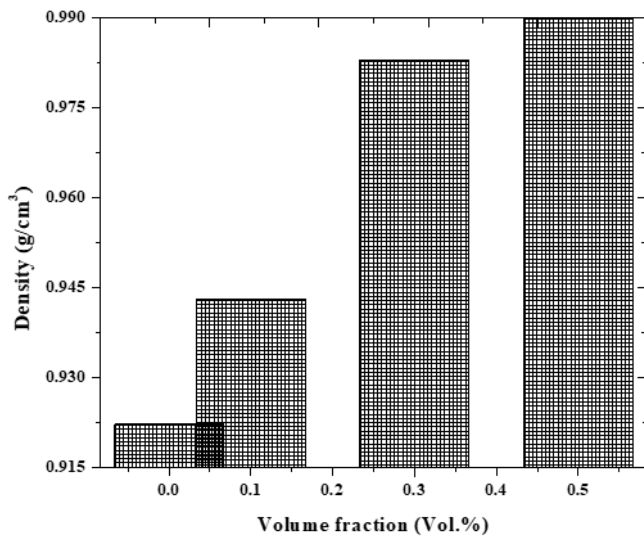


**Figure 4.** Density of Nanofluid at A Different Volume Fraction

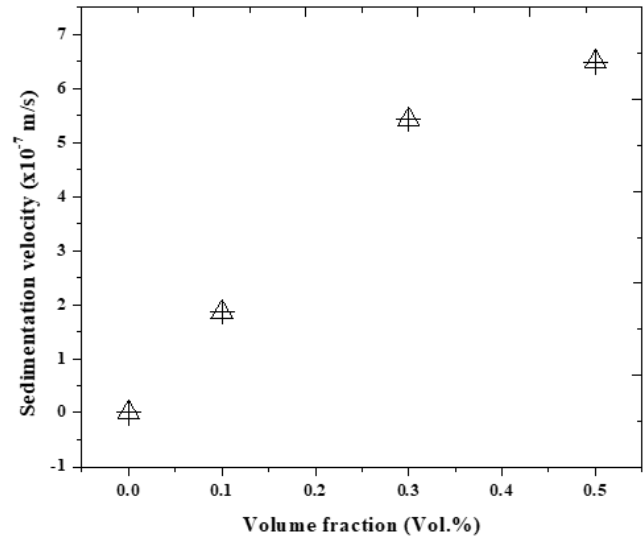

**Figure 7.** Sedimentation Velocity of TiO<sub>2</sub>/Virgin Coconut Oil Nanofluids

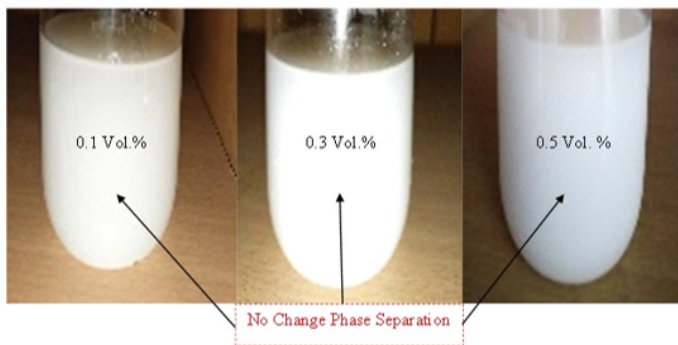

**Figure 5.** Photographs of TiO<sub>2</sub>/Virgin Coconut Oil Nanofluid at The Static Condition: Just After Preparation

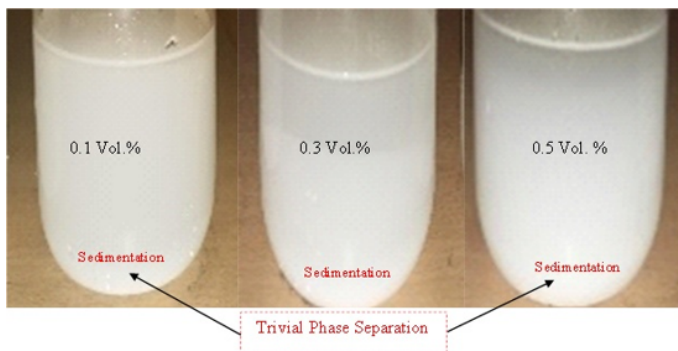

**Figure 6.** Photographs of TiO<sub>2</sub>/Virgin Coconut Oil Nanofluid at The Static Condition: Eight Days After Preparation

ration and eight days after preparation of nanofluids at room temperature of 28°C. The samples were taken in the order of increasing volume fraction. The first time, freshly prepared nanofluids did not show any significant change (Figure 5). However, as shown in Figure 6, trivial phase separation appeared in the samples as the setting time increased to 8 days. It means huge aggregates/sedimentations of nanoparticles tend to settle at the bottom owing to gravity. The sedimentation level enlarged with the increase of volume fraction. It can be confirmed by the sedimentation velocity in Figure 7.

Figure 7 showed the sedimentation velocity of each sample. The range of sedimentation velocity varied from 1.8621 to 6.495x10<sup>-7</sup> m/s. It can be seen that the velocity of sedimentation increased with the increase of volume fraction. The higher the volume fraction (0.5 wt.%), the higher the sedimentation velocity (6.495x10<sup>-7</sup> m/s). The highest and lowest velocity occurred in 0.5 wt.% and 0.1 wt.% of volume fraction, respectively. The increasing sedimentation velocity is caused by the highest nanoparticle in the highest volume fraction (Kumar et al., 2020; Xian et al., 2020).

#### 4. CONCLUSION

A study has been performed on the preparation, viscosity, density, and stability of TiO<sub>2</sub>/VCO nanofluid. Nanofluids with different volume fractions of 0.1, 0.3, and 0.5 vol.% were prepared by a two-step method. The viscosity, density, and stability measurements of the samples were executed at temperature ranges of 28, 40, and 100°C. Based on the study, the following results are obtained. The viscosity of TiO<sub>2</sub>/VCO nanofluids increased with volume fraction and decreased with temperature rise. The density decreased concerning temperature and increased for the volume fraction. The prepared TiO<sub>2</sub>/VCO nanofluids



showed good stability for 8 days. The stability of nanofluids was hampered by the addition of nanoparticles and aging. Sedimentation degree i.e., level and velocity of  $\text{TiO}_2/\text{VCO}$  nanofluids increased with increasing volume fraction.

## 5. ACKNOWLEDGMENT

The publication of this paper was supported by the DIPA of Universitas Sriwijaya 2021 Public Service Agency, SP DIPA-23.17.2.677515/2021, on November 23, 2021. On April 28, 2021, the Rector's Decree 0010/ UN9/ SK. LP2M. PT/2021 was issued.

## REFERENCES

- Aberoumand, S. and A. Jafarimoghaddam (2017). Experimental Study on Synthesis, Stability, Thermal Conductivity and Viscosity of Cu-engine Oil Nanofluid. *Journal of the Taiwan Institute of Chemical Engineers*, **71**; 315–322
- Ahmadi, H., A. Rashidi, A. Nouralishahi, and S. S. Mohtasebi (2013). Preparation and Thermal Properties of Oil-based Nanofluid From Multi-walled Carbon Nanotubes and Engine Oil As Nano-lubricant. *International Communications in Heat and Mass Transfer*, **46**; 142–147
- Ali, A. R. I. and B. Salam (2020). A Review on Nanofluid: Preparation, Stability, Thermophysical Properties, Heat Transfer Characteristics and Application. *SN Applied Sciences*, **2**(10); 1636
- Azizie, N. A. and N. Hussin (2020). Preparation of Vegetable Oil-based Nanofluid And Studies on Its Insulating Property: A Review. *Journal of Physics: Conference Series*, **1432**(1); 012025
- Bhogare, R. A. and B. Kothawale (2013). A Review on Applications And Challenges of Nanofluids As Coolant In Automobile Radiator. *International Journal of Scientific and Research Publications*, **3**(8); 1–11
- Darminesh, S. P., N. A. C. Sidik, G. Najafi, R. Mamat, T. L. Ken, and Y. Asako (2017). Recent Development on Biodegradable Nanolubricant: A Review. *International Communications in Heat and Mass Transfer*, **86**; 159–165
- Deepak, S. N. and C. N. Ram (2021). Physio-chemical Study of Traditional Lubricant SAE 20 W40 and Virgin Coconut Oil Using  $\text{TiO}_2$  Nano-additives. *Materials Today: Proceedings*, **42**; 1024–1029
- Giwa, S. O., M. Sharifpur, M. H. Ahmadi, S. Sohel Murshed, and J. P. Meyer (2021). Experimental Investigation on Stability, Viscosity, and Electrical Conductivity of Water-based Hybrid Nanofluid of Mwcnt- $\text{Fe}_2\text{O}_3$ . *Nanomaterials*, **11**(1); 136
- Harish, R. J. V. V. S. N., V. and P. C. N. Rao (2020). Experimental Evaluation of Vegetable Oil Based Copper Oxide Hybrid Nano Fluid As a Lubricant in Turning. *Nanomaterials*, **4**; 5335–5358
- Huminc, G. and A. Huminc (2018). Hybrid Nanofluids for Heat Transfer Applications—a State-of-the-art Review. *International Journal of Heat and Mass Transfer*, **125**; 82–103
- Katpatal, D. C., A. B. Andhare, P. M. Padole, and R. S. Khedkar (2017). Study of Dispersion Stability and Thermophysical Properties of Cuo-jatropha Oil-based Nanolubricants. *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, **39**; 3657–3668
- Kedzierski, M. A. (2013). Viscosity and Density of Aluminum Oxide Nanolubricant. *International Journal of Refrigeration*, **36**(4); 1333–1340
- Kedzierski, M. A., R. Brignoli, K. Quine, and J. Brown (2017). Viscosity, Density, and Thermal Conductivity of Aluminum Oxide and Zinc Oxide Nanolubricants. *International Journal of Refrigeration*, **74**; 3–11
- Kong, L., J. Sun, and Y. Bao (2017). Preparation, Characterization and Tribological Mechanism of Nanofluids. *Rsc Advances*, **7**(21); 12599–12609
- Kotia, A., P. Rajkhowa, G. S. Rao, and S. K. Ghosh (2018). Thermophysical and Tribological Properties of Nanolubricants: A Review. *Heat and Mass Transfer*, **54**; 3493–3508
- Kumar, P. M., K. Palanisamy, and V. Vijayan (2020). Stability Analysis of Heat Transfer Hybrid/water Nanofluids. *Materials Today*, **21**; 708–712
- Moldoveanu, G. M., A. A. Minea, M. Iacob, C. Ibanescu, and M. Danu (2018). Experimental Study on Viscosity Of Stabilized  $\text{Al}_2\text{O}_3$ ,  $\text{TiO}_2$  Nanofluids and Their Hybrid. *Thermochimica Acta*, **659**; 203–212
- Mukherjee, S., S. Jana, P. C. Mishra, P. Chaudhuri, and S. Chakrabarty (2021). Experimental Investigation on Thermo-physical Properties and Subcooled Flow Boiling Performance of  $\text{Al}_2\text{O}_3/\text{water}$  Nanofluids in A Horizontal Tube. *International Journal of Thermal Sciences*, **159**; 106581
- Salimon, J., N. Salih, and E. Yousif (2010). Biolubricants: Raw Materials, Chemical Modifications and Environmental Benefits. *European Journal of Lipid Science and Technology*, **112**(5); 519–530
- Shafi, W. K. and M. Charoo (2018). Nanolubrication Systems: An Overview. *Materials Today: Proceedings*, **5**(9); 20621–20630
- Shahnazar, S., S. Bagheri, and S. B. Abd Hamid (2016). Enhancing Lubricant Properties by Nanoparticle Additives. *International Journal of Hydrogen Energy*, **41**(4); 3153–3170
- Sidik, N. A. C., M. N. A. W. M. Yazid, and R. Mamat (2015). A Review on The Application of Nanofluids In Vehicle Engine Cooling System. *International Communications in Heat and Mass Transfer*, **68**; 85–90
- Su, Y., L. Gong, and D. Chen (2016). Dispersion Stability and Thermophysical Properties of Environmentally Friendly Graphite Oil-based Nanofluids Used in Machining. *Advances in Mechanical Engineering*, **8**(1); 1687814015627978
- Wanatasanappan, V. V., M. Abdullah, and P. Gunnasegaran (2020). Thermophysical Properties of  $\text{Al}_2\text{O}_3$ -CuO Hybrid Nanofluid at Different Nanoparticle Mixture Ratio: An Experimental Approach. *Journal of Molecular Liquids*, **313**; 113458
- Xian, H. W., N. A. C. Sidik, and R. Saidur (2020). Impact of Different Surfactants and Ultrasonication Time on the Sta-

bility and Thermophysical Properties of Hybrid Nanofluids. *International Communications in Heat and Mass Transfer*, **110**; 104389  
Zawawi, N., W. Azmi, A. Redhwan, M. Sharif, and

M. Samykano (2018). Experimental Investigation on Thermo-physical Properties of Metal Oxide Composite Nanolubricants. *International Journal of Refrigeration*, **89**; 11–21