

Photocatalytic Degradation of Malachite Green by Layered Double Hydroxide Based Composites

by Risfidian Mohadi

Submission date: 22-Dec-2022 08:43PM (UTC+0700)

Submission ID: 1985861784

File name: Malachite_Green_by_Layered_Double_Hydroxide_Based_Composites.pdf (1.11M)

Word count: 5875

Character count: 29345



Research Article

Photocatalytic Degradation of Malachite Green by Layered Double Hydroxide Based Composites

Nova Yuliasari¹, Alfian Wijaya², Risfidian Mohadi^{2,3}, E. Elfita¹, Aldes Lesbani^{2,4,*}

¹Department of Chemistry, Faculty of Mathematics and Natural Sciences, Universitas Sriwijaya, Jl. Palembang Prabumulih Km.32 Ogan Ilir 30662, Indonesia.

²Research Center of Inorganic Materials and Coordination Complexes, Faculty of Mathematics and Natural Sciences, Universitas Sriwijaya, Jl. Palembang Prabumulih Km.32 Ogan Ilir 30662, Indonesia.

³Magister Programme Graduate School of Mathematics and Natural Sciences, Universitas Sriwijaya, Jl. Padang Selasa No. 524 Ilir Barat 1, Palembang 30139, Indonesia.

⁴Doctoral Program, Faculty of Mathematics and Natural Sciences, Universitas Sriwijaya, Jl. Padang Selasa No. 524 Ilir Barat 1, Palembang 30139, Indonesia.

Received: 22nd January 2022; Revised: 22nd February 2022; Accepted: 22nd February 2022
Available online: 2nd March 2022; Published regularly: June 2022



Abstract

Studies of LDH materials to be applied as photocatalyst for dye pollutant degradation have been developed. These interesting efforts are inseparable from the investigation of degradation performance and competitive synthetic methods. Composites based on Zn/Al and Mg/Al layered double hydroxides (LDHs) with ZnO and TiO₂ were prepared by coprecipitation-impregnation method following by calcination at 300 °C to forms Zn/Al-ZnO, Mg/Al-ZnO, Zn/Al-TiO₂, and Mg/Al-TiO₂. Composites were characterized by XRD, FTIR, SEM and UV-DRS. Photodegradation of malachite green (MG) was carried out, after optimization of pH, catalyst loading and contact time in batch system under UV irradiation. XRD and spectroscopic data shows composites were successfully formed indicated by formation of both pristine materials. Degradation of malachite green showed that composites as photocatalyst have higher catalytic activity than pristine LDHs. LDH-ZnO composite have better activity, energy band gap and degradation reusability than LDH-TiO₂. The Zn/Al-ZnO and Zn/Al-TiO₂ composites degraded 97.1% and 96.3% MG, whereas the Mg/Al-ZnO and Mg/Al-TiO₂ composites were able to degrade 99.8% and 98.6% MG, respectively.

Copyright © 2022 by Authors, Published by BCREC Group. This is an open access article under the CC BY-SA License (<https://creativecommons.org/licenses/by-sa/4.0/>).

Keywords: Malachite Green; Layered Double Hydroxide; Photocatalytic

How to Cite: N. Yuliasari, A. Wijaya, R. Mohadi, E. Elfita, A. Lesbani (2022). Photocatalytic Degradation of Malachite Green by Layered Double Hydroxide Based Composites. *Bulletin of Chemical Reaction Engineering & Catalysis*, 17(2), 240-249 (doi: 10.9767/bcrec.17.2.13482.240-249)

Permalink/DOI: <https://doi.org/10.9767/bcrec.17.2.13482.240-249>

1. Introduction

The rapid advancement of industry, including industries that require dyestuff, is accompanied by the consequences of waste pollution. The stability of textile dyes compounds makes it difficult to decompose. This type of organic pollutant is carcinogenic and has high toxicity to the

environment. Research efforts in degrading dyes are often carried out using photocatalysts [1–3]. Pollutant photodegradation is the most economical technique compared to sediment coagulation, adsorption, membrane separation and osmosis. Malachite green, a dye that is widely used in textile, leather and pharmaceuticals, was reported in a study to be degraded by a photocatalyst ZnO on Mg/Al-coated double hydroxide calcined to 500 °C (LDH) [4].

* Corresponding Author.
Email: aldeslesbani@pps.unsri.ac.id (A. Lesbani);

Advanced materials that have easy modification for various purposes such as layered double hydroxide (LDH) have been reported to degrade organic pollutants. The general formula for LDH is $[M^{2+}_{1-x}M^{3+}_x(OH)_2]^{x+}[(A^{n-})_{x/n} \cdot yH_2O]^x$, with composition M is metallic element with valence 2+ and 3+ [5]. The LDH is relatively simple and economical to synthesize in both laboratory and industrial scales [6]. Research on LDH as a photocatalyst that degrades organic pollutants have been synthesized with various alternatives. Mg/AlNi³⁺ LDH was synthesized by coprecipitation in the presence of Na hypochlorite as oxidizing media [7], and Pt modified ZnAl LDH was synthesized mechanochemically as a catalyst for degradation [8].

Modification of LDH is often carried out by composites with metal oxides because of the ability of the hexagonal layer to facilitate fast electron transfer [9]. Modifications of LDH-metal oxides, such as LDH-ZnO, result in dispersion of the active components. ZnO was composited with LDH to avoid aggregation [10]. The ZnO is an excellent photocatalyst due to its efficient photosensitivity, harmless nature and chemically stability [11,12]. Catalyst NiFe-LDH@ZnO@NF was hydrothermally synthesized to degrade Rhodamine B. However, the application of LDH-ZnO is the most widely used in the field of electrochemistry and is still very rarely used as a photocatalytic.

The composite between LDH and other metal oxides, namely TiO₂, provides the advantage of simplifying the filtration process and avoiding TiO₂ agglomeration [13]. TiO₂ has excellent photocatalytic activity, non-toxicity and commercial availability [3,14]. LDH material is used as a TiO₂ support material owing to its good dispersion, helps interaction and sedimentation rate within minutes or at the end of the catalysis process [14,15]. TiO₂ has high catalytic activity [16]. However, TiO₂ nanoparticles easily agglomerate, thereby reducing their catalytic activity. Many studies modify it with various support materials including LDH to degrade dyes [13] including: synthesis of NiAlCu LDH dox-TiO₂ using the hydrothermal method [14]; Mg/Al LDH-TiO₂ was prepared by coprecipitation with molar ratio M²⁺/M³⁺ was 2 [5]; MgZn/Al-TiO₂ LDH synthesized by coprecipitation and ultrasonification was reported to degrade at 4 – 9 hours [3]; sol gel preparation of Mg/Al, Mg/Fe, and Zn/Al LDH-TiO₂ [16,17]. Many studies are still developing the advantages of LDH as a degradation photocatalyst.

Previous studies on the synthesis of LDH-ZnO or LDH-TiO₂ photodegradation catalysts using a calcination temperature of 500 °C or 550 °C include studies by Yan *et al.* [4], Elhalil *et al.* [11], Contreras-Ruiz *et al.* [16], Contreras-Ruiz *et al.* [17], and Hadnadjev-Kostic *et al.* [26]. Those studies used relatively high calcination temperatures. This research therefore seeks to contribute to the lower consumption of calcined energy which is important for large-scale applications to be more energy efficient. This study modified Mg/Al LDH and Zn/Al LDH with metal oxides ZnO and TiO₂, respectively, but calcined at a lower temperature of 300 °C to be applied as degradation photocatalysts. The composites graded malachite green (MG) as a model under UV light. The degradation activity was determined from the percent degradation of the dye and the apparent rate constant.

2. Materials and Methods

2.1 Chemicals and Instrumentation

All chemicals were used after received without specific treatment, Al(NO₃)₃·9H₂O (Merck), Mg(NO₃)₂·6H₂O (Merck), Zn(NO₃)₂·6H₂O (Smart-Lab), TiO₂ (Merck), ZnO (LOBA Chemie), NaOH (Merck), Na₂CO₃ (Merck) and HCl (Mallinckrodt LabGuard). Water was supplied from Inorganic Materials and Complexes Research Group using resin ion exchange reverse method.

Analysis and characterization of materials were performed by Rigaku XRD Miniflex-6000 diffractometer by scanning at 1 deg/min. Analysis of IR was conducted using Shimadzu FTIR Prestige-21 using KBr method. Sample was scanned at 400–4000 cm⁻¹. Band gap analysis was carried out using JASCO V-60 UV-Vis Diffuse Reflectance Spectrometer. Degradation of malachite green was analyzed by UV-Vis Biobase BK-UV 1800 PC spectrophotometer at 617 nm.

2.2 Synthesis of Zn/Al LDH and Mg/Al LDH

LDH was synthesized by coprecipitation method according to a slight modification of the method reported by Lesbani *et al.* [18] and Rahmadan *et al.* [19]. The Zn/Al LDH was synthesized by means of 50 mL Zn(NO₃)₂·6H₂O 0.75 M added with 50 mL Al(NO₃)₃·9H₂O 0.25 M in a shaker for 2 hours. The mixture was added with NaOH and Na₂CO₃ with a mole ratio of 2:1 in 120 mL of distilled water, until the mixture had a pH of 10. This mixture was shaken again for 10 hours at a temperature of

80 °C. After the mixture was filtered and washed with distilled water then dried using an oven at a temperature of 110 °C then the LDH was weighed. The synthesis of Mg/Al LDH was carried out with the same procedure as above, but the salt used was $\text{Mg}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$.

2.3 Synthesis of LDH-Metal Oxide Composite

50 mL solution of $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ or $\text{Mg}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ with a concentration of 0.75 M was added with 50 mL $\text{Al}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ 0.25 M in a shaker for 2 hours, to prepared Zn/Al LDH or Mg/Al LDH. The mixture was added with NaOH and Na_2CO_3 with a mole ratio of 2:1. 120 mL of distilled water, until the pH of the mixture was pH 10. This mixture was shaken again for 10 hours at a temperature of 80 °C. ZnO was dispersed in the mixture with a ratio of LDH pristine: ZnO was 1:1 by weight, then shaken for 3 hours. This mixture was then added with 150 mL of 0.37 M NaOH and stirred for 10 hours at a temperature of 70 °C. The mixture was washed with distilled water and filtered. Then the filtrate was calcined at a temperature of 300 °C in a furnace for 7 hours. The LDH- TiO_2 composite was made using the same procedure as above, but the oxide used was TiO_2 .

2.4 Photodegradation Activity

The synthesized composites were used as a photocatalyst for the degradation of 5 mg/L malachite green as a model in 20 mL dye solution. Degradation in batch system with variable pH, catalyst loading, and contact time of

degradation. The mixture of dye solution and photocatalyst was shaken for 20 minutes in the dark, then continued with the degradation process using UV light (4×20 watt with 352 nm). Photodegradation performance was analyzed by the determination of %degradation and kinetics. Determination of the apparent constant rate of degradation (k_{ap}) over time (t) according to the pseudo first order kinetics model equation $\ln(C_0/C) = k_{ap} \cdot t$, where C_0 is the initial malachite green concentration and C is the concentration of malachite green after the degradation has progressed [12]. The desorption was carried out ultrasonically, and determination of catalyst reusability up to 5 cycles of use.

3. Result and Discussion

Layered double hydroxides (LDHs) are more commonly synthesized by coprecipitation. The synthesis paid attention to the arrangement of metal elements composition, anion intercalation and the ratio of carbonate to NaOH as a precipitant. This study uses the mole ratio of $\text{M}^{2+}/\text{M}^{3+}$ was 3 and the mole ratio of $\text{NaOH}/\text{Na}_2\text{CO}_3$ was 2. The LDH pristine contains various ratios of valence metal 2+ (M^{2+}) to valence 3+ (M^{3+}). Li *et al.* [2] investigated that there was only a slight difference in %degradation by Cu doped Zn/Al LDH between the molar ratios of metals 3 and 4, 77% and 78%, respectively. Another study also used a $\text{M}^{2+}/\text{M}^{3+}$ ratio of 3, but the synthesis was carried out by a combination of coprecipitation and hydrothermal methods to prepare Ba doped Zn/Al LDH [11]. The synthesis resulted in a higher percentage of degradation when using carbonate for interlayer anion than using

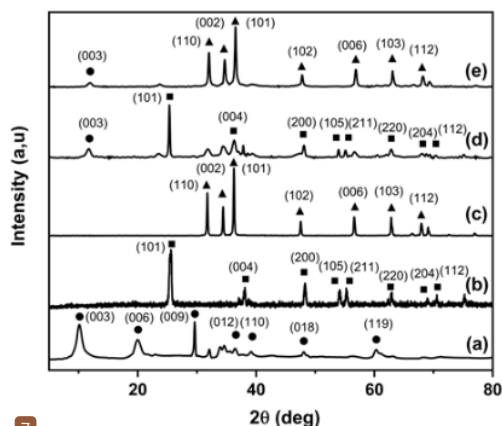


Figure 1. XRD pattern of Zn/Al LDH (a), TiO_2 (b), ZnO (c), Zn/Al- TiO_2 (d), and Zn/Al-ZnO (e).

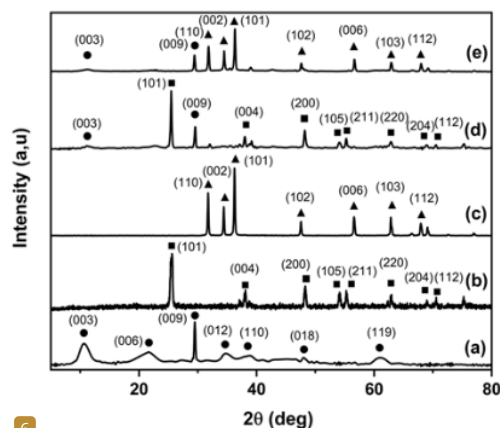


Figure 2. XRD pattern of Mg/Al LDH (a), TiO_2 (b), ZnO (c), Mg/Al- TiO_2 (d), and Mg/Al-ZnO (e).

sulfate, nitrate and chloride [21,22]. This study also used carbonate as counterion. Many variations in the molarity ratio between precipitating sodium hydroxide and carbonate have been reported. Li *et al.* [2], Yan *et al.* [4], and Hu *et al.* [20] used ratio NaOH/Na₂CO₃ was two. The presence of Al cations as 3+ valence metal in LDH increased photocatalytic activity, morphology, particle size and stability [11]. Optimization of the synthesis of Mg/Al LDH-TiO₂ obtained the optimum LDH-TiO₂ weight ratio was 1 [5]. This study also used a ratio of 1 by weight of LDH-metal oxide.

Pristine LDH, metal oxide and LDH-metal oxide composites were characterized using XRD to reveal the characteristic peaks of LDH and oxide, as shown in Figure 1 and Figure 2. The Zn/Al LDH has a unique peak indicating the layer structure at an angle of 2 theta 10.15°. The presence of interlayer anions is indicated by a peak of 60.0° and a metal oxide peak at 20–35° [11,18]. In this study, these peaks were seen in both pristine LDH and composite LDH. The peak at angle 12.1° was the peak (006) planes of Zn/Al LDH in the LDH-ZnO composite [23], while the peak that appears for Zn/Al-ZnO in this study was at 11.9°. Elhalil *et al.* [11] reported that the ZnO peak resulting from

the calcination of Ba doped ZnAl LDH appeared at 31.8° (110), 34.5° (002), 36.3° (101), 47.6° (102), 56.6° (006), 62.9° (103), 68° (112) and 69.1° (201). The ZnO composite peaks in this study appeared at 31.8°, 34.5°, 36.3°, 47.5°, 56.6°, 68°, and 69.1° for Mg/Al-ZnO and 32°, 34.6°, 36.5°, 47.8°, 56.8°, 63°, 68.2°, and 69.3° for Zn/Al-ZnO. Contreras-Ruiz *et al.* [16] investigated the sol-gel synthesized Mg/Al-TiO₂ and Zn/Al-TiO₂ obtained peaks of 25° (101), 38° (004), 48° (200), 55° (105), and 63° (220). This study resulted in peaks of 25.5°, 37.9°, 48.2°, 55.2°, and 62.9° for Mg/Al-TiO₂ and 25.3°, 37.8°, 48°, 55.1°, and 67.2° for Zn/Al-TiO₂.

SEM investigated the morphology of the composites, which showed the distribution of metal oxides in LDHs. The SEM images represent that LDH-ZnO composites have a relatively more homogeneous morphology than LDH-TiO₂ composites. Figure 3 shows images of LDH-metal oxide composites magnified 5000 times, respectively.

The IR spectra of LDH between 3600 – 3200 cm⁻¹ show the stretching vibration of the hydroxyl groups of water molecules located between layers and the hydroxyl is physically absorbed [11]. This study obtained a range of

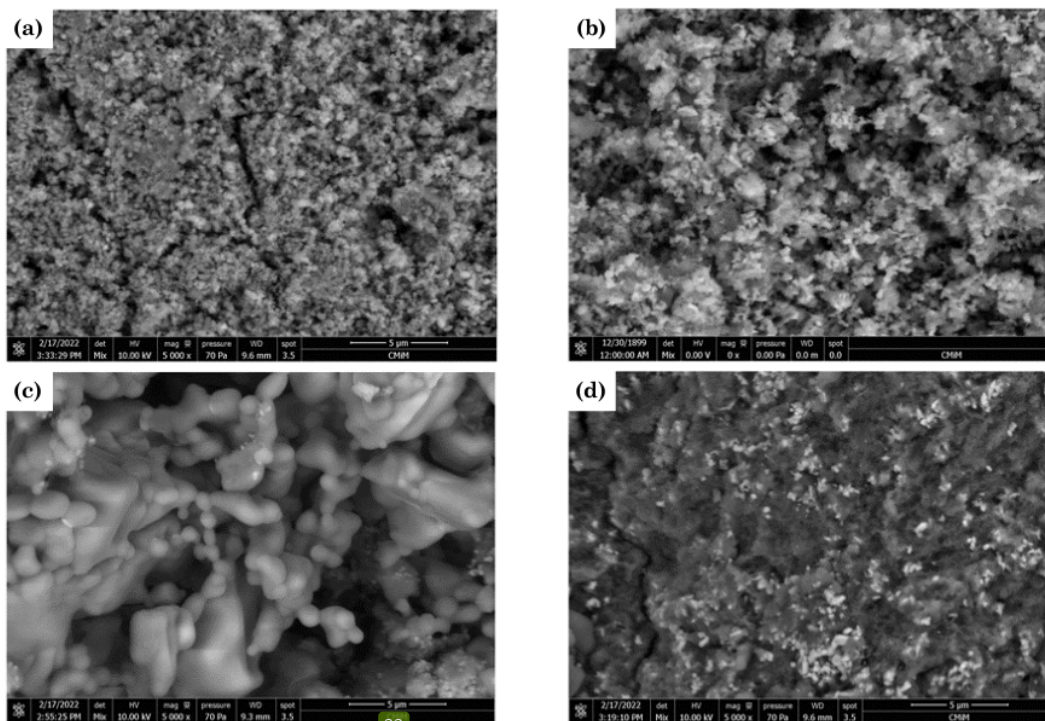


Figure 3. SEM images of composites Zn/Al-TiO₂ (a), Zn/Al-ZnO (b), Mg/Al-TiO₂ (c), and Mg/Al-ZnO (d).

spectra between 3464 to 3441 cm^{-1} in pristine LDHs and composites. Wijaya *et al.* [24] claimed that band 2368 cm^{-1} was the M-O vibration. In this study, band 2368 cm^{-1} was also found in both Zn/Al LDH and Mg/Al-ZnO. Hosseini *et al.* [6] claimed that the peak of CO_3 vibration was at 1381 cm^{-1} , while Zhao *et al.* [3] stated that the 1384 cm^{-1} band which was close to 1360 cm^{-1} showed stretching vibrations of the CO_3 group. In this study the carbonate band of all pristine LDH and composite LDH appeared at 1381 cm^{-1} . Contreras-Ruiz *et al.* [16] stated that the Ti-O band appears at 613 cm^{-1} and 614 cm^{-1} while the ZnO composite didn't show these bands. The Ti-O-Ti band appears at 551-556 cm^{-1} . In this study, it appeared that the 570 and 547 cm^{-1} bands belong to Mg/Al-TiO₂ and Zn/Al-TiO₂, respectively. Aoudjit *et al.* [15] conveyed that the band indi-

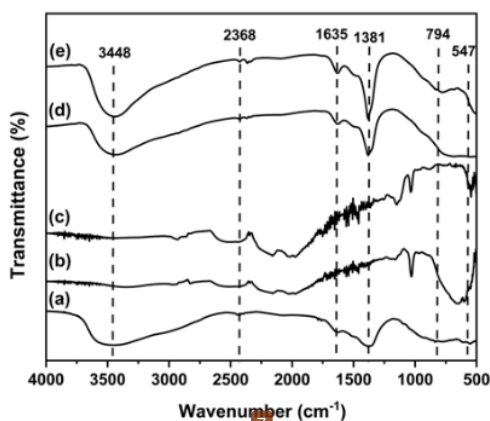


Figure 4. FTIR spectra of Zn/Al LDH (a), TiO₂ (b), ZnO (c), Zn/Al-TiO₂ (d), and Zn/Al-ZnO (e).

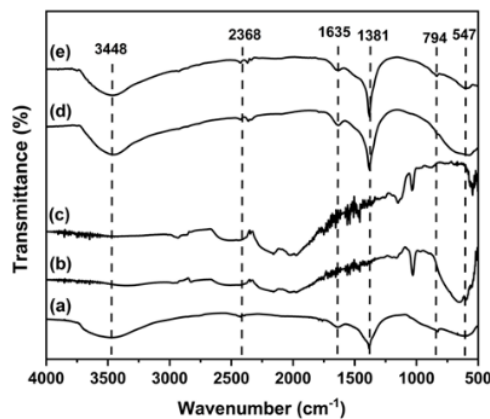


Figure 5. FTIR spectra of Mg/Al LDH (a), TiO₂ (b), ZnO (c), Mg/Al-TiO₂ (d), and Mg/Al-ZnO (e).

29 cating the presence of M-O and O-M-O was in the 400-800 cm^{-1} range. Wijaya *et al.* [24] reported that a band of 462 cm^{-1} was the Zn-O vibration. The IR spectra of the catalysts in this study showed a band between 401 to 779 cm^{-1} . Figure 4 and Figure 5 represent the FTIR spectra of metal oxide, LDH and LDH-metal oxides composites.

The UV-DRS spectrum of the composite is shown in Figure 6(a). On the coordinate axis of the spectrum there is a Kubelka-Munk absorption (KM function) which is the absorbance coefficient per scattering so that it is analogous to absorbance [2]. The composite response in absorbing radiation energy is effective in the UV region identified at peaks around 340 to 380 nm.

36 Figure 6(b) shows the band gap energies of pristine LDH and LDH-composite. According to Wijaya *et al.* [24], Zn/Ti LDH catalyst has a direct transition type so that the curve coordinates are the value $(ah\nu)^2$, where a is the absorptivity coefficient, h is the plank constant and ν is the light frequency. The abscissa value

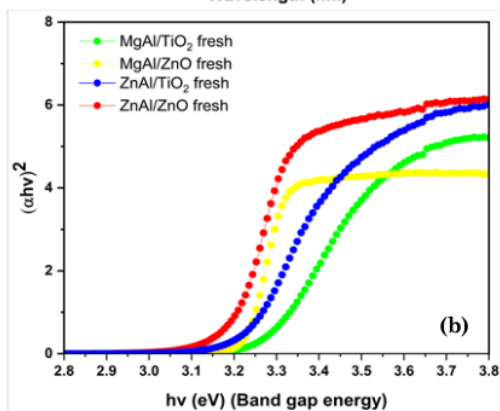
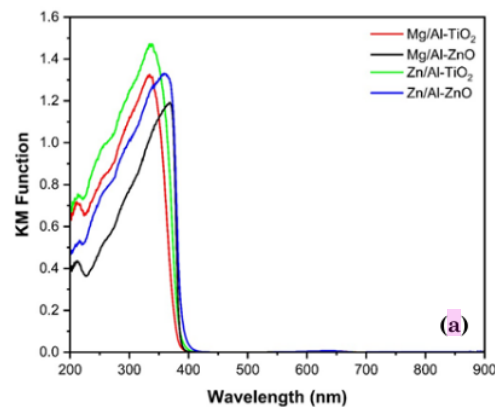


Figure 6. UV-DRS spectra (a) and Energy band gap (b) of LDH-TiO₂ and LDH-ZnO.

is hv or energy band gap, the energy band gap for Zn/Ti LDH was 3.35 eV. Hadnadjev-Kostic *et al.* [26] reported that Zn/Al LDH with metal molar ratio was 0.3 which was impregnated with TiO₂ with water medium had an energy band gap of 3.24 eV, whereas when impregnated in alkaline medium it had 3.21 eV. This study used alkaline media to composite metal oxides. The energy band gap Zn/Al-TiO₂ obtained was also 3.21 eV. The band gap energies of Mg/Al-TiO₂, Mg/Al-ZnO and Zn/Al-ZnO were 3.26, 3.21, and 3.19 eV, respectively. The energy of the Zn/Al-ZnO band gap is lower than that of Zn/Al-TiO₂, allowing the Zn/Al-ZnO photocatalyst to further trigger MG degradation. This is consistent with experimental data of higher value of kinetic rate (k_{ap}) in Section 3.1.4 and higher %degradation in Section 3.1.5. Likewise, the energy band gap of Mg/Al-ZnO is lower than that of Mg/Al-TiO₂. These data correspond to higher k_{ap} values in Section 3.1.4 and higher %degradation in Section 3.1.5 compared to degradation in the presence of Mg/Al-TiO₂.

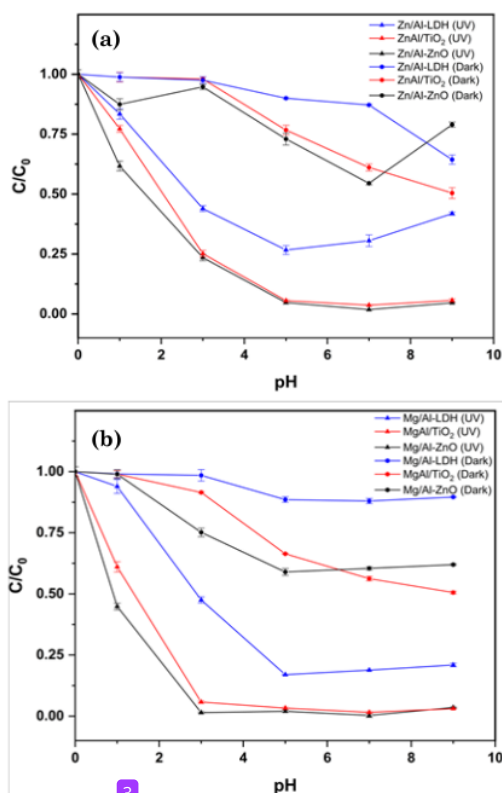


Figure 7. Effect of pH on MG degradation: by Zn/Al-LDH and Zn/Al-metal oxide (a) and by Mg/Al LDH and Mg/Al-metal oxide (b).

The photocatalytic mechanism of the metal-oxide LDH composite was described by Wu *et al.* [12]. Due to the energy of UV irradiation, an effective separation of electron-hole pairs is formed. Photogenerated holes metal oxide could move to the valence band (VB) LDH. Photogenerated electrons in the conduction band (CB) LDH could migrate to the metal oxide CB. Photogenerated holes lead to the formation of OH• by reacting with water or hydroxyl, while photogenerated electrons cause the formation of O₂•⁻ by reacting with oxygen. Both OH• and O₂•⁻ are capable of degrading organic pollutants. The photocatalytic activity of the composite improves material properties because LDH inhibits the recombination of electron-hole pairs of metal oxides.

3.1 Degradation of Malachite Green

3.1.1 Effect of pH on degradation

The photodegradation was carried out by taking into account the optimum pH perfor-

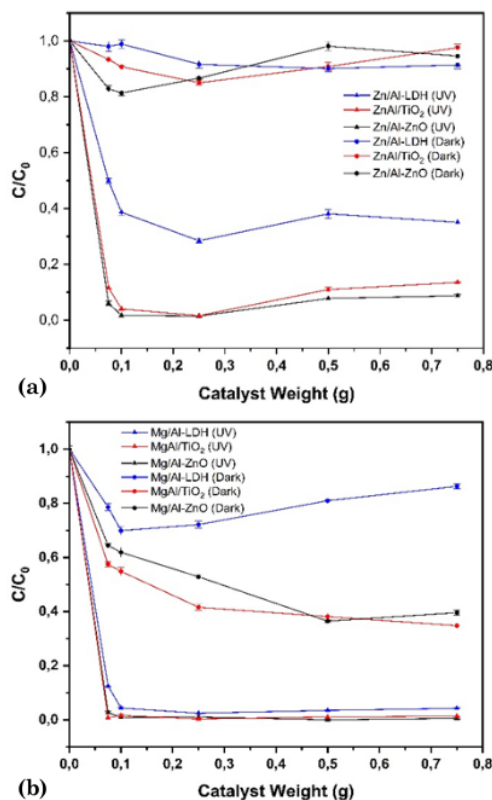


Figure 8. Effect of catalyst loading on MG degradation: by Zn/Al-LDH and Zn/Al-metal oxide (a) and Mg/Al LDH and Mg/Al-metal oxide (b).

mance of LDH pristine and each metal oxide LDH. The experimental results showed that the optimum pH was different between LDH pristine and LDH-metal oxide. Pristine LDH consisting of Mg/Al and Zn/Al LDHs has an optimum pH of 5, while Mg/Al-TiO₂, Mg/Al-ZnO, Zn/Al-TiO₂, Zn/Al-ZnO have an optimum pH of 7. Figure 7 shows the optimum pH in the photodegradation process for 120 minutes using a catalyst loading of 0.1 g. The optimum pH of the composite LDH is above the optimum pH of pristine LDH. Elhalil *et al.* [11] reported that there was a dissolution reaction and photo-decomposition reaction of ZnO oxide to Zn²⁺ in LDH ZnO in acidic media, thereby reducing the degradation performance of the composite.

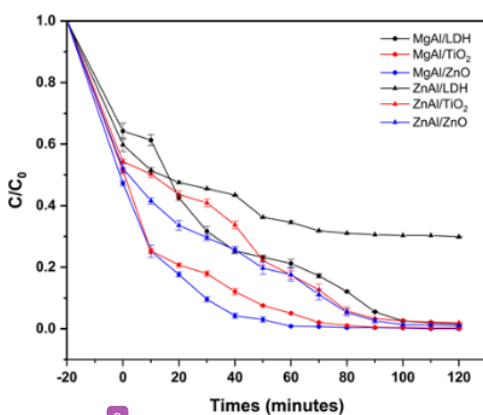


Figure 9. Effect of contact time on MG degradation by pristine LDH and composite LDH.

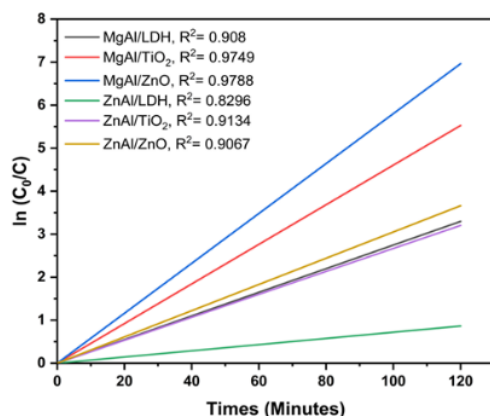


Figure 10. Kinetic curve based on pseudo first order kinetics model equation pristine LDH and LDH composite.

3.1.2 Effect of catalyst loading on degradation

Optimization of catalyst loading is carried out to avoid a shortage of catalyst and excessive catalyst weight. The optimum use of catalysts for both pristine LDH and all composites is 0.25 g. Figure 8 shows the optimum catalyst loading at the optimum pH degradation conditions of each catalyst for 120 minutes of photodegradation. A slight decrease in degradation performance with the use of catalyst weight above the optimum weight can be caused by light refraction and reduced light penetration into the solution [11].

3.1.3 Effect of contact time on photodegradation

The effect of time on the performance of the catalyst in the malachite green degradation process showed a positive effect. The reduction of MG concentration during the first 20 minutes of contact was an adsorption process due to it takes place in dark conditions. UV radiation was turned on for up to 120 minutes to calculate percent degradation and kinetic parameters. Percent degradation by Mg/Al LDH was 96.7%, while that by Mg/Al-ZnO and Mg/Al-TiO₂ was 99.8% and 98.6%, respectively. LDHs modified with metal oxides allows the ability of the hexagonal layer to facilitate fast electron transfer so that it degrades better than pristine LDH [9]. Percent degradation of Zn/Al LDH was only 68.7%, while Zn/Al-ZnO and Zn/Al-TiO₂ composites degraded 97.1% and 96.3%, respectively. Figure 9 shows the reduction in MG concentration during contact time.

Table 1. Value of apparent constant (k_{ap}) of catalysts.

Catalysts	k_{ap} (mg/L.min)	Ref.
Zn/Co-Biochar	0.0260	[27]
45/Fe-Go/GS	0.0046	[28]
Mg/Al-TiO ₂	0.0055	[16]
Mg/Fe-TiO ₂	0.0043	[16]
Zn/Al-TiO ₂	0.0060	[16]
ZnCo/Al LDH	0.0120	[29]
10/ZnGaNO LDH	0.0200	[20]
Zn/Al LDH	0.0072	This study
Mg/Al LDH	0.0280	This study
Zn/Al-ZnO	0.0310	This study
Zn/Al-TiO ₂	0.0270	This study
Mg/Al-ZnO	0.0580	This study
Mg/Al-TiO ₂	0.0461	This study

LDH-ZnO composite had a higher %degradation than LDH-TiO₂. This phenomena was in accordance with the apparent rate constant value which can also be higher than LDH-TiO₂. These results also agree with Yan *et al.* [4] who informed that ZnO has better organic compound degradation activity than TiO₂.

3.1.4 Kinetics of degradation

The degradation kinetics is based on pseudo first order kinetics model calculation as conveyed at experimental section. Figure 10 shows the curve $\ln(C_0/C)$ against time (t), the slope of the curve is the value of the apparent degradation rate constant, k_{ap} [15]. In this study, the k_{ap} value of degradation using composite LDH was better than pristine LDH because the degradation was more effective when the k_{ap} value was greater. Table 1 shows the value of the apparent constant (k_{ap}). In the table, it can be seen that the rate of degradation of the LDH-ZnO composite was better than the rate of LDH-TiO₂. Pseudo first order kinetics model allowed that the reaction rate (r) is comparable to the surface of the catalyst covered with pollutants, when the pollutant solutions are not concentrated. Therefore, because the k_{ap} rate constant is proportional to the reaction rate (r), the higher the k_{ap} value indicates the more efficient the degradation [16]. Table 1 shows the k_{ap} values of organic pollutant photodegradation catalysts produced by other studies, then compared with the k_{ap} values obtained by this study. The comparison shows that all composite k_{ap} values in this study are higher or better than all other research results. Even the pristine LDH k_{ap} value of Mg/Al LDH (0.028 mg/L minutes) was able to outperform the composite LDH from other previous studies. This result was in

agreement with the higher %degradation of LDH-ZnO and information from Yan *et al.* [4] who stated that the degradation activity of ZnO was better than TiO₂.

3.1.5 Reusability of photocatalysts

The use of the catalyst is expected to be efficient so that it can be used repeatedly to degrade organic pollutants, this ability is known from the decrease in the percentage of degradation after several cycles of repeated use. Figure 11 shows a slight decrease in the degradation ability after reuse of the composite as a photocatalyst. After 5 cycles of using the catalyst there was a decrease in % degradation of Mg/Al LDH and Zn/Al LDH to 78.92% and 20.58%, respectively. The decrease in %degradation of LDH composites after 5 cycles of use by Zn/Al-ZnO, Zn/Al-TiO₂, Mg/Al-ZnO and Mg/Al-TiO₂ were 73.1%, 71.88%, 89.72%, 88.24%, respectively. The reusability of pristine LDH and composite LDH corresponded to the %degradation and apparent rate value. From the results of reusability, it can be seen that the LDH-ZnO was better than the LDH-TiO₂.

4. Conclusion

LDH-ZnO and LDH-TiO₂ composites which were synthesized by coprecipitation and followed by calcination at 300 °C have been succeeded in degrading malachite green as a model dye. XRD and FTIR characterization showed the presence of typical peaks or bands of metal oxide LDH. The results of the investigation carried out according to pH, catalyst loading and optimum contact time showed %degradation, degradation rate, and reusability of LDH-ZnO and LDH-TiO₂ composites were better

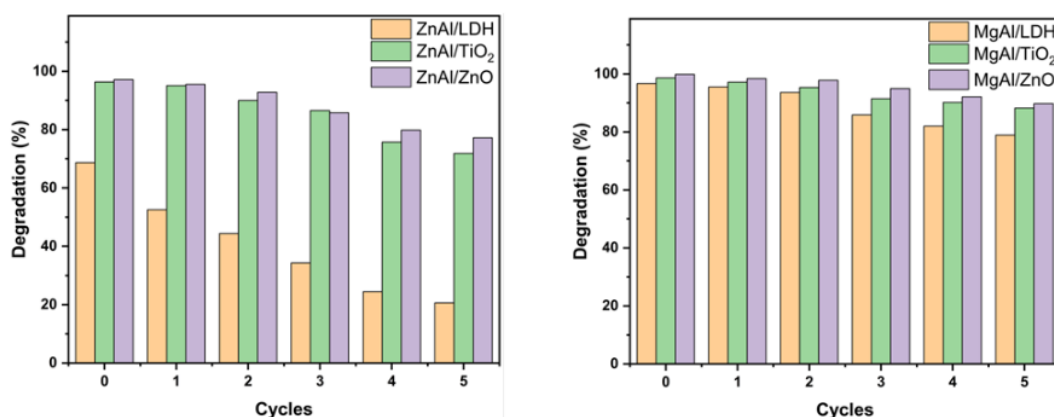


Figure 11. Reusability of pristine LDH and composite LDH in the fifth cycle.

1 than pristine LDH. LDH-ZnO composite has better activity, energy band gap and reusability degradation than LDH-TiO₂.

Acknowledgement

9 The authors profoundly thanks to Research Centre of Inorganic Materials and Complexes FMIPA Universitas Sriwijaya for instrumental analysis.

References

- [1] Mohadi, R., Palapa, N.R., Lesbani, A. (2021). Preparation of Ca / Al-Layered Double Hydroxides / Biochar Composite with High Adsorption Capacity and Selectivity toward Cationic Dyes in Aqueous. *Bulletin of Chemical Reaction Engineering & Catalysis*, 16(2), 244–252. DOI: 10.9767/brec.16.2.10211.244-252
- [2] Li, S., Wang, L., Li, Y.D., Zhang, L., Wang, A., Xiao, N., Gao, Y., Li, N., Song, W., Ge, L., Liu, J. (2019). Novel photocatalyst incorporating Ni-Co layered double hydroxides with P-doped CdS for enhancing photocatalytic activity towards hydrogen evolution. *Applied Catalysis B: Environmental*, 254, 145–155. DOI: 10.1016/j.apcatb.2019.05.001
- [3] Zhao, G., Zou, J., Li, C., Yu, J., Jiang, X., Zheng, Y., Hu, W., Jiao, F. (2018). Enhanced photocatalytic degradation of rhodamine B, methylene blue and 4-nitrophenol under visible light irradiation using TiO₂/MgZnAl layered double hydroxide. *Journal of Materials Science: Materials in Electronics*, 29(8), 7002–7014. DOI: 10.1007/s10854-018-8687-y
- [4] Yan, R.Q., Liu, G.H., Wang, Q.F., Liu, W., Song, C.L. (2016). Fast Photodegradation of Malachite Green using Nano-ZnO on Ceramic MgAl Carbonate Layered Double Hydroxides Support. *Chinese Journal of Chemical Physics*, 29(2), 241–244. DOI: 10.1063/1674-0068/29/cjcp1505104
- [5] Djeda, R., Mailhot, G., Prevot, V. (2020). Porous layered double hydroxide/TiO₂ photocatalysts for the photocatalytic degradation of orange II. *ChemEngineering*, 4(2), 1–15. DOI: 10.3390/chemengineering4020039
- [6] Hosseini, S.A., Akbari, M. (2016). ZnO/Mg-Al layered double hydroxides as a photocatalytic bleaching of methylene orange - A black box modeling by artificial neural network. *Bulletin of Chemical Reaction Engineering & Catalysis*, 11(3), 299–315. DOI: 10.9767/brec.11.3.570.299-315
- [7] Ryltsova, I., Tarasenko, E., Lebedeva, O. (2021). Photodecolorization of congo red dye in presence of Ni³⁺ layered double hydroxide. *BIO Web of Conferences*, 30, 02010. DOI: 10.1051/bioconf/20213002010
- [8] Li, Z., Chen, M., Hu, H., Zhang, Q., Tao, D. (2020). Mechanochemical synthesis of novel Pt modified ZnAl-LDH for effective ciprofloxacin photodegradation. *Journal of Solid State Chemistry*, 290, 290, 121594. DOI: 10.1016/j.jssc.2020.121594
- [9] Bhuvaneswari, K., Palanisamy, G., Pazhanivel, T., Maiyalagan, T., Bharathi, G. (2019). Photodegradation Activity of Nitrogen-rich Graphitic Carbon Nitride Intercalated ZnO\Mg-Al Layered Double Hydroxide Ternary Nanocomposites on Methylene Blue Dye. *ChemistrySelect*, 4(11), 2982–2990. DOI: 10.1002/slct.201900146
- [10] Ai, Z., Liu, C., Zhang, Q., Qu, J., Li, Z., He, X. (2018). Adding ZnO and SiO₂ to scatter the agglomeration of mechanochemically prepared Zn-Al LDH precursor and promote its adsorption toward methyl orange. *Journal of Alloys and Compounds*, 763, 342–348. DOI: 10.1016/j.jallcom.2018.05.201
- [11] Elhalil, A., Abdennouri, M., Sadiq, M., Kadmi, Y., Favier, L., Barka, N. (2018). Synthesis of Ba doped ZnO-Al₂O₃ nanocomposite from layered double hydroxide structure and their photocatalytic activity for the degradation of caffeine. *Journal of Applied Surfaces and Interfaces*, 4(1–3), 9–16. DOI: 10.4844/IMIST.PRSM/jasi-v4i1-3.12153.
- [12] Wu, J., Gong, Y., Fu, Q., Pan, C. (2019). NiFe-LDH@ZnO@NF composite for photodegradation of Rhodamine B dye. *MRS Advances*, 234, 1887. DOI: 10.1557/adv.2019.2.34
- [13] Mourid, E.H., El Mouchtari, E.M., El Mersly, L., Benaziz, L., Rafqah, S., Lakraimi, M. (2020). Development of a new recyclable nanocomposite LDH-TiO₂ for the degradation of antibiotic sulfamethoxazole under UVA radiation: An approach towards sunlight. *Journal of Photochemistry and Photobiology A: Chemistry*, 396, 112530. DOI: 10.1016/j.jphotochem.2020.112530
- [14] Jo, W.K., Kim, Y.G., Tonda, S. (2018). Hierarchical flower-like NiAl-layered double hydroxide microspheres encapsulated with black Cu-doped TiO₂ nanoparticles: Highly efficient visible-light-driven composite photocatalysts for environmental remediation. *Journal of Hazardous Materials*, 357, 19–29. DOI: 10.1016/j.jhazmat.2018.05.038
- [15] Aoudjit, F., Cherifi, O., Halliche, D. (2019). Simultaneously efficient adsorption and photocatalytic degradation of sodium dodecyl sulfate surfactant by one-pot synthesized TiO₂/layered double hydroxide materials. *Separation Science and Technology (Philadelphia)*, 54(7), 1095–1105. DOI: 10.1080/01496395.2018.1527352

- [16] Contreras-Ruiz, J.C., Martínez-Gallegos, S., García-Rivas, J.L., Illescas, J., González-Juárez, J.C., Miranda, G.M., Regil, E.O. (2019). Influence of the textural parameters of LDH-TiO₂ composites on phenol adsorption and photodegradation capacities. *International Journal of Photoenergy*, 2019. DOI: 10.1155/2019/5783507
- [17] Contreras-Ruiz, J.C., Martínez-Gallegos, M.S., Ordoñez-Regil, E. (2016). Surface fractal dimension of composites TiO₂-hydrotalcite. *Materials Characterization*, 121, 17–22. DOI: 10.1016/j.matchar.2016.09.032
- [18] Lesbani, A., Siregar, P.M.S.B.N., Palapa, N.R., Taher, T., Riyanti, F. (2021). Adsorptive removal methylene-blue using zn/al ldh modified rice husk biochar. *Polish Journal of Environmental Studies*, 30(4), 3117–3124. DOI: 10.15244/pjoes/130971
- [19] Rahmadan, J., Parhusip, V., Palapa, N.R., Taher, T., Mohadi, R., Lesbani, A. (2021). ZnAl-Humic Acid Composite as Adsorbent of Cadmium(II) From Aqueous Solution. *Science and Technology Indonesia*, 6(4), 247 - 255. DOI: 10.26554/sti.2021.6.4.247-255
- [20] Hu, Y.L., Wu, Z., Zheng, X., Lin, N., Yang, Y., Zuo, J., Sun, D., Jiang, C., Sun, L., Lin, C., Fu, Y. (2017). ZnO/ZnGaNO heterostructure with enhanced photocatalytic properties prepared from a LDH precursor using a coprecipitation method. *Journal of Alloys and Compounds*, 709, 42–53. DOI: 10.1016/j.jallcom.2017.02.124
- [21] Sepehr, M.N., Al-Musawi, T.J., Ghahramani, E., Kazemian, H., Zarrabi, M. (2017). Adsorption performance of magnesium/aluminum layered double hydroxide nanoparticles for metronidazole from aqueous solution. *Arabian Journal of Chemistry*, 10(5), 611–623. DOI: 10.1016/j.arabjc.2016.07.003
- [22] Ma, C., Wang, F., Zhang, C., Yu, Z., Wei, J., Yang, Z., Li, Y., Li, Z., Zhu, M., Shen, L., Zeng, G. (2017). Photocatalytic decomposition of Congo red under visible light irradiation using MgZnCr-TiO₂ layered double hydroxide. *Chemosphere*, 168, 80–90. DOI: 10.1016/j.chemosphere.2016.10.063
- [23] Zhang, L., Li, L., Sun, X., Liu, P., Yang, D., Zhao, X. (2016). ZnO-layered double hydroxide/graphitic carbon nitride composite for consecutive adsorption and photodegradation of dyes under UV and visible lights. *Materials*, 9(11), 927. DOI: 10.3390/ma9110927
- [24] Wijaya, A., Siregar, P.M.S.B.N., Priambodo, A., Palapa, N.R., Taher, T., Lesbani, A. (2021). Innovative Modified of Cu-Al/C (C = Biochar, Graphite) Composites for Removal of Procion Red from Aqueous Solution. *Science and Technology Indonesia*, 6(4), 228 - 234. DOI: 10.26554/sti.2021.6.4.228-234
- [25] Zhu, Y., Zhu, R., Zhu, G., Fay, D.L., Akhavan, S., Goldberg, V.M. (2018). Plasmonic Ag coated Zn/Ti-LDH with excellent photocatalytic activity. *Applied Surface Science*, 433, 458-467. DOI: 10.1016/j.apsusc.2017.09.236
- [26] Hadnadjev-Kostic, M., Vulic, T., Marinkovic-Neducin, R., Lončarević, D., Dostanić, J., Markov, S., Jovanović, D. (2017). Photo-induced properties of photocatalysts: A study on the modified structural, optical and textural properties of TiO₂-ZnAl layered double hydroxide based materials. *Journal of Cleaner Production*, 164, 1–18. DOI: 10.1016/j.jclepro.2017.06.091
- [27] Gholami, P., Khataee, A., Soltani, R.D.C., Dinpazhoh, L., Bhatnagar, A. (2020). Photocatalytic degradation of gemifloxacin antibiotic using Zn-Co-LDH@biochar nanocomposite. *Journal of Hazardous Materials*, 382, 121070. DOI: 10.1016/j.jhazmat.2019.121070
- [28] Motlagh, P.Y., Khataee, A., Hassani, A., Sadeghi Rad, T. (2020). ZnFe-LDH/GO nanocomposite coated on the glass support as a highly efficient catalyst for visible light photodegradation of an emerging pollutant. *Journal of Molecular Liquids*, 302, 112532. DOI: 10.1016/j.molliq.2020.112532
- [29] Li, D., Fan, L., Qi, M., Shen, Y., Liu, D., Li, S. (2018). Enhanced visible-light-driven photocatalytic activity of ZnAl layered double hydroxide by incorporation of Co²⁺. *Bulletin of Chemical Reaction Engineering & Catalysis*, 13(3), 502–511. DOI: 10.9767/brec.13.3.2168.502-511

Photocatalytic Degradation of Malachite Green by Layered Double Hydroxide Based Composites

ORIGINALITY REPORT

29%

SIMILARITY INDEX

17%

INTERNET SOURCES

20%

PUBLICATIONS

10%

STUDENT PAPERS

PRIMARY SOURCES

1	doaj.org Internet Source	6%
2	Submitted to Sriwijaya University Student Paper	4%
3	Yulizah Hanifah, Risfidian Mohadi, Mardiyanto Mardiyanto, Aldes Lesbani. "Polyoxometalate Intercalated MgAl-Layered Double Hydroxide for Degradation of Malachite Green", Ecological Engineering & Environmental Technology, 2023 Publication	3%
4	Submitted to Universitas Islam Indonesia Student Paper	2%
5	pdfs.semanticscholar.org Internet Source	1%
6	Risfidian Mohadi, Patimah Mega Syah Bahar Nur Siregar, Neza Rahayu Palapa, Tarmizi Taher, Aldes Lesbani. "Layered Double Hydroxide/Chitosan Composite (Mg-Al/CT) as	1%

a Selective Adsorbent in Congo Red Adsorption from Aqueous Solution", Ecological Engineering & Environmental Technology, 2022

Publication

-
- 7 Neza Palapa, Tarmizi Taher, Patimah Siregar, Normah Normah, Novie Juleanti, Alfian Wijaya, Arini Badri, Aldes Lesbani. "High Structural Stability and Adsorption Capacity of Zn/Al-Biochar and Cu/Al-Biochar Toward Adsorption of Cr(VI)", Journal of Ecological Engineering, 2021
Publication 1 %
-
- 8 S. A. Abdel Moaty, Rehab K. Mahmoud, Nada A. Mohamed, Yasser Gaber et al. "Synthesis and characterisation of LDH - type anionic nanomaterials for the effective removal of doxycycline from aqueous media", Water and Environment Journal, 2019
Publication <1 %
-
- 9 www.ukm.my
Internet Source <1 %
-
- 10 keep.lib.asu.edu
Internet Source <1 %
-
- 11 Barahuie, Farahnaz, Mohd Hussein, Sharida Fakurazi, and Zulkarnain Zainal. "Development of Drug Delivery Systems Based on Layered Hydroxides for

Nanomedicine", International Journal of
Molecular Sciences, 2014.

Publication

12

Ahmed, A.A.A.. "Thermal, optical and dielectric properties of Zn-Al layered double hydroxide", Applied Clay Science, 201202

Publication

<1 %

13

Huali Zuo, Weiyu Chen, Bei Li, Kewei Xu, Helen Cooper, Zi Gu, Zhi Ping Xu. "MnAl Layered Double Hydroxide Nanoparticles as a Dual-Functional Platform for Magnetic Resonance Imaging and siRNA Delivery", Chemistry - A European Journal, 2017

Publication

<1 %

14

link.springer.com

Internet Source

<1 %

15

Sumanta Sahu, Padmaja Kar, Nisarani Bishoyi, Laxmi Mallik, Raj Kishore Patel. "Synthesis of Polypyrrole-Modified Layered Double Hydroxides for Efficient Removal of Cr(VI)", Journal of Chemical & Engineering Data, 2019

Publication

<1 %

16

"Green Photocatalytic Semiconductors", Springer Science and Business Media LLC, 2022

Publication

<1 %

17 Aicha Aissani, Mostefa Kameche, Khalil Benabbou. " Synthesis and characterization of TiO /LDH layered double hydroxide composites: Utilization as photocatalysts for amoxicillin degradation under UVA irradiation ", Inorganic and Nano-Metal Chemistry, 2022
Publication

18 Liangcai Wang, Linen Xie, Xin Feng, Xiang Li, Huanhuan Ma, Guolin Han, Derui Yang, Jianbin Zhou. "Optimization process of porous carbon derived from coconut shell: A novel preparation condition and investigation on pore surface roughness", Diamond and Related Materials, 2022
Publication

19 www.sid.ir
Internet Source

20 Zhao Li, Qiwu Zhang, Xiaoman He, Min Chen. "Enhanced visible light photocatalytic activity of the mechanochemically prepared nanosized Zn x Cd 1-x S/Zn-Al layered double hydroxide precursor heterojunctions", Applied Clay Science, 2018
Publication

21 downloads.hindawi.com
Internet Source

22

Fatima Zahra Mahjoubi, Abderrahim Khalidi, Mohamed Abdennouri, Noureddine Barka. "Zn–Al layered double hydroxides intercalated with carbonate, nitrate, chloride and sulphate ions: Synthesis, characterisation and dye removal properties", Journal of Taibah University for Science, 2018

Publication

<1 %

23

J. C. Contreras-Ruiz, S. Martínez-Gallegos, J. L. García-Rivas, J. Illescas et al. " Influence of the Textural Parameters of LDH-TiO Composites on Phenol Adsorption and Photodegradation Capacities ", International Journal of Photoenergy, 2019

Publication

<1 %

24

ulster.pure.elsevier.com

Internet Source

<1 %

25

sciencetechindonesia.com

Internet Source

<1 %

26

Arini Fousty Badri, Novie Juleanti, Neza Rahayu Palapa, Yuliza Hanifah, Risfidian Mohadi, Mardiyanto Mardiyanto, Aldes Lesbani. "Oxalate Intercalated Mg/Cr Layered Double Hydroxide as Adsorbent of Methyl Red and Methyl Orange From Aqueous Solution", Ecological Engineering & Environmental Technology, 2021

Publication

<1 %

27 Eleonora Conterosito, Gianluca Croce, Luca Palin, Cinzia Pagano et al. "Structural characterization and thermal and chemical stability of bioactive molecule–hydrotalcite (LDH) nanocomposites", Physical Chemistry Chemical Physics, 2013
Publication

28 Lan Wang, Zhiqiang Zhu, Fu Wang, Yihao Qi, Wei Zhang, Chuanyi Wang. "State-of-the-art and prospects of Zn-containing layered double hydroxides (Zn-LDH)-based materials for photocatalytic water remediation", Chemosphere, 2021
Publication

29 Submitted to Pusan National University Library
Student Paper

30 Submitted to Universiti Pendidikan Sultan Idris
Student Paper

31 Zhao Li, Qiwu Zhang, Xinzhong Liu, Lei Wu, Huimin Hu, Yue Zhao. "One-step mechanochemical synthesis of plasmonic Ag/Zn–Al LDH with excellent photocatalytic activity", Journal of Materials Science, 2018
Publication

32 cjcp.ustc.edu.cn
Internet Source

33

eprints.qut.edu.au

Internet Source

<1 %

34

["Nanotechnology in Environmental Science", Wiley, 2018](#)

Publication

<1 %

35

[Hongtao Lu, Zhiliang Zhu, Hua Zhang, Jianyao Zhu, Yanling Qiu, Linyan Zhu, Stephan Küppers. "Fenton-Like Catalysis and Oxidation/Adsorption Performances of Acetaminophen and Arsenic Pollutants in Water on a Multimetal Cu-Zn-Fe-LDH", ACS Applied Materials & Interfaces, 2016](#)

Publication

<1 %

36

[Jiajun Nong, Yuexiang Jin, Jun Tan, Hongxia Ma, Yuan Lian. " The construction of NiCo-LDH/g-C N heterojunctions as efficient photocatalysts for enhanced degradation of tetracycline hydrochloride and hydrogen evolution ", New Journal of Chemistry, 2022](#)

Publication

<1 %

37

[Nawal Taoufik, Fatima Zahra Janani, Habiba Khair, Mhamed Sadiq et al. "MgO-La₂O₃ mixed metal oxides heterostructure catalysts for photodegradation of dyes pollutant: synthesis, characterization and artificial intelligence modelling",](#)

<1 %

Environmental Science and Pollution Research, 2022

Publication

38

Ridouan Benhiti, Abdeljalil Ait Ichou, Ahmed Zaghloul, Rachid Aziam et al. "Synthesis, characterization, and comparative study of MgAl-LDHs prepared by standard coprecipitation and urea hydrolysis methods for phosphate removal", Environmental Science and Pollution Research, 2020

Publication

<1 %

39

Zhao Li, Min Chen, Huimin Hu, Qiwu Zhang, Dongping Tao. "Mechanochemical synthesis of novel Pt modified ZnAl-LDH for effective ciprofloxacin photodegradation", Journal of Solid State Chemistry, 2020

Publication

<1 %

40

Ziqiang Ai, Changqing Liu, Qiwu Zhang, Jun Qu, Zhao Li, Xiaoman He. "Adding ZnO and SiO₂ to scatter the agglomeration of mechanochemically prepared Zn-Al LDH precursor and promote its adsorption toward methyl orange", Journal of Alloys and Compounds, 2018

Publication

<1 %

41

iopscience.iop.org
Internet Source

<1 %

42

Internet Source

<1 %

43

www.hindawi.com

Internet Source

<1 %

44

Aldes Lesbani, Hensen Hensen, Tarmizi Taher, Nurlisa Hidayati, Risfidian Mohadi, Roy Andreas. "Intercalation of Zn/Al layered double hydroxides with Keggin ion as adsorbent of cadmium(II)", AIP Publishing, 2018

Publication

<1 %

45

Pigna, Massimo, James J. Dynes, Antonio Violante, Alessia Sommella, and Antonio G. Caporale. "Sorption of Arsenite on Cu-Al, Mg-Al, Mg-Fe, and Zn-Al Layered Double Hydroxides in the Presence of Inorganic Anions Commonly Found in Aquatic Environments", Environmental Engineering Science, 2015.

Publication

<1 %

46

Qiang Wang, Dermot O'Hare. "Recent Advances in the Synthesis and Application of Layered Double Hydroxide (LDH) Nanosheets", Chemical Reviews, 2012

Publication

<1 %

47

Yanfeng Lu, Yu Huang, Jun-ji Cao, Wingkei Ho, Qian Zhang, Dandan Zhu, Shun Cheng Lee. "

<1 %

Insight into the Photocatalytic Removal of NO
in Air over Nanocrystalline Bi Sn O under
Simulated Solar Light ", Industrial &
Engineering Chemistry Research, 2016

Publication

48

Jianxing Liang, Ying Wei, Jianguo Zhang, Yan
Yao, Guangyu He, Bo Tang, Haiqun Chen. "
Scalable Green Method to Fabricate
Magnetically Separable NiFe O -Reduced
Graphene Oxide Nanocomposites with
Enhanced Photocatalytic Performance Driven
by Visible Light ", Industrial & Engineering
Chemistry Research, 2018

Publication

<1 %

Exclude quotes Off

Exclude matches Off

Exclude bibliography On