

5. sudiyani2017.pdf

Optimization pretreatment condition of sweet sorghum bagasse for production of second generation bioethanol

Yanni Sudyani, Joko Waluyo, Eka Triwahyuni, Dian Burhani, Muryanto, Prasetyo Primandaru, Andika Putra Riandy, and Novia Sumardi

Citation: *AIP Conference Proceedings* **1803**, 020015 (2017); doi: 10.1063/1.4973142

View online: <http://dx.doi.org/10.1063/1.4973142>

View Table of Contents: <http://aip.scitation.org/toc/apc/1803/1>

Published by the American Institute of Physics

30

Articles you may be interested in

16 Statistical analysis of NaOH pretreatment effects on sweet sorghum bagasse characteristics
AIP Conference Proceedings **1803**, 020008020008 (2017); 10.1063/1.4973135

15 Degradation of black liquor from bioethanol process using coagulation and Fenton-like methods
AIP Conference Proceedings **1803**, 020007020007 (2017); 10.1063/1.4973134

5 Effect of coagulant/flocculant dosage and pH to water recovery of black liquor wastewater in bioethanol production from oil palm empty fruit bunch using response surface methodology
AIP Conference Proceedings **1803**, 020004020004 (2017); 10.1063/1.4973131

18 Lipid extraction of wet BLT0404 microalgae for biofuel application
AIP Conference Proceedings **1803**, 020006020006 (2017); 10.1063/1.4973133

Optimization Pretreatment Condition of Sweet Sorghum Bagasse for Production of Second Generation Bioethanol

Yanni Sudiyani^{1,a)}, Joko Waluyo¹⁾, Eka Triwahyuni¹⁾, Dian Burhani¹⁾, Muryanto¹⁾, Prasetyo Primandaru²⁾, Andika Putra Riandy²⁾, Novia Sumardi²⁾

¹Research Center for Chemistry, Indonesian Institute of Sciences (LIPI), Kawasan PUSPIPTEK Serpong, Tangerang Selatan, Indonesia

²Chemical Engineering Department, Sriwijaya University, Palembang

^{a)}Corresponding author: sudiyani@gmail.com

Abstract. The bagasse residue of Sweet sorghum (*Sorghum bicolor* (L.) Moench) consist of cellulose 39.48%; hemicellulose 16.56% and lignin 24.77% that can be converted to ethanol. Pretreatment is of great importance to ethanol yield. In this study, pretreatment process was conducted in a 5-liter reactor using NaOH 10% at various temperature 110, 130, 150°C and reaction time 10, 20, 30 minutes and optimizing severity parameter (log R_0 between 1.3 - 2.9). The statistical analysis using two way anova showed that third variations of temperature give different effects significant on lignin, hemicellulose and cellulose content at 95% the confidence level. The optimum pretreatment of bagasse sorghum were obtained with Log R_0 value between 2.4-2.9. High severity value in pretreatment condition reduce lignin almost 84-86%, maximum reducing lignin content was 86% obtained at temperature 150°C for 20 minutes reaction time and cellulose increased almost two times the initial content.

INTRODUCTION

Today bioethanol has become one of prospective biofuels in the transportation sector. Most of bioethanol produced in Indonesia currently is from molasses, or starchy raw materials, such as cassava and corn, known first generation bioethanol (G1). These materials are important raw materials for producing food and supporting food industries, so will not be sufficient to meet the increasing demand for the fuel ethanol [1]. On the other side, there are large amount of abundantly lignocellulosic biomass wastes of agricultural, estate crops and forestry industries that has not been used, can be converted to ethanol, called as second generation bioethanol (G2), is a possible candidate for a cheap and renewable source of energy.

The bagasse residue after extracting the juice from the sweet sorghum stalk is lignocellulosic material that consist of cellulose hemicellulose and lignin, these material can be hydrolyzed into sugar and further fermented to ethanol [2]. On the conversion of lignocellulosic to ethanol, need three key steps i.e. pretreatment to modify the lignocellulose structure, enzymatic hydrolysis to obtain sugars and fermentation process. Pretreatment of lignocellulose has received considerable research globally due to its influence on the technical, economic and environmental sustainability of cellulosic ethanol production. For developing countries, alkali-based methods are relatively easy to deploy in decentralized, low-tech systems owing to advantages such as the requirement of simple reactors and the easy of operation.

25 Alkaline pretreatment is the target to reduce lignin content to increase enzyme access to holocellulose [3,4], reduction of cellulose crystallinity [5,6], and increase 17 in the surface area [7,8] and porosity [9,10] of pretreated substrates, resulting in increased hydrolysis rate. The mechanism of alkaline pretreatment is saponification of intermolecular ester bonds crosslinking 9ylan, hemicelluloses and other component [11,12].

To fully utilize bagasse residue of sweet sorghum as a feedstock for ethanol product 19 optimal pretreatment is required to render the cellulose fiber more amenable to the action of hydrolyze enzyme. The main goal of this 22 work is to study the effect pretreatment of alkaline NaOH 10% concentration, reaction time and temperature on the sweet sorghum bagasse as raw material for ethanol production, function of pretreatment time and temperature was investigated to optimize the operating parameter of pretreatment, while glucose production is the parameter for evaluating allow enzymatic performance.

MATERIALS AND METHODS

Materials

Bagasse of Sweet Sorghum (*Sorghum bicolor* (L.) Moench) called (BS) was obtained from PT. Panen Energy, Malang East Java, Indonesia. After air-dried, physical pretreatment i.e. chipping and milling until 3 mm was conducted to maximize contact area of the substrate.

Alkaline Pretreatment

24 In this work optimization process of pretreatment was conducted using bench scale reactor a 5-liter at the Research Centre for Chemistry, Indonesian Institute of Sciences (LI 10 250 g of BS (10% moisture content) was heated using NaOH 10% (kg/L) at 110,130 and 150°C for 70, 20 and 30 minutes. A solid liquid ratio was 1:5. The pressure was controlled four bars at early heating. After pretreatment, the material was pressed in order to separate solidity from liquid fraction. Solidity of BS treated was washed until wash water turned to pH 7 and 20 dried in the oven at 50-60°C overnight. The composition of materials component before and after pretreatment was analyzed according to National Renewable Energy Laboratory (NREL) standard procedures [13].

The treatment severity was quantified by a semi-empirical parameter called severity parameter, $\log R_0$, combining pretreatment time and temperature according to the equation Overend, 1987, [14].

$$R_0 = t.e^{\left[\frac{7.00}{14.75}\right]} \quad (1)$$

where t is the time in minute and T the temperature in degree Celcius.

TABLE 1. Severity Factor of Experiment

Pretreatment		Log R ₀
Temperature (°C)	Time (min)	
110	10	1.3
110	20	1.6
110	30	1.8
130	10	1.9
130	20	2.2
130	30	2.4
150	10	2.5
150	20	2.8
150	30	2.9

Enzymatic Hydrolysis

Two Enzyme cellulase Cellic[®]CTec2 and Cellic[®]HTec2 were applied for hydrolysis (saccharification) process of pretreated BS. Cellic[®]CTec2 is complex enzymes that consist of cellulase, β -glucosidase, and hemicellulase whereas Cellic[®]HTec2 consists of endoxylanase with high specificity toward soluble hemicellulose and cellulase. Hemicellulose could be converted to x₁₀ because Cellic[®]CTec2 has hemicellulase and Cellic[®]HTec2 has endoxylanase using combined enzymes. The activity of Cellic[®]CTec2 is 144 FPU·g⁻¹ cellulose (measured by NREL method) [15], while the activity of Cellic[®]HTec2 is 240 CBU·g⁻¹ (reported by Novozyme). In this study, the saccharification applied Cellic[®]CTec2 of 30 FPU·g⁻¹ dry biomass and one-fifth of Cellic[®]CTec2 (v/v) for Cellic[®]HTec2. The optimum hydrolysis condition for enzyme provided by company of Novozyme was temperature and velocity agitation was set 50°C and 150 rpm respectively.

Duplicate process was arranged to get the best approach 23 the samples, containing pretreated 15% (g/ml) in the erlenmeyer flask containing 0.05 M the buffer citrate with pH 4.8, v₂re autoclaved at 121°C for 20 minutes. After cooling, 30 FPU of Cellic[®]CTec2 per gram d₂ biomass and 20% Cellic[®]HTec2 was added for each. All of the samples were placed in the shaking incubator. Sampling every 24 hour was employed to monitor producing sugar, glucose and xylose were measured as a product in this hydrolysis.

Statistical analysis

The content of chemical component of cellulose, hemicellulose, lignin, sugar and ethanol were analyzed with Two Way ANOVA procedurs using the software SPSS 16 and statistical significance confidance of 95% to evaluate the significant differences among mean treatments.

RESULT AND DISCUSSION

Pretreatment Condition

Pretreatment using alkali solution such as NaOH, CaOH or amonia can remove lignin and a part of hemicelluloses that caused weight loss [14,15]. In these study pretreatment process of BS was conducted with NaOH 10% (kg/L), biomass quantity each pretreatment was 250 g. After treatment and followed wash neutralization and dried, the mass was measured to calculate biomass recovery, the result as shown in Table 2.

TABLE 2. Pretreated Samples Results

Pretreatment		After Treatment Charged Dry Matter (g)	Weight Loss (g)	Yield %	Recovered Biomass (%)
Temperature (°C)	Time (min)				
110	10	150.27	99.73	39.89	60.11
110	20	149.28	100.72	40.29	59.71
110	30	103.51	146.49	58.60	41.40
130	10	134.28	115.72	46.29	53.71
130	20	149.34	100.66	40.26	59.74
130	30	139.17	110.83	44.33	55.67
150	10	154.43	95.57	38.23	63.44
150	20	158.59	128.60	51.44	65.56
150	30	163.89	86.11	34.44	63.44

After pretreatment, showed that some pretreatment results in terms of pretreatment efficiency is expressed as recovered biomass in percentage compared to initial biomass charged into the reactor. Dilute NaOH application loosens the biomass structure, separate the bonds between the lignin and the carbohydrates, increases the internal surface, decreases the degree of polymerization and crystallinity, and disrupts the lignin structure, that caused weight loss [15,16]. Highest recovered biomass was observed at temperature 150°C.

Composition components of Pretreated substrates

Before pretreatment the carbohydrate fraction of BS (cellulose and hemicellulose) were 56.04% of total biomass, and the major component were cellulose (39.48%). Meanwhile, lignin content of BS was 24.77%, comparable to the lignin content of empty of fruit bunch (25.83%) [17]. Lignocellulosic biomass requires pretreatment, mainly because the lignin in plant cell walls forms a barrier against enzyme attack. An ideal pretreatment reduces the lignin content and crystallinity of the cellulose and increase surface area [18]. The loss of lignin in the pretreatment is one of the most important indicators of pretreatment effectiveness because the presence of lignin impedes enzymatic hydrolysis of the carbohydrates [15]. In order to degrade and reduce the lignin and non-cellulose component, BS was treated using alkaline solution NaOH 10%, nine samples were selected for the following stage, in the range Log R₀ 1.3-2.9. The effect of NaOH 10% at different temperature and different times pretreatment. After treatment at all condition, the BS was quantified for lignocellulose components, the results as shown in Tabel 3.

Pretreatment changed the BS composition. From Table 3 it can be seen during pretreatment delignification was occurred and the process was effective for reduction of hemicellulose, so the proportion of lignin decreased, and the cellulose content after pretreatment was increased in all pretreatment condition. The results shows the optimum pretreatment condition was NaOH 10% at 150°C for 10-30 minutes, with the optimum loss of lignin and hemicellulose was 86%, and 55% respectively. Further increasing reaction time also affected in increase of cellulose content from 10 to 20 minutes and there was no significant effect reaction time after 20 minutes. The optimum cellulose content was 86.85% was achieved at 150°C for 20 minutes. Comparing the two parameter, we observe an approximately constant trend which does influence of recovered biomass in line with cellulose content after treatment. The increase of cellulose content and the decrease of hemicellulose and lignin content can facilitate the process of enzymatic hydrolysis.

TABLE 3. Chemical Composition of Bagasse Sweet Sorghum

Pretreatment Temperature (°C), Time (min)	Cellulose %	Hemicellulose %	Lignin %	Ash %
Untreated	39.48	16.56	24.77	4.20
110, 10	76.52	10.03	8.61	0.16
110, 20	78.06	9.94	8.31	0.32
110, 30	84.03	9.93	8.08	0.28
130, 10	81.74	8.87	6.16	0.25
130, 20	83.32	9.37	6.11	0.37
130, 30	88.25	8.57	5.45	0.55
150, 10	86.72	7.37	3.76	0.25
150, 20	86.85	7.45	3.51	0.52
150, 30	86.44	7.50	3.49	0.53

Further investigation for pretreatment parameters were carried out, using the analysis of two way ANOVA, to identify which parameter significantly affect the component cellulose, hemicellulose and lignin.

TABLE 4. ANOVA

Source	DF	Lignin				Hemicellulose				Cellulose			
		SS	MS	F	Sig	SS	MS	F	Sig	SS	MS	F	Sig
Corrected Model	8	68.16	8.52	2479	0.00	21.43	2.68	419.25	0.00	268.83	33.60	100.89	0.00
Intercept	1	636.40	636.40	185200	0.00	1380.17	1380.17	216000	0.00	125646.25	125646.25	377200	0.00
Temperature	2	67.19	33.59	9774	0.00	20.74	10.37	1623	0.00	159.75	79.87	239.80	0.00
Time	2	0.73	0.36	105.51	0.00	0.20	0.10	15.83	0.00	68.67	34.33	103.08	0.00
Temperature*Time	4	0.25	0.06	18.33	0.00	0.49	0.12	18.97	0.00	40.42	10.11	30.34	0.00
Error	9	0.03	0.00			0.06	0.01			3.00	0.33		
Total	18	704.60				1401.66				125918.08			
Corrected Total	17	68.19				21.49							
R Squared (Adjst. R Squared)		1.00 (0.999)				0.997 (0.995)				0.989 (0.979)			

Considering parameter condition, optimal pretreatment seem to move towards higher Log R₀ 2.4. In these study best results in terms of raw material (cellulose content 39,48%) was obtained at temperatur 150°C. These results in line with the statistical analysis using two way anova showed that third variations of temperature give different effects significant on lignin, hemicellulose and cellulose content at 95% the confidence level.

Considering the overall process, optimum pretreatment of bagasse sorghum were obtained with Log R₀ value between 2.4-2.9. High severity value in pretreatment condition resulted high in reduce lignin almost 84-86%, maximum reducing lignin content was 86% obtained at temperatur 150°C for 20 minutes reaction time and cellulose increased almost two times the initial content.

Enzymatic hydrolysis of treated substrate

Enzymatic hydrolysis is a step after pretreatment for bioethanol production. The BS substrate treated by NaOH 10% at 150°C was subjected to enzymatic saccharification. This condition was selected based on the highest component of cellulose of BS treated for 10, 20 and 30 minutes was 86.44-86.85% and the lowest component of lignin at 3.49-3.76%. The BS substrate was treated with commercial cellulase preparation at enzyme loading 30 FPU/g substrate. The result can be seen in Figure 1.

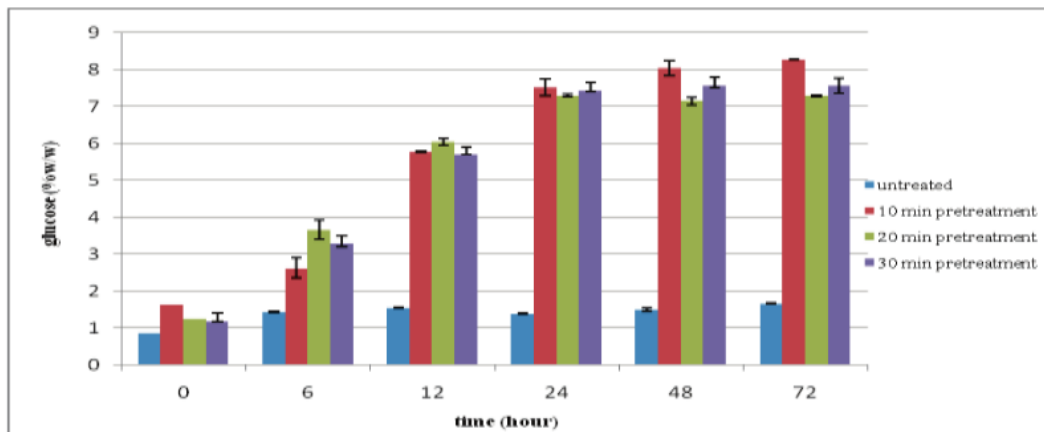


FIGURE 1. Glucose concentration from enzymatic hydrolysis of pretreated substrates with alkaline pretreatment at 150°C and reaction time 10, 20 and 30 minutes

Figure 1 showed that glucose concentration from each substrates increased for 72 h of enzymatic hydrolysis. The treated substrates produced higher glucose concentration than untreated substrate. It is because of reduction of lignin content, reduction of cellulose crystallinity and increasing porosity of treated substrates. The highest concentration of glucose concentration can be obtained by pretreatment substrate at 150oC, 10 minutes. The optimum time for enzymatic hydrolysis was 48 h that produce glucose almost similar with 72 h, i.e. above 8% w/w. From the data can be conclude that alkaline pretreatment at 150oC, 10 minutes has been enough to produce high glucose concentration.

CONCLUSIONS

Considering the overall process, optimum pretreatment of bagasse sorghum were obtained at Log R0 value between 2.4-2.9. Based on the results, pretreatment at 150oC gives the highest of cellulose content and the lowest of lignin content. The pretreatment condition of bagasse sorghum at 150oC for 10 minutes produces the optimal glucose concentration for bioethanol production.

ACKNOWLEDGEMENTS

The authors are in deeply indebted to Hendris Hendarsyah Kurniawan, and Novita Ariani for their technical support and cooperation.

REFERENCES

1. Lijun Wang, Zhenglin Luo, Abolghasem Shahbazi. Optimization of simultaneous saccharification and fermentation for the production of ethanol from sweet sorghum (*Sorghum bicolor*) bagasse using response surface methodology. *Industrial Crops and Products*. 2013; 42: 280-291.
2. Shen,F., Saddler, J.N.,Liu,R.,Lin,L., Deng,S., Zhang,Y., Yang,G., Xiao,H., Li,Y. Evaluation of Steam pretreatment on sweet sorghum bagasse for enzymatic hydrolysis and bioethanol production. *Carbohydrate Polymers*. 2011; 86: 1542-1548.
3. J. S. Lim, Z. Abdul Manan, S. R. Wan Alwi, and H. Hashim. A review on utilisation of biomass from rice industry as a source of renewable energy," *Renewable and Sustainable Energy Reviews*. 2012; 16, (5): 3084–3094.
4. Y. Z. Pang, Y. P. Liu, X. J. Li, K. S. Wang, and Yuan, H. R. Improving biodegradability and biogas production of corn stover through sodium hydroxide solid state pretreatment. *Energy and Fuels*, 2008; 22 (4): 2761–2766.
5. J. Gabhane, S. P. M. Prince William, A. N. Vaidya, K. Mahapatra, and T. Chakrabarti. Influence of heating source on the efficacy of lignocellulosic pretreatment—a cellulosic ethanol perspective. *Biomass and Bioenergy*. 2011; 35(1) : 96–102.
6. Y. Kim, R. Hendrickson, N. S. Mosier et al., "Enzyme hydrolysis and ethanol fermentation of liquid hot water and AFEX pretreated distillers' grains at high-solids loadings," *Bioresource Technology*, 2008; 99 (12) :5206–5215.
7. J.-S. Lee, B. Parameswaran, J.-P. Lee, and S.-C. Park, "Recent developments of key technologies on cellulosic ethanol production," *Journal of Scientific and Industrial Research*, vol. 67, no. 11, pp. 865–873, 2008.
8. Y. Li, R. Ruan, P. L. Chen et al., "Enzymatic hydrolysis of corn stover pretreated by combined dilute alkaline treatment and homogenization," *Transactions of the American Society of Agricultural Engineers*. 2004; 47(3); 821–825.
9. P. Harmsen, W. Huijgen, L. Bermudez, and R. Bakker. Literature review of physical and chemical pretreatment processes for lignocellulosic biomass," Tech. Rep. 1184, Biosynergy, Wageningen UR Food & Biobased Research, 2010.
10. J.-W. Lee and T. W. Jeffries, "Efficiencies of acid catalysts in the hydrolysis of lignocellulosic biomass over a range of combined severity factors," *Bioresource Technology*. 2011;102(10): 5884–5890, 2011.
11. Zhu, S., Wu, Y., Yu, Z., Chen, Q., Wu, G., Yu, F., Wang, C. and Jin, S. Microwave-assisted alkali pretreatment of wheat straw and its enzymatic hydrolysis. *Process Biochemistry*. 2006; 94 (3):437-442.
12. Zhao, Y., Wang, Y., Zhu, J.Y., Ragauskas, A. and Dengl, Y. Enhanced enzymatic hydrolysis of Spruce by Alkaline Pretreatment at Low Temperature. *Biotechnology and Bioengineering*, 2008; 99 (6).
13. Overend, R.p. et al. Fractionation of lignocellulosic by steam –aqueous pre-treatment., *Phil.Trans.R.Soc.Lond.A*; 1987: 523-536.
14. Sluiter, B., Hames, R., Ruiz, C., Scarlata, J., Sluiter, D., Templeton, M., and Crocker, D. Determination of structural carbohydrates and lignin in biomass. *Technical report NREL/TP-510-Int. J. Environ. Bioener.* 2012, 3(2): 88-97Copyright.
15. Mosier N., Wyman,C., Dale B., et al., Features of promising technologies for pretreatment of lignocellulosic biomass. *Bioresource Technology*. 2005;96 (6): 673–686.
16. Rocha GJMR, Nascimento VM, Silva FMN, Corso DLS,Goncalves AR. Contributing to the environmental sustainability of the secondgeneration ethanol production:Delignification of sugarcane bagassewith sodium hydroxide recycling. *Industrial Crops and Products*. 2014; 59: 63–68.
17. Sudiyani, Y., Kiky C. Sembiring., hendarsyah H., Alawiyah, S. Alkaline pretreatment and enzymatic saccharification of oil palm empty fruit bunch fiber for ethanol production. *Indonesian J. of Biotechnology Reaserach on Estate Crops*. 2010 (78) 2 : 74-78.
18. Silverstein, R. A. Chen, Y., Sharma-Shivappa, R. R., Boyette, M. D. and J. Osborne, "A comparison of chemical pretreatment methods for improving saccharification of cotton stalks," *Bioresource Technology*. 2007;98(16): 3000–3011.

5. sudiyani2017.pdf

ORIGINALITY REPORT

20%

SIMILARITY INDEX

PRIMARY SOURCES

- 1 Franco Cotana, Gianluca Cavalaglio, Mattia Gelosia, Andrea Nicolini, Valentina Coccia, Alessandro Petrozzi. "Production of Bioethanol in a Second Generation Prototype from Pine Wood Chips", Energy Procedia, 2014
39 words — 1%
Crossref
- 2 Yanni Sudiyani, Eka Tri Wahyuni, Muryanto Muryanto, Sephtian Marno, Nelizza Putri. "Bioethanol Production from Alkali Steam Explosion of Oil Palm of Empty Fruit Bunch Fiber", IOP Conference Series: Materials Science and Engineering, 2020
36 words — 1%
Crossref
- 3 Yulin Zhao, Ying Wang, J.Y. Zhu, Art Ragauskas, Yulin Deng. "Enhanced enzymatic hydrolysis of spruce by alkaline pretreatment at low temperature", Biotechnology and Bioengineering, 2008
35 words — 1%
Crossref
- 4 S. Hari Krishna, K. Prasanthi, G.V. Chowdary, C. Ayyanna. "Simultaneous saccharification and fermentation of pretreated sugar cane leaves to ethanol", Process Biochemistry, 1998
34 words — 1%
Crossref
- 5 M. Ettoumi, M. Jouini, C.M. Neculita, S. Bouhlel, L. Coudert, I. Haouech, M. Benzaazoua. "Characterization of Kef Shfeir phosphate sludge (Gafsa,

Tunisia) and optimization of its dewatering", Journal of Environmental Management, 2020

Crossref

6 www.iges.or.jp 27 words — 1%

Internet

7 Isabella De Bari, Federico Liuzzi, Antonio Villone, Giacobbe Braccio. "Hydrolysis of concentrated suspensions of steam pretreated Arundo donax", Applied Energy, 2013 25 words — 1%

Crossref

8 Zhang, Q.. "Enzymatic hydrolysis of alkali-pretreated rice straw by Trichoderma reesei ZM4-F3", Biomass and Bioenergy, 2008 24 words — 1%

Crossref

9 Jianliang Yu, Jing Zhong, Xu Zhang, Tianwei Tan. "Ethanol Production from H₂SO₃-Steam-Pretreated Fresh Sweet Sorghum Stem by Simultaneous Saccharification and Fermentation", Applied Biochemistry and Biotechnology, 2008 22 words — 1%

Crossref

10 Teuku Beuna Bardant, Deliana Dahnum, Nur Amaliyah. "Simultaneous or separated; comparison approach for saccharification and fermentation process in producing bio-ethanol from EFB", AIP Publishing, 2017 22 words — 1%

Crossref

11 Ni Ketut Sari, Intan Yuniar Purbasari. "pH Optimization in Pretreatment Process from Liquid Waste of Tapioca Flour with Response Surface Method", 2021 IEEE 7th Information Technology International Seminar (ITIS), 2021 19 words — 1%

Crossref

-
- 12 eprints.undip.ac.id 18 words — 1%
Internet
-
- 13 Muryanto, Eka Triwahyuni, Haznan Abimayu, Agung Cahyono, Effendi Tri Cahyono, Yanni Sudiyani. "Alkaline Delignification of Oil Palm Empty Fruit Bunch Using Black Liquor from Pretreatment", *Procedia Chemistry*, 2015 16 words — 1%
Crossref
-
- 14 www.scirp.org 16 words — 1%
Internet
-
- 15 Ajeng Arum Sari, Feni Amriani, Rifahny Intan Satria Akhmad, Muhammad Rylo Pambudi, Rievan Putra Pamungkas, Muryanto Muryanto. "Adsorption of acid red and acid orange with adsorbent from bioethanol black liquor sludge", *AIP Publishing*, 2018 15 words — 1%
Crossref
-
- 16 Ting-Ting Jiang, Yan Liang, Xiang Zhou, Zi-Wei Shi, Zhi-Jun Xin. "Optimization of a pretreatment and hydrolysis process for the efficient recovery of recycled sugars and unknown compounds from agricultural sweet sorghum bagasse stem pith solid waste", *PeerJ*, 2019 15 words — 1%
Crossref
-
- 17 W.-L. Sun, W.-Y. Tao. "Simultaneous Saccharification and Fermentation of Rice Straw Pretreated by a Sequence of Dilute Acid and Dilute Alkali at High Dry Matter Content", *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects*, 2013 15 words — 1%
Crossref
-
- 18 Arif Rahman, Nining Betawati Prihantini, Nasruddin. "Fatty acid of microalgae as a potential feedstock for biodiesel production in Indonesia", *AIP Publishing*, 2019 12 words — < 1%

19 Jamal, MS, SMA Sujan, MY Miah, SK Banik, SU Ahmed, and B Feroza. "Ball Milling Pretreatment of Bagasse for Ethanol Production by Enzymatic Saccharification and Fermentation", Bangladesh Journal of Scientific and Industrial Research, 2011. 12 words — < 1%

Crossref

20 Biotechnology for Fuels and Chemicals, 2008. 11 words — < 1%

Crossref

21 P.R. Mohan, B. Ramesh, O.V.S. Reddy. "Production and Optimization of Ethanol from Pretreated Sugarcane Bagasse using *Saccharomyces bayanus* in Simultaneous Saccharification and Fermentation", Microbiology Journal, 2012 10 words — < 1%

Crossref

22 Matsakas, Leonidas, and Paul Christakopoulos. "Fermentation of liquefacted hydrothermally pretreated sweet sorghum bagasse to ethanol at high-solids content", Bioresource Technology, 2013. 9 words — < 1%

Crossref

23 Peyman Salehian, Keikhosro Karimi. "Alkali Pretreatment for Improvement of Biogas and Ethanol Production from Different Waste Parts of Pine Tree", Industrial & Engineering Chemistry Research, 2013 9 words — < 1%

Crossref

24 Vera BARLIANTI, Deliana DAHNUM, . MURYANTO, Eka TRIWAHYUNI, Yosi ARISTIAWAN, Yanni SUDIYANI. "Enzymatic hydrolysis of oil palm empty fruit bunch to produce reducing sugar and its kinetic Hidrolisis enzimatik tandan kosong kelapa sawit untuk menghasilkan gula 9 words — < 1%

- 25 Benkun Qi, Xiangrong Chen, Fei Shen, Yi Su, Yinhua Wan. "Optimization of Enzymatic Hydrolysis of Wheat Straw Pretreated by Alkaline Peroxide Using Response Surface Methodology", Industrial & Engineering Chemistry Research, 2009

8 words — < 1%

Crossref

- 26 Florian Monlau, Abdellatif Barakat, Eric Trably, Claire Dumas, Jean-Philippe Steyer, Hélène Carrère. "Lignocellulosic Materials Into Biohydrogen and Biomethane: Impact of Structural Features and Pretreatment", Critical Reviews in Environmental Science and Technology, 2013

8 words — < 1%

Crossref

- 27 Muryanto, , Eka Triwahyuni, Hendris Hendarsyah, and Haznan Abimanyu. "Reuse Black Liquor of Alkali Pretreatment in Bioethanol Production", Energy Procedia, 2015.

8 words — < 1%

Crossref

- 28 Zehui Jiang, Benhua Fei, Zhiqiang Li. "Pretreatment of bamboo by ultra-high pressure explosion with a high-pressure homogenizer for enzymatic hydrolysis and ethanol fermentation", Bioresource Technology, 2016

8 words — < 1%

Crossref

- 29 scholarbank.nus.edu.sg

Internet

8 words — < 1%

- 30 discovery.ucl.ac.uk

Internet

6 words — < 1%

EXCLUDE QUOTES ON

EXCLUDE SOURCES OFF

EXCLUDE BIBLIOGRAPHY ON

EXCLUDE MATCHES OFF